

Majorana bound states in encapsulated bilayer graphene

Fernando Peñaranda, Ramón Aguado, Elsa Prada and Pablo San-Jose

Instituto de Ciencia de Materiales de Madrid, Consejo Superior de Investigaciones Científicas (ICMM-CSIC), Madrid, Spain

Abstract

The search for robust topological superconductivity and Majorana bound states continues, exploring both one-dimensional (1D) systems such as semiconducting nanowires and two-dimensional (2D) platforms. In this work we study a 2D approach based on graphene bilayers encapsulated in transition metal dichalcogenides that, unlike previous proposals involving the Quantum Hall regime in graphene, requires weaker magnetic fields and does not rely on interactions. The encapsulation induces strong spin-orbit coupling on the graphene bilayer, which opens a sizeable gap and stabilizes fragile pairs of helical edge states. We show that, when subject to an in-plane Zeeman field, armchair edges can be transformed into p-wave one-dimensional topological superconductors by contacting them laterally with conventional superconductors. We demonstrate the emergence of Majorana bound states (MBSs) at the sample corners of crystallographically perfect flakes, belonging either to the D or the BDI symmetry classes depending on parameters. We compute the phase diagram, the resilience of MBSs against imperfections, and their manifestation as a 4π -periodic effect in Josephson junction geometries, all suggesting the existence of a topological phase within experimental reach.



Copyright F. Peñaranda *et al.*

This work is licensed under the Creative Commons

[Attribution 4.0 International License](https://creativecommons.org/licenses/by/4.0/).

Published by the SciPost Foundation.

Received 24-06-2022

Accepted 17-01-2023

Published 18-04-2023

doi:[10.21468/SciPostPhys.14.4.075](https://doi.org/10.21468/SciPostPhys.14.4.075)



Check for updates

Contents

1	Introduction	2
2	Edge modes in encapsulated bilayer graphene	4
3	Superconducting proximity effect and Majoranas	6
4	BDI-class Majorana pairs	8
5	Effect of disorder and misalignment	11
6	Josephson effect	11
7	Conclusion	13
A	Resilience of helical modes in the presence of arbitrary edge orientation and scalar disorder	14
	References	16

1 Introduction

Majorana bound states (MBSs) were predicted by Kitaev in 2001 [1] as the fractionalized, zero-energy, protected fermion states that develop at the boundaries of one-dimensional (1D) topological superconductors. Interest in these states quickly grew past fundamental research, as it was realized that their spatial wavefunction non-locality could enable, in principle, scalable protection of quantum information [2–7]. A practical proposal to engineer MBSs in proximitized Rashba nanowires was made by Oreg. *et al.* and Lutchyn *et al.* a few years later [8, 9], soon followed by the first experiments [10], which revealed promising hints of potential MBSs. Since these hallmark results the story of MBSs in nanowires has grown increasingly complex [11, 12]. Remarkable fabrication improvements and careful experimental characterization [13, 14] have now clearly confirmed the existence of zero modes in these systems [15], but have also revealed significant interpretation issues and departures from theoretical expectation in their behavior [11]. The reasons are varied, and are thought to include disorder [16, 17], electrostatics [18, 19], metallization [20] and non-topological near-zero energy states due to confinement effects, including quantum dot formation [21, 22] and smooth potentials [23–26]. One decade after their theoretical proposal, proximitized nanowires have evolved into the most studied and advanced solid state platform for topological superconductivity. However, we have still not been able to conclusively demonstrate the predicted topological MBSs, let alone harness their potential for quantum computation.

This state of affairs has pushed numerous researchers to explore alternative experimental platforms for topological superconductivity (TSC), including atomic chains [27, 28], 2D semiconducting heterostructures [29, 30], planar Josephson junctions [31, 32], full-shell nanowires [22, 33], graphene-based platforms [34, 35], several 2D crystals [36–38] and van der Waals heterostructures [39]. Many of the proposals for 1D TSCs start from the basic Fu-Kane recipe [40, 41]: couple an s-wave superconductor to a 1D spinless electron liquid with finite helicity (i.e. to non-degenerate 1D modes with some degree of spin-momentum locking, such as the edge states of a 2D Quantum Spin Hall system [42, 43]). The s-wave pairing opens a finite p-wave TSC gap on the helical liquid [4], and gives rise to zero-energy MBSs at boundaries with trivial gaps. The various implementations of this recipe typically differ in the mechanism that generates the spinless helical phase. For example, in the original 1D Rashba nanowires proposal [8, 9] it is a combination of Rashba spin-orbit coupling (SOC), Zeeman field and low electron densities.

We focus here on graphene-based approaches to MBSs. Graphene allows for exquisitely clean electronics [44, 45] and good superconducting proximity effect under magnetic fields [46–49], properties that could help overcome some of the material-specific problems of Majorana nanowires. In Ref. 50 it was experimentally demonstrated that the $\nu = 0$ quantum Hall state of monolayer graphene behaves, under a strong in-plane magnetic field, as a quantum spin Hall state, an observation explained as the result of Zeeman polarization of an antiferromagnetic ground state induced by strong electron-electron interactions [51, 52]. In Ref. 34 it was shown that a 1D TSC could be created on such a polarized $\nu = 0$ quantum Hall state by proximitizing its edges. The proposed configuration, while conceptually correct for the purpose of generating Majoranas, was experimentally problematic, since s-wave pairing breaks down quickly under the required magnetic fields, thus making the proximity effect of the $\nu = 0$ state challenging. A subsequent proposal was put forward that does away with the need of strong in-plane magnetic fields by employing twisted bilayer graphene in the QH regime under a strong perpendicular electric field [35, 53]. The latter is used to transform the bilayer QH edge states into a spinless helical phase by tuning each layer to an opposite filling factor $\nu = \pm 1$. This proposal, however, still requires strong electron-electron interactions to trigger the helical spin structure, as it exploits the ferrimagnetic sublattice polarization induced by

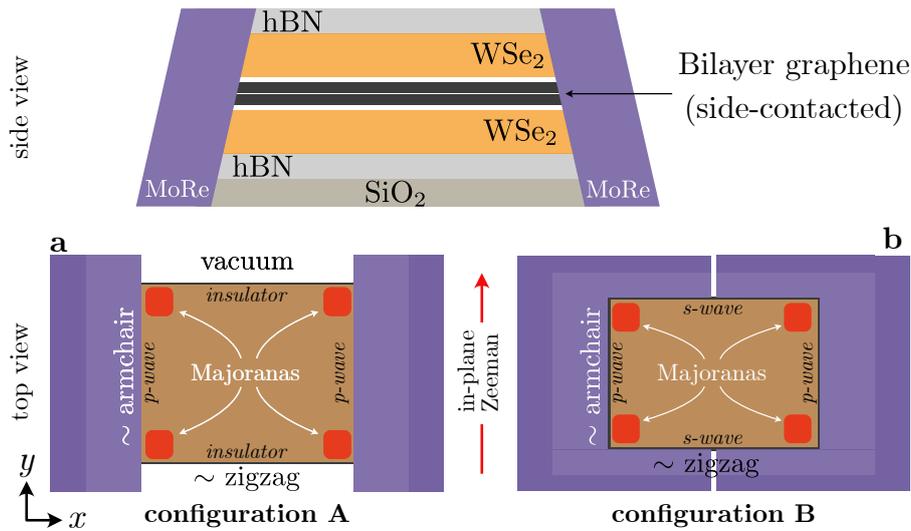


Figure 1: Lateral and top views of proposed device configurations A and B for the generation of Majorana bound states (MBSs) (schematically represented in red). The device is composed of a graphene bilayer (black), encapsulated in a transition metal dichalcogenide (TMDC) (orange) and laterally contacted with conventional s-wave superconductors (purple). The superconductor split in (b) creates a weak link that allows to phase-bias the junction.

interactions to stabilize $\nu = \pm 1$ QH plateaus. Furthermore, it presents other potential problems such as a reduced topological gap and a required electron-hole character of the bilayer, which could hinder superconducting pairing by a nearby superconductor. Other proposed avenues towards MBSs based on electronic interactions include the use of intrinsic superconducting correlations in magic-angle twisted graphene bilayers in combination with other 2D crystals [54].

In this work we present a third kind of approach to MBSs in graphene that does not rely on the QH effect or electron-electron interactions. Instead, it exploits the strong spin-orbit coupling (SOC) induced onto a Bernal-stacked graphene bilayer when it is encapsulated in a semiconducting transition metal dichalcogenide (TMDC) such as WSe₂, see Fig. 1(top). The SOC gaps the bulk of the bilayer [55–57, 57–60], and is thought to be responsible for anomalies observed in different graphene-based Josephson junctions [61, 62]. In the bilayer, the induced SOC produces Kramers pairs of counterpropagating topologically fragile edge states at the boundaries, see red and blue lines in Fig. 2(a,b). We show that some of these boundaries can develop spinless helical 1D modes under small Zeeman fields. We use here the term spinless helicity, as is conventional, to denote the existence of an odd number of pairs of non-degenerate counterpropagating modes at a given energy and edge, whose spin depends on the direction of propagation. The development of spinless helicity depends on edge crystallographic orientation. It is optimal for armchair edges and is absent for zigzag edges. A spinless helical edge can be gapped into a p-wave superconductor by side-contacting it to an s-wave superconductor [40]. MBSs then arise at the corners of the sample (see Fig. 1) above a Zeeman field comparable to the induced superconducting gap, as in Majorana nanowires. Despite their dependence on the crystallographic orientation of the edges, we show that MBSs are resilient to a certain amount of contact disorder and misalignment, and exhibit the expected 4π -periodic topological Josephson effect [41, 63]. Our analysis also reveals the appearance of an intriguing regime with pairs of near-zero modes at each corner, analogous to the approximate BDI-class MBSs of narrow multimode nanowires [64, 65], that occupies a large portion of parameter space around charge neutrality.

2 Edge modes in encapsulated bilayer graphene

TMDCs are semiconducting 2D crystals, such as WSe_2 or MoS_2 , with strong spin-orbit. The possibility of inducing a strong SOC on graphene monolayers by placing it in contact to a TMDC was demonstrated using a variety of theoretical [66–68] and experimental techniques [55–57, 57–60]. Two main types of SOC are generated on the low-energy sector of monolayer graphene close to the neutrality point: Ising and Rashba [59, 60, 67]. At low energies these two couplings can be written as

$$H_I = \frac{\lambda_I}{2} \tau_z s_z, \quad (1)$$

$$H_R = \frac{\lambda_R}{2} (\sigma_x \tau_z s_y - \sigma_y s_x), \quad (2)$$

in terms of the valley (τ), spin (s) and pseudospin (σ) Pauli matrices, which act on the subspace of the K and K' valleys, the physical electron spin and the carbon sublattices within the graphene unit cell, respectively.

The expected magnitude of the couplings is rather sizable, of the order of $\lambda_R \lesssim \lambda_I \approx 2 - 3$ meV in the case of WSe_2 [59] (possibly larger for WS_2 [55, 56]) and depends strongly on the interlayer rotation angle with graphene [66]. The low-energy model for graphene becomes $H = H_0 + H_I + H_R$, where $H_0 = v_F(\tau_z k_x \sigma_x + k_y \sigma_y)$ is the Dirac Hamiltonian for an isolated graphene monolayer and v_F is the Fermi velocity.

In the case of a graphene bilayer encapsulated on both sides with lattice-aligned WSe_2 , each layer acquires the above couplings, with the peculiarity that the corresponding λ_I and λ_R have an opposite sign on each layer [59, 69]. In the low-energy sector of bilayer graphene the pseudospin is equal to the layer quantum number [70], so that the low-energy effective model for bilayer graphene with a simple Bernal interlayer hopping t_1 (i.e. neglecting trigonal warping [70]) becomes

$$H = \frac{v_F k^2}{t_1} (\tau_z \sigma_x k_x + \sigma_y k_y)^2 + \frac{\tilde{\lambda}_I}{2} \tau_z s_z \sigma_z + \mathcal{O}(k^3),$$

$$\tilde{\lambda}_I = \left(1 - 2 \frac{v_F^2 k^2}{t_1^2} \right) \lambda_I. \quad (3)$$

Note that H_R does not contribute to the low-energy bulk modes to this order. The H_I , in contrast, becomes a Kane-Mele coupling [42], which in the monolayer would open a topological QSH gap at the Dirac point of magnitude $\sim \lambda_I$. Here, λ_I is much larger than the (impractically small) intrinsic Kane-Mele term of the monolayer, but is expected to open a topologically trivial gap due to the 2π Berry phase of each valley in the bilayer (as opposed to π in the monolayer) with pairs of topologically fragile helical modes on each edge inside it [69]. We confirm this expectation below. Despite their technically fragile nature, we note that the helical edge states are robust against a wide range of disorder, in particular any form of spin-independent disorder on the lattice, including vacancies or other valley-mixing perturbation (see App. A). The reason is that, as will be shown promptly, their helicity is exact, in the sense that counterpropagating edge states have opposite out-of-plane spin s_z on any edge, so backscattering requires a spin-active perturbation.

To understand the structure of SOC-induced edge states we numerically simulate the bandstructure of graphene bilayer nanoribbons with both armchair and zigzag edges. The bilayer is modeled with a Bernal-stacked tight-binding Hamiltonian [70]. To reach experimental sizes (particularly important in the next section) we use a scaled lattice constant, with hopping parameters also scaled to keep low-energy observables scaling-independent [71]. On each layer

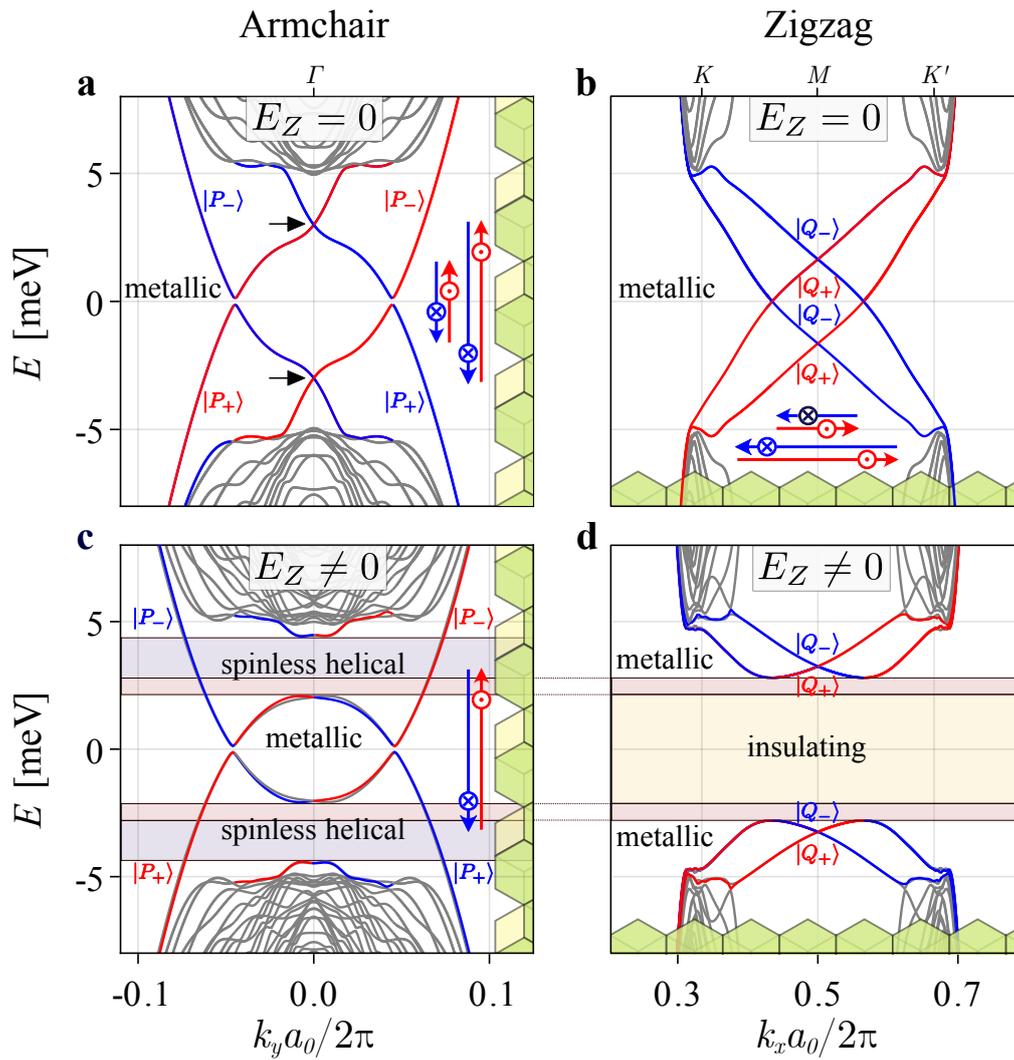


Figure 2: Dispersion and spin structure of edge modes along armchair (a,c) and zigzag (b,d) edges of a graphene bilayer flake where a full TMDC encapsulation opens a gap $\lambda_I = 10$ meV. Red and blue denote subgap modes propagating along a given edge with opposite out of plane spin polarization (\odot and \otimes), which is locked to momentum as shown in the insets. $|P_{\pm}\rangle$ and $|Q_{\pm}\rangle$ denote an additional quantum numbers due to orbital symmetries P and Q , see text. On the bottom row we show the effect of an in-plane Zeeman field E_Z on the edge modes. On an armchair edge (c) E_Z opens helical windows around the $k_y = 0$ (Γ -point) band crossings [black arrows in (a)], while on a zigzag edge (d) it opens an insulating gap around zero energy. The different combinations of armchair/zigzag phases are encoded in each energy interval by a white, purple, salmon and yellow background (see also Fig. 3).

we add the SOC terms H_I and H_R with opposite sign. The resulting bandstructures are shown in Fig. 2 for armchair nanoribbons (left column) and zigzag nanoribbons (right column).

The effective low-energy Kane-Mele coupling is indeed found to open a SOC gap, with two pairs of counterpropagating states on each edge. Spin-symmetry is broken, with two distinct propagating modes of opposite spin out-of-plane for each edge and propagation direction. These states are shown in Fig. 2(a,b), with red and blue denoting their spin orientation. Despite the fact that Rashba SOC H_R does not enter the low-energy Hamiltonian of bulk modes, it does affect the edge modes. For armchair edges, in particular, it constitutes a weak, time-

reversal-symmetric, gap-opening perturbation around zero energy (charge neutrality point), see Fig. 2(a).

If we neglect Rashba, we find that armchair edge states $|k_y\rangle$ have a second (orbital) quantum number, independent of the spin and associated to their behavior under the parity operator $P = \sigma_x \mathcal{K}$, where \mathcal{K} is conjugation and σ_x exchanges layers and sublattices. This quantum number is $\eta = \langle -k_y | P | k_y \rangle = \pm 1$, and its value for each mode is indicated by $|P_+\rangle$ (even) and $|P_-\rangle$ (odd) in Figs. 2(a,c). In the zigzag case all subbands are even under parity, but at the M -point crossings ($k_x a_0 / 2\pi = 0.5$ in Fig. 2), edge states $|M\rangle$ can be classified by a second orbital symmetry $Q = \sigma_y$, where σ_y is now defined to act on the two columns of sites in the unit cell perpendicular to the edge. Unlike P , the Q symmetry is just approximate, but quickly becomes exact in the limit of small a_0 . The corresponding quantum number $\eta' = \langle M | Q | M \rangle = \pm 1$ of each band is denoted in Figs. 2(b,d) as $|Q_\pm\rangle$. These orbital symmetries are important to understand the splitting of the edge modes under an in-plane Zeeman field.

Let us focus first on the Γ -point crossing at finite energy in the armchair edge states, see the black arrows in Fig. 2(a). Both of these are crossings between states of equal parity η . The addition of a Zeeman field along the y direction

$$H_Z = E_Z \sigma_y, \tag{4}$$

preserves parity but breaks the time-reversal symmetry, and immediately turns the crossings into anticrossings. This is illustrated in Fig. 2(c). The reason is the opposite (helical) out-of-plane spin orientation of the armchair states crossing at $k_y = 0$, see the inset sketch. The out-of-plane spin polarization is due to the dominant Ising SOC H_I of Eq. (1). The in-plane Zeeman H_Z mixes the crossing modes, opening energy windows inside the SOC gap (shaded in purple and salmon color) wherein armchair edges support spinless helical edge modes. In contrast, for the crossings at $k_y \neq 0$ and zero energy, the crossing modes have opposite parity, which prevents their splitting (unless Rashba is non-zero).

Zigzag edge modes behave in the opposite way, acquiring a full gap around zero energy, while the crossings at the M point remain unsplit owing to the opposite η' of the crossing modes. Depending on the value of the chemical potential inside the SOC gap, zigzag edges can therefore be either insulating or metallic (i.e. with spinful edge modes as in the absence of Zeeman field), but never spinless. There are then four distinct combinations possible in a vacuum terminated (normal) sample, corresponding to either spinless helical or metallic armchair edges and to insulating or metallic zigzag edges. We encode these four phases in white, purple, yellow and salmon throughout this work, see Fig. 2. The sample can be tuned to any of the four by adjusting Zeeman and chemical potential. Note that here and in the following, we use the term ‘metallic’ to denote edges where an even number of counterpropagating edge modes coexist at a given energy, in contrast to the case of a spinless helical edge with an odd number of them.

3 Superconducting proximity effect and Majoranas

For the purposes of implementing a Fu-Kane approach to generate MBSs in this system we need to introduce superconducting pairing correlations on the spinless helical edge modes. We follow the conventional route of inducing superconductivity externally by contacting a conventional superconductor laterally to the encapsulated bilayer, a technique that has been extensively demonstrated [46–49]. We analyze two distinct geometries, see Fig 1. Configuration A, Fig. 1(a), has proximitized armchair and vacuum-terminated zigzag edges, while in B, Fig. 1(b), the zigzag edges are also contacted to a superconductor (possibly with a weak link to allow phase-biasing the junction, though this detail can be ignored until Sec. 6). The

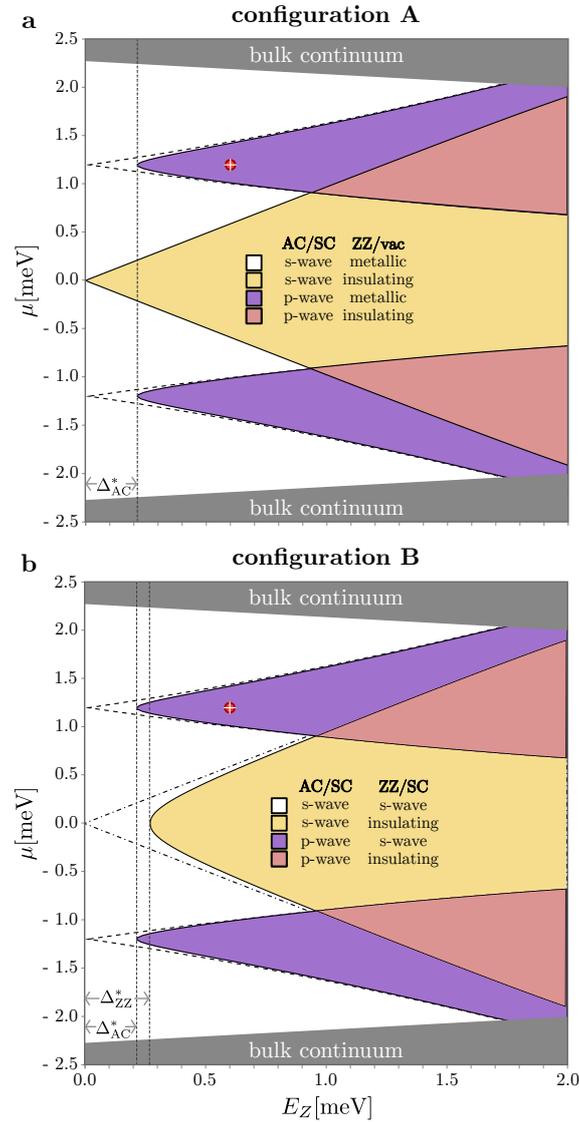


Figure 3: Phase diagrams of an encapsulated bilayer with induced SOC $\lambda_I = 5$ meV versus Zeeman and chemical potential. Panels (a) and (b) correspond to configurations A and B in Fig. 1, respectively. Each region is defined by different types of edge states along armchair (AC) and zigzag (ZZ) edges, terminated with either vacuum (vac) or a superconductor (SC), see legend for each configuration. An induced pairing $\Delta = 0.3$ meV is applied to any edge sites in direct contact to a SC. Dashed (dash-dotted) lines are metallic/helical (metallic/insulating) boundaries in AC/vac (ZZ/vac) edges. Vertical dotted lines indicate effective induced gaps Δ^* in AC and ZZ edges. In the salmon-colored regions of both phase diagrams, the system develops a D-class MBS at each sample corner [where a p-wave AC/SC edge and an insulating ZZ/vac (insulating ZZ/SC) meet in configuration A (B)]. In the purple region, corner MBSs also appear in configuration B, whereas Majorana states delocalize along the ZZ/vac metallic edges in configuration A. In the yellow region, BDI-class pairs of MBSs develop at each corner for both configurations if Rashba SOC is neglected (see text for details).

superconducting proximity effect is modeled as a pairing term Δ on the boundary sites of each edge, although the results are qualitatively similar with a more elaborate model where a square-lattice superconductor is explicitly incorporated in the tight-binding lattice.

We compute their corresponding phase diagrams in each configuration, see Figs. 3(a,b), by locating Γ -point band inversions in sufficiently wide infinite nanoribbons, with either armchair/superconductor or zigzag/superconductor edges. We find that proximitized edges of any type develop a trivial s-wave gap at zero Zeeman field (white region in the phase diagrams). On proximitized armchair edges tuned to their spinless helical window, a Zeeman energy above the effective induced pairing Δ_{AC}^* (here ≈ 0.21 meV for the chosen value of $\Delta = 0.3$ meV), creates a band inversion into a topological p-wave phase (purple and salmon-colored regions), as predicted by Fu and Kane [4,40]. In contrast, on a proximitized zigzag edge close to neutrality, $\mu = 0$, a Zeeman that exceeds the corresponding $\Delta_{ZZ}^* \approx 0.27$ meV transforms the s-wave phase into an insulator [yellow and salmon-colored regions in Fig. 3(b)]. As a result, a device in configuration A or B within the salmon-colored region (strong Zeeman fields) should localize a MBS at each of its armchair/zigzag corners, as these are boundaries between topological (p-wave) and trivial (insulating) edges. However, within purple regions (weaker Zeeman) only configuration B should host localized corner MBSs (corners become p-wave/s-wave boundaries). Configuration A should instead delocalize its corner MBSs along the metallic zigzag edges.

These predictions are readily confirmed by numerical simulations of large but finite-size rectangular samples in both A and B configurations. In Fig. 4 we show the low-energy eigenvalues for A and B samples (top row) as a function of E_Z , and the local density of states (LDOS, bottom row) corresponding to the lowest (red) eigenstates. For both configurations (left and right columns) we choose a point within the purple region (marked with a red dot in Fig. 3). As anticipated, the LDOS exhibits spatially localized/delocalized MBSs in the B/A configurations as described above. The energy of localized MBSs in Fig. 4(d) remains pinned to zero within the purple region, but eventually becomes finite in the salmon-colored region due to finite-size effects (splitting due to MBS overlap). In contrast, delocalized MBSs in configuration A, purple region, strongly hybridize along the zigzag edge with the MBS at the opposite corner, splitting and merging into a quasi-continuous set of finite energy Andreev bound states.

4 BDI-class Majorana pairs

To complete the analysis of the phase diagram we now show the spectrum within the yellow regions of Fig. 3(a,b). Focusing on configuration B at zero chemical potential $\mu = 0$, one would expect an s-wave gap along the armchair edge, and an s-wave or insulating gap for $E_Z < \Delta_{ZZ}^*$ and $E_Z > \Delta_{ZZ}^*$, respectively. In both cases, the generic expectation is therefore to have no zero-modes. Surprisingly, however, the spectrum shows a multiply-degenerate *near-zero mode* at $E_Z > \Delta_{ZZ}^*$ (insulating zigzag edge). These states become exact zero modes when we remove the Rashba coupling, $\lambda_R = 0$. The results are shown in Fig. 5 at $\mu = 0$ (a), $\mu = 0.6$ meV (b) and $\mu = 1.2$ meV (c), and as a function of λ_R (d,e), for the same parameters as in Figs. 3 and 4 but for a longer $2\mu\text{m}$ junction along x and an increased $\Delta = 1$ meV.

To understand the nature of these unexpected zero modes we must recall the phenomenology of multimode Rashba nanowires, which may also exhibit multiple near-zero modes at either end when an even number of modes become topological. When the number of inverted modes is even, the wire is technically in a trivial D-class phase with $\nu_D = 0$ invariant ($\nu_D \in \mathbb{Z}_2$), so no protected zero energy MBSs are expected. It was shown [65,72], however, that a hidden BDI-symmetry [73] emerges if the SOC-induced inter-mode coupling vanishes, which is a good approximation for nanowires of width much smaller than the spin-orbit length. In such

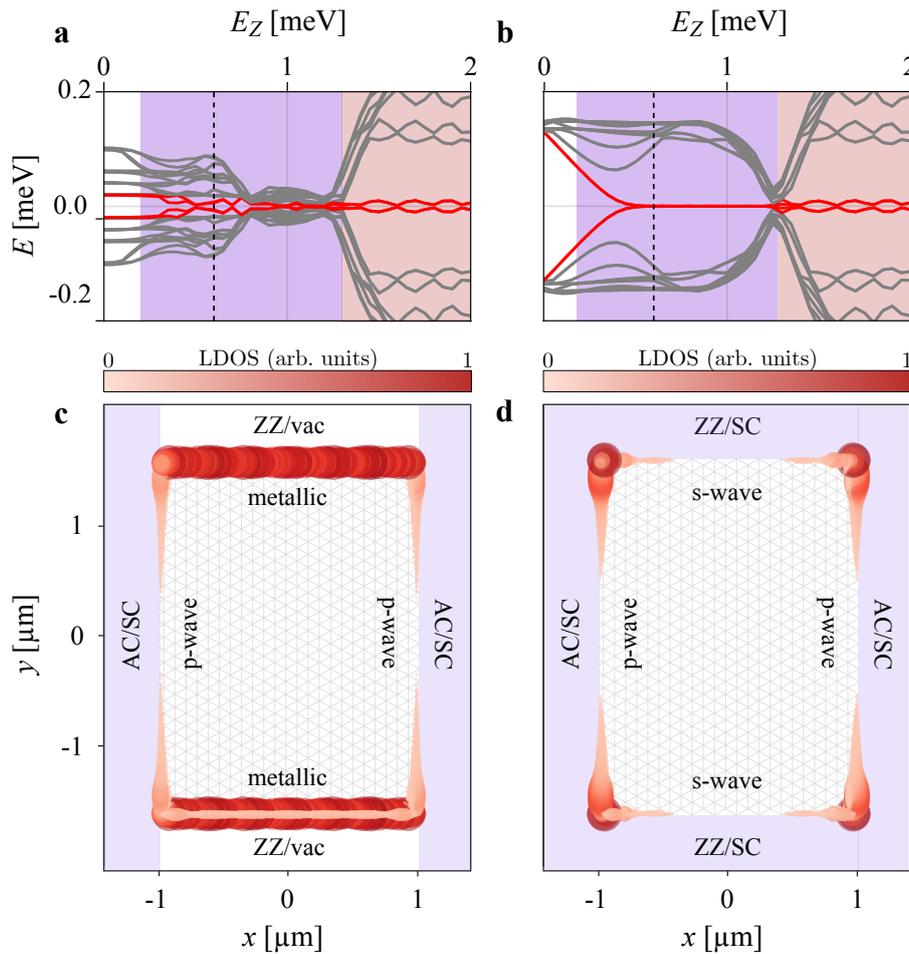


Figure 4: (a,b) Low-energy spectrum as a function of Zeeman splitting E_Z of a rectangular sample in the two configurations A and B of Fig. 1 and with the same parameters as Fig. 3. Background colors match Fig. 3. (c,d) Local density of states across the sample corresponding to the four lowest eigenstates [red curves in (a,b)] at the vertical dashed line in (a,b) (p-wave armchair phase). In configuration A (a,c), the zigzag edges are metallic, so the MBSs become spatially delocalized and merge into a quasi-continuum of zigzag states, while in configuration B (b,d) zigzag edges have a trivial s-wave gap, so the MBS remain localized at the corners.

limit the nanowire Hamiltonian can be cast into a real matrix belonging to the BDI symmetry class, albeit one where time-reversal symmetry (TRS) $\mathcal{T} = is_y\mathcal{K}$ is broken by Zeeman, and a pseudo-TRS $\tilde{\mathcal{T}} = \mathcal{K}$ (conjugation) takes its place. The BDI invariant in 1D is $\nu_{\text{BDI}} \in \mathbb{Z}$. The total number of zero modes at a nanowire boundary then becomes the difference in ν_{BDI} at either side of the boundary, which can be more than one [65, 72]. In nanowires the value of ν_{BDI} actually matches the total number of spinless modes that have undergone a topological transition. For small but finite E_Z , such that no modes have transitioned yet, it is therefore $\nu_{\text{BDI}} = 0$ (like in vacuum). This trivial invariant can also be physically understood as a consequence of the *opposite helicity* of two pairs of modes weakly split by Zeeman in a Rashba nanowire.

A similar situation applies to the armchair edge in our encapsulated bilayer. The low-energy Hamiltonian Eq. (3) for a nanoribbon with proximitized armchair edges and zero Rashba $\lambda_R = 0$ can be cast into a real form, so its symmetry class effectively becomes BDI in this limit, with invariant $\nu_{\text{BDI}}^{\text{AC}} \in \mathbb{Z}$ when TRS is broken by a finite Zeeman field. A crucial

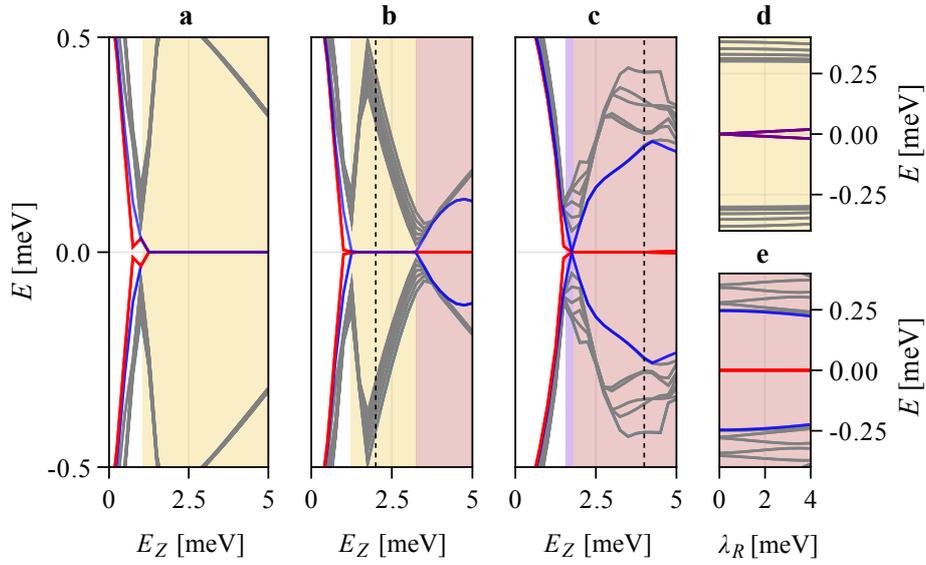


Figure 5: Low-energy spectrum as a function of E_Z of a $2\mu\text{m} \times 2\mu\text{m}$ device similar to Fig. 4d but with λ_R set to zero and Δ increased to 1meV. Panels (a-c) correspond to $\mu = 0$ (a), $\mu = 0.6\text{meV}$ (b) and $\mu = 1.2\text{meV}$ (c). Background colors correspond to different regions of the phase diagram, similar to Fig. 3(b) but with phase boundaries pushed to larger E_Z due to the increased Δ . For $E_Z \gtrsim \Delta_{ZZ}^*$, in the yellow regions, unexpected pairs of Majorana zero modes at each sample corner appear that correspond to a BDI-class \mathbb{Z} -invariant $\nu_{\text{BDI}}^{\text{AC}} = 2$ for the AC edge and $\nu_{\text{BDI}}^{\text{ZZ}} = 0$ for the ZZ one. The zero-energy eigenvalues in the yellow region are therefore eightfold-degenerate. These become near-zero modes as the BDI symmetry is slightly broken by a finite Rashba coupling λ_R (d). In the regions with salmon-colored background of (b) and (c) the armchair edge has a $\nu_{\text{D}}^{\text{AC}} = \nu_{\text{BDI}}^{\text{AC}} = 1$ invariant, regardless of symmetry class. Thus, the four zero-energy MBSs (red lines), one at each sample corner, remain insensitive to Rashba (e). Vertical dashed lines in (b,c) correspond to the E_Z used in (d,e), respectively.

difference with nanowires, however, is that the spinful edge modes along a given armchair edge do not have zero net helicity: the two pairs of modes in a given edge have an *equal* (instead of opposite) helicity, determined by the sign of λ_I [see inset in Fig. 2(a)]. As a consequence, the \mathbb{Z} BDI invariant in an armchair edge at small E_Z (and actually all throughout the white and yellow regions of Fig. 3) is $\nu_{\text{BDI}}^{\text{AC}} = 2$, not zero. This has the dramatic implication that *pairs* of localized MBSs will arise at each corner as soon as the zigzag edge becomes insulating, and hence trivial, with zero BDI invariant $\nu_{\text{BDI}}^{\text{ZZ}} = 0$ (yellow region). This phenomenon is shown in Fig. 5(a). In Fig. 5(b) we see that at finite μ we can cross from the $\nu_{\text{BDI}}^{\text{AC}} = 2$ regime (yellow region, metallic armchair) to the conventional D-class $\nu_{\text{D}}^{\text{AC}} = \nu_{\text{BDI}}^{\text{AC}} = 1$ regime (salmon-colored region, spinless helical armchair), whereupon the number of MBSs per edge is halved, from two to one, following a band inversion. Degenerate BDI-class MBSs are expected to survive as near-zero modes if the BDI-breaking effect of Rashba coupling λ_R on the armchair edge states is finite but small, as is the case for typical experimental values of $\lambda_R \sim 1-5$ meV, see Fig. 5(f). In contrast, increasing λ_R leaves the MBSs in the salmon-colored region completely unaffected in large enough samples, see Fig. 5(d), since in this case the D-class armchair edge remains topologically non-trivial.

5 Effect of disorder and misalignment

Up to this point all our results have assumed perfect crystallographic armchair and zigzag edges. In real samples it is impossible to avoid a certain degree of misalignment when fabricating the superconducting contacts, or to create some amount of disorder. Since MBSs are topologically protected states, they should withstand such perturbations to a certain extent, but it is far from clear a priori if they are resilient to a realistic degree of misalignment and disorder. In this section we attempt to address this question by simulating the spectrum of a sample in configuration B with a fraction of vacancies along each edge and a finite rotation of the lattice.

Figure 6 compares the spatial localization of BDI-class and D-class MBSs on pristine, unrotated samples (a, b) and in samples with a 1% contact disorder and with a 2° contact misalignment (c, d). Disorder is introduced in our simulation in the form of vacancies at the given fraction of terminal sites along contact edges, removing any dangling bonds that are produced. While disorder and misalignment degrade MBS localization, for the device parameters considered they are found to remain spatially decoupled at this level of contact imperfections. Disorder above $\sim 2\%$ or misalignments above 7° leads to a splitting of MBSs due to edge leakage and overlap. We also quantitatively show in panels (e, f) the size of the minigap and degree of MBS splitting in contacts without disorder, purely as a function of the misalignment angle. We find that, at least in the regimes explored in our simulations, the BDI-class MBS minigap is actually more resilient to misalignment than the one of D-class MBSs. The latter tend to delocalize faster and to exhibit a minigap that becomes quickly polluted by low-lying states as the angle is increased. Above a $5^\circ - 7^\circ$ misalignment, the MBSs in both cases are found to quickly merge into an edge-state quasicontinuum.

6 Josephson effect

A hallmark consequence of an odd number of MBSs at either side of a Josephson junction is the development of an anomalous 4π -periodic Josephson effect [41, 74] in the superconducting phase difference ϕ across the junction. A short (in x) and wide (in y) junction in configuration B, with a superconductor split as in Fig. 1(b), can be operated by tuning ϕ across the split weak link. As the junction is assumed much wider than the size of the MBSs, it should behave as two Josephson junctions in parallel (one along each zigzag edge).¹ In the D-class ($\lambda_R \neq 0$) the device can be tuned to host either one or zero Majoranas per corner, which should produce an Andreev spectrum and Josephson current with 4π - or 2π -periodicity in ϕ , respectively. In the BDI-class ($\lambda_R = 0$), Majorana pairs at a given corner will be decoupled from each other, so they should produce a 4π -periodic spectrum and supercurrent.

We confirm these expectations, first for $\lambda_R = 0$, both for $\nu_{\text{BDI}}^{\text{AC}} = 2$ MBSs per corner, Fig. 7(a), and $\nu_{\text{D}}^{\text{AC}} = \nu_{\text{D}}^{\text{AC}} = 1$ MBS per corner, Fig. 7(b). Breaking BDI symmetry with a finite $\lambda_R = 2$ meV makes the invariant trivial, $\nu_{\text{D}}^{\text{AC}} = 0$, so the Josephson effect becomes 2π -periodic, Fig. 7(c). Again, D-class Majoranas are unaffected by Rashba, and remain 4π -periodic, Fig. 7(d).

¹In a realistic experiment, the phase bias is controlled by an external magnetic field on a SQUID geometry. The field could in principle produce a flux across the bilayer graphene junction that would result in a ϕ gradient across the junction width. Note that we neglect such gradients here, so ϕ is assumed to be y -independent. This is equivalent to neglecting the junction area as compared to that of the SQUID.

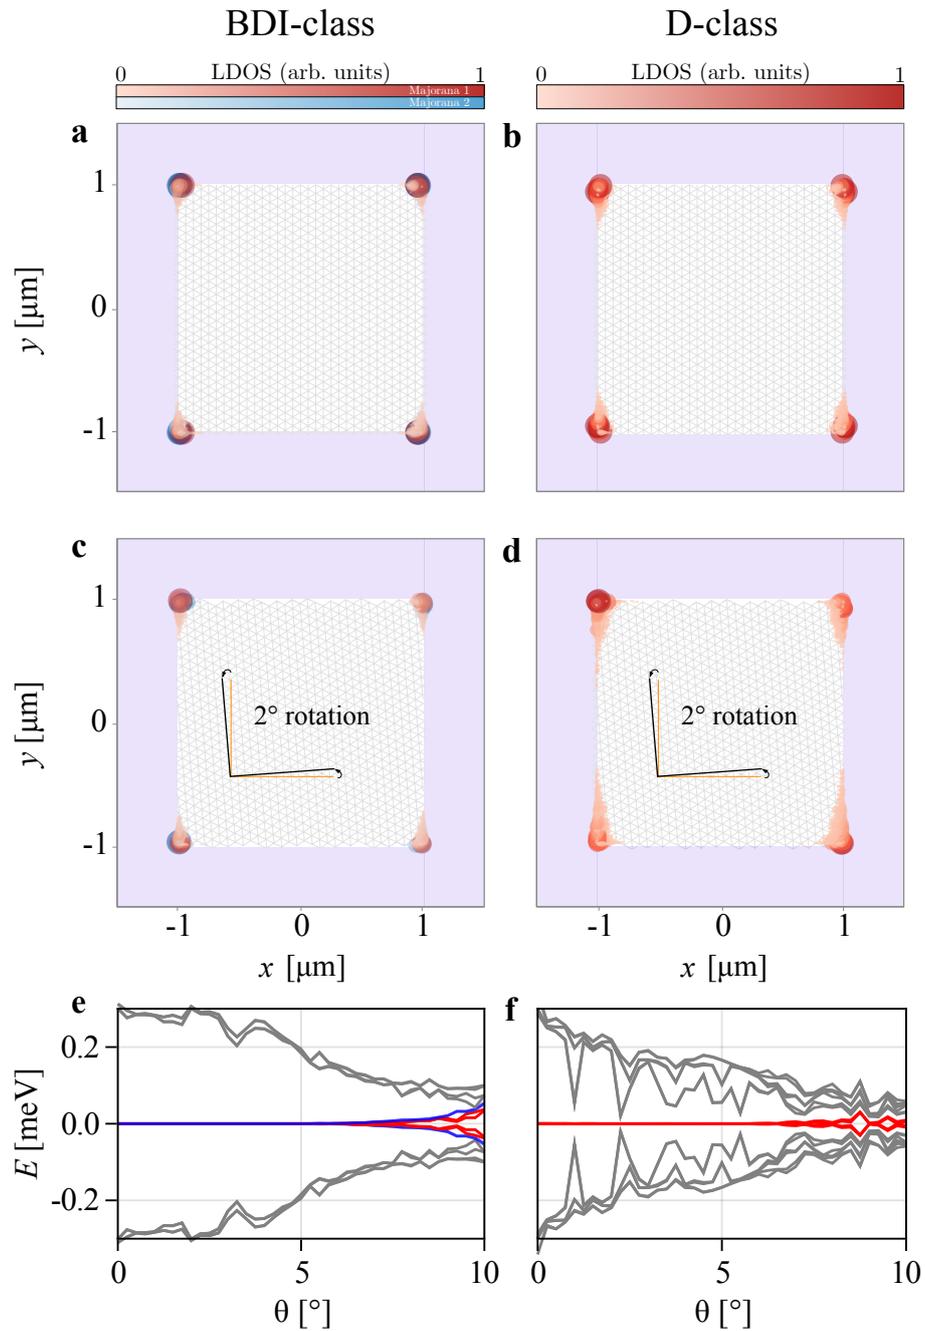


Figure 6: Spatial profile of MBSs, both in pristine (a,b) and imperfect (c,d) samples in configuration B. Left and right columns correspond, respectively, to BDI-class and D-class MBSs [for parameters marked with dashed lines of Figs. 5(b) and 5(c)]. In (c,d) contact disorder is 1% and misalignment angle is 2°. (e,f) Misalignment angle dependence of the low-energy spectrum in otherwise clean samples. In the BDI-class we depict the two Majoranas at each corner in blue and red, while the lone MBSs in the D-class are shown in red. The scaling of the lattice constant in the simulation has only a small effect on the magnitude and evolution of the topological gap in (e,f).

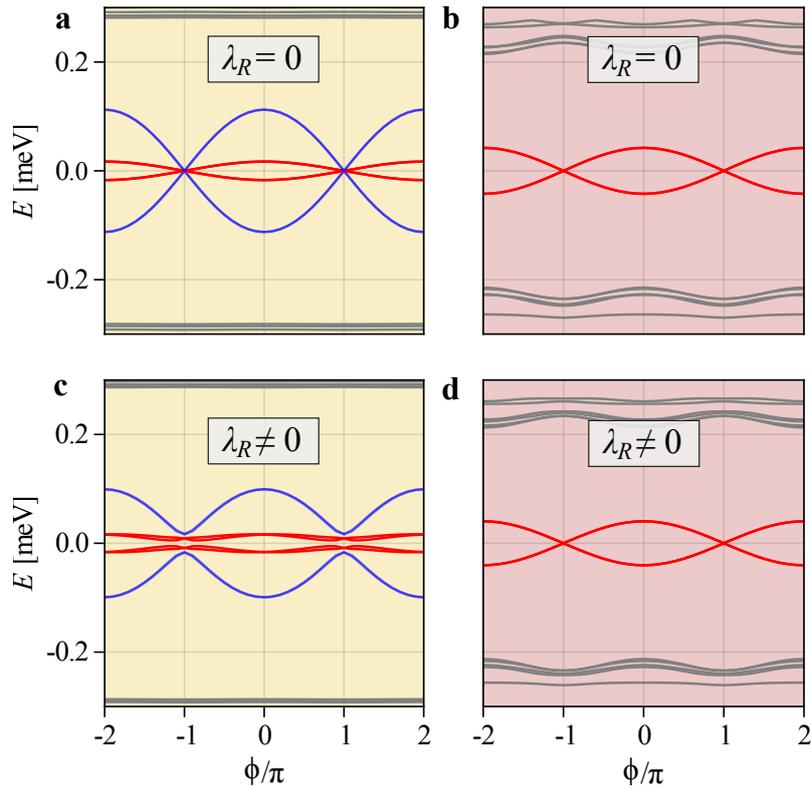


Figure 7: Andreev levels as a function of superconducting phase bias in a Josephson junction similar to Fig. 1(b), for $\lambda_R = 0$ (a,b) and $\lambda_R = 2$ meV (c,d). The value of E_Z is fixed to the vertical dashed line of Fig. 5(b) (a,c) and Fig. 5(c) (b,d). The width of the junction is $W = 2.5\mu\text{m}$, but the length is shortened to $L = 0.2\mu\text{m}$ to increase the phase-dependent MBS hybridization across the junction. Both the pairs of BDI-class MBSs in (a) and the lone D-class MBSs in (b) give rise to an approximate 4π Josephson effect. Increasing λ_R breaks the BDI symmetry of (a), making the Josephson effect from corner Majorana pairs (near-zero modes) 2π -periodic, and hence trivial (c). The 4π case of a single MBS per corner is however unaffected by Rashba (d).

7 Conclusion

We have shown that bilayer graphene, proximitized by laterally contacted superconductors and vertically encapsulated in transition metal dichalcogenides, exhibits a phase diagram with several topological phases below the spin-orbit bulk gap induced by the encapsulation. It includes non-trivial phases with single or pairs of MBSs at each armchair/zigzag corners, depending on the induced Rashba coupling. The system's phase can be controlled by tuning the chemical potential and an in-plane Zeeman field in ranges of the order of the bulk spin-orbit gap and the induced superconducting gap, respectively. The mechanism behind the topological phases is directly connected to the distinct properties of armchair and zigzag edges and the type of boundary modes they develop as a result of the SOC induced by the encapsulation. Despite the requirements of concrete armchair/zigzag crystallographic edges, a finite tolerance of around $\sim 5^\circ$ in contact misalignment and $\sim 1\%$ in contact disorder is predicted, making experimental realizations feasible.

A brief comparison of the above proposal to Majorana nanowires, as the current leading platform for MBSs, is in order. The two approaches exhibit interesting differences. One disad-

vantage of graphene is the g-factor, which is smaller (~ 2) than in semiconducting nanowires ($\sim 2 - 18$, depending on details such as degree of metallization). As both approaches require a Zeeman energy comparable or greater than the induced superconducting gap, this demands stronger magnetic fields for comparable induced gaps. It has been shown, however, that highly controllable contacts and induced gaps are possible in graphene by using robust Type-II superconductors such as MoRe, that have much larger critical fields than Aluminum (the superconductor of choice for Majorana nanowires). This makes graphene's reduced g-factor potentially less of an issue. The problem of disorder also exhibits very different characteristics. In nanowires, charged defects and other sources of disorder are considered one of the most important challenges towards realizing MBSs [16, 17]. In graphene-based van der Waals heterostructures, a very good control of puddles and bulk disorder is now possible using particular 2D crystals as substrates, such as hBN and graphite [75, 76]. It is also to be expected that potential disorder will scatter electrons very differently in graphene than in semiconductors. Finally, the scale of energies that trigger multimode physics in our proposal is $\lambda_I \sim 2 - 10$ meV, which is larger than in typical low-density nanowires ($\hbar^2/[2m^*R^2] \sim 0.5$ meV). All these differences suggest that encapsulated graphene is worth exploring as a potential alternative to Majorana nanowires.

Methods

All our tight-binding simulations were performed using Quantica.jl v0.5.0 [77]. All the code is available at Zenodo [78].

Data availability

All data presented here is available at Zenodo [78].

Acknowledgments

We thank Srijit Goswami and Prasanna Rout for valuable discussions.

Competing interests: The Authors declare no Competing Financial or Non-Financial Interests.

Funding: This research was supported by the Spanish Ministry of Economy and Competitiveness through Grants FIS2017-84860-R, PCI2018-093026 (FlagERA Topograph), PGC2018-097018-B-I00 and PID2021-122769NB-I00 (AEI/FEDER, EU), and the Comunidad de Madrid through Grant S2018/NMT-4511 (NMAT2D-CM).

Author contributions: F. P. prepared the numerical codes and performed the numerical simulations. F. P. and P.S.-J. processed the data and prepared the figures. P.S.-J. designed and oversaw the project. All authors contributed to discussing the physics and writing the manuscript.

A Resilience of helical modes in the presence of arbitrary edge orientation and scalar disorder

In the main text we have analyzed the emergence of helical edge modes in the armchair and

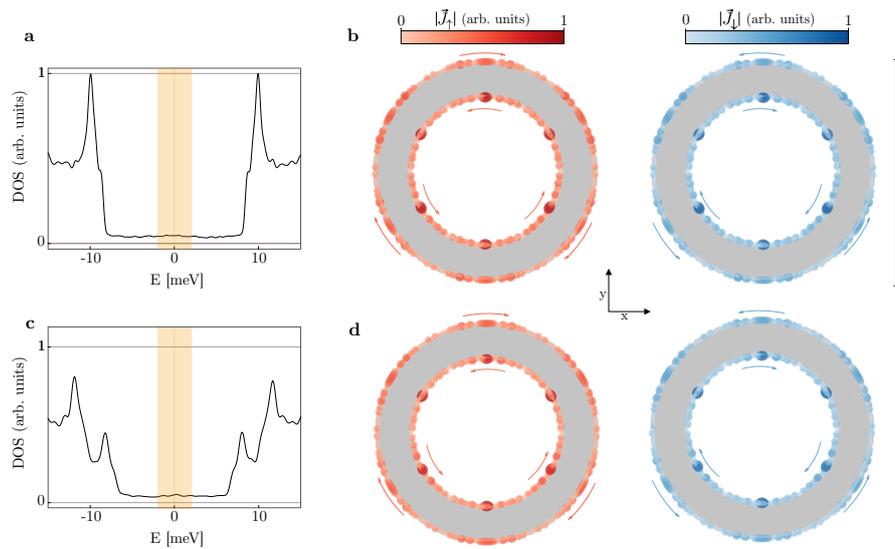


Figure 8: (a) Total density of states (DOS) of encapsulated bilayer graphene without Rashba or Zeeman couplings, with $\lambda_I = 20\text{meV}$, and with the shape of a circular strip. The subgap DOS comes from edge states that remain ungapped all along the boundaries of the sample, which span all crystallographic orientations from armchair to zigzag. The edge states carry a spin current, shown in (b) for states within the yellow strip. The current is not suppressed by the varying edge orientation, since localization would require spin-flip-backscattering. Curved arrows indicate current direction, and colored circles encode current magnitude. (c,d) The same as in (a,b) but with the addition of Anderson disorder of amplitude 2meV and zero average, distributed throughout the sample. Again, the spin-independent nature of the disorder leaves the edge states unperturbed, even though the DOS around and above the gap edge is strongly affected.

zigzag edges by analyzing their respective bandstructures. Their robustness against disorder and edge misalignment is also studied, but only at the level of the p-wave phase and the associated MBSs in an SC-N contact. This does not directly address, however, the question about the general stability of the original helical states even before proximitization with a superconductor. We have argued that the induced SOC does not open a true topological-insulator gap, whose edge modes would be protected against any time-reversal-invariant perturbation by virtue of the bulk topology. Instead, the 2π Berry phase of the bilayer spectrum makes the SOC gap topologically fragile, meaning that time-reversal-symmetric perturbations such as Rashba may in principle destroy the associated pairs of helical edge states. In this appendix we demonstrate that this is not the case, at least for conventional spin-independent graphene imperfections, such as intervalley scattering at the edges or charge puddles.

As discussed in the main text, counterpropagating edge states have exactly opposite out-of-plane spin s_z in both the armchair and zigzag cases. This is true even if we include realistic Rashba couplings, to a good approximation, due to its subleading contribution in the low-energy sector. Hence, backscattering of the edge states requires a spin-flip for both crystallographic orientations. Conventional scalar disorder should then be unable to localize edge states. We now show that this is also true for any other edge orientation, even in the presence of disorder.

Figure 8(a) shows the total density of states (DOS) in a sample of encapsulated bilayer graphene, with zero Zeeman and Rashba, and shaped like a circular strip. It is computed using the Kernel Polynomial Method [79]. The circular geometry has edges that vary across

all possible crystallographic orientations. Figure 8(b) shows the corresponding spin-resolved current densities $\vec{J}_{\uparrow,\downarrow}$ in real space for all states within an energy window around neutrality (yellow box). The states were obtained by exact diagonalization using the Arnoldi method.

We see that despite the varying edge orientation around the circular strip, the DOS remains finite (ungapped) throughout the SOC gap (here from -10meV to 10meV). All these subgap states are spatially localized at the boundaries of the sample, and carry a net spin current, just as in the armchair and zigzag cases. This shows that edge states remain robust and gapless in the presence of arbitrary variations of edge orientation. The analysis can be extended by adding disorder. We apply strong Anderson disorder throughout the whole circular strip, uniformly distributed in the interval $[-2\text{meV}, 2\text{meV}]$. The result is presented in Fig. 8(c,d). While disorder has a strong effect on the DOS outside the gap, the subgap DOS remains unperturbed. Likewise, the edge current remains insensitive to the disorder. We thus find that the helical edge states behave as true topological modes protected against arbitrary perturbations, as long as they are spin-independent, or at most commute with s_z .

References

- [1] A. Y. Kitaev, *Unpaired Majorana fermions in quantum wires*, Phys. Uspekhi **44**, 131 (2001), doi:[10.1070/1063-7869/44/10S/S29](https://doi.org/10.1070/1063-7869/44/10S/S29).
- [2] X.-L. Qi and S.-C. Zhang, *Topological insulators and superconductors*, Rev. Mod. Phys. **83**, 1057 (2011), doi:[10.1103/RevModPhys.83.1057](https://doi.org/10.1103/RevModPhys.83.1057).
- [3] C. Nayak, S. Simon, A. Stern, M. Freedman and S. Das Sarma, *Non-Abelian anyons and topological quantum computation*, Rev. Mod. Phys. **80**, 1083 (2008), doi:[10.1103/RevModPhys.80.1083](https://doi.org/10.1103/RevModPhys.80.1083).
- [4] J. Alicea, *New directions in the pursuit of Majorana fermions in solid state systems*, Rep. Prog. Phys. **75**, 076501 (2012), doi:[10.1088/0034-4885/75/7/076501](https://doi.org/10.1088/0034-4885/75/7/076501).
- [5] D. Aasen et al., *Milestones toward Majorana-based quantum computing*, Phys. Rev. X **6**, 031016 (2016), doi:[10.1103/PhysRevX.6.031016](https://doi.org/10.1103/PhysRevX.6.031016).
- [6] S. Plugge, A. Rasmussen, R. Egger and K. Flensberg, *Majorana box qubits*, New J. Phys. **19**, 012001 (2017), doi:[10.1088/1367-2630/aa54e1](https://doi.org/10.1088/1367-2630/aa54e1).
- [7] R. Aguado and L. P. Kouwenhoven, *Majorana qubits for topological quantum computing*, Phys. Today **73**, 44 (2020), doi:[10.1063/PT.3.4499](https://doi.org/10.1063/PT.3.4499).
- [8] Y. Oreg, G. Refael and F. von Oppen, *Helical liquids and Majorana bound states in quantum wires*, Phys. Rev. Lett. **105**, 177002 (2010), doi:[10.1103/PhysRevLett.105.177002](https://doi.org/10.1103/PhysRevLett.105.177002).
- [9] R. M. Lutchyn, J. D. Sau and S. Das Sarma, *Majorana fermions and a topological phase transition in semiconductor-superconductor heterostructures*, Phys. Rev. Lett. **105**, 077001 (2010), doi:[10.1103/PhysRevLett.105.077001](https://doi.org/10.1103/PhysRevLett.105.077001).
- [10] V. Mourik, K. Zuo, S. M. Frolov, S. R. Plissard, E. P. A. M. Bakkers and L. P. Kouwenhoven, *Signatures of Majorana fermions in hybrid superconductor-semiconductor nanowire devices*, Science **336**, 1003 (2012), doi:[10.1126/science.1222360](https://doi.org/10.1126/science.1222360).
- [11] E. Prada et al., *From Andreev to Majorana bound states in hybrid superconductor-semiconductor nanowires*, Nat. Rev. Phys. **2**, 575 (2020), doi:[10.1038/s42254-020-0228-y](https://doi.org/10.1038/s42254-020-0228-y).

- [12] R. Aguado, *Majorana quasiparticles in condensed matter*, Riv. Nuovo Cimento **40**, 523 (2017), doi:[10.1393/ncr/i2017-10141-9](https://doi.org/10.1393/ncr/i2017-10141-9).
- [13] P. Krogstrup et al., *Epitaxy of semiconductor–superconductor nanowires*, Nat. Mater. **14**, 400 (2015), doi:[10.1038/nmat4176](https://doi.org/10.1038/nmat4176).
- [14] J. E. Sestoft et al., *Engineering hybrid epitaxial InAsSb/Al nanowires for stronger topological protection*, Phys. Rev. Mat. **2**, 044202 (2018), doi:[10.1103/PhysRevMaterials.2.044202](https://doi.org/10.1103/PhysRevMaterials.2.044202).
- [15] H. Zhang et al., *Large zero-bias peaks in InSb – Al hybrid semiconductor-superconductor nanowire devices*, (arXiv preprint) doi:[10.48550/arXiv.2101.11456](https://doi.org/10.48550/arXiv.2101.11456).
- [16] H. Pan and S. Das Sarma, *Physical mechanisms for zero-bias conductance peaks in Majorana nanowires*, Phys. Rev. Res. **2**, 013377 (2020), doi:[10.1103/PhysRevResearch.2.013377](https://doi.org/10.1103/PhysRevResearch.2.013377).
- [17] S. Das Sarma and H. Pan, *Disorder-induced zero-bias peaks in Majorana nanowires*, Phys. Rev. B **103**, 195158 (2021), doi:[10.1103/PhysRevB.103.195158](https://doi.org/10.1103/PhysRevB.103.195158).
- [18] F. Domínguez, J. Cayao, P. San-Jose, R. Aguado, A. L. Yeyati and E. Prada, *Zero-energy pinning from interactions in Majorana nanowires*, npj Quantum Mater. **2**, 13 (2017), doi:[10.1038/s41535-017-0012-0](https://doi.org/10.1038/s41535-017-0012-0).
- [19] S. D. Escribano, A. L. Yeyati and E. Prada, *Interaction-induced zero-energy pinning and quantum dot formation in Majorana nanowires*, Beilstein J. Nanotechnol. **9**, 2171 (2018), doi:[10.3762/bjnano.9.203](https://doi.org/10.3762/bjnano.9.203).
- [20] C. Reeg, D. Loss and J. Klinovaja, *Metallization of a Rashba wire by a superconducting layer in the strong-proximity regime*, Phys. Rev. B **97**, 165425 (2018), doi:[10.1103/PhysRevB.97.165425](https://doi.org/10.1103/PhysRevB.97.165425).
- [21] E. J. H. Lee, X. Jiang, M. Houzet, R. Aguado, C. M. Lieber and S. De Franceschi, *Spin-resolved Andreev levels and parity crossings in hybrid superconductor-semiconductor nanostructures*, Nat. Nanotechnol. **9**, 79 (2014), doi:[10.1038/nnano.2013.267](https://doi.org/10.1038/nnano.2013.267).
- [22] M. Valentini et al., *Nontopological zero-bias peaks in full-shell nanowires induced by flux-tunable Andreev states*, Science **373**, 82 (2021), doi:[10.1126/science.abf1513](https://doi.org/10.1126/science.abf1513).
- [23] G. Kells, D. Meidan and P. W. Brouwer, *Near-zero-energy end states in topologically trivial spin-orbit coupled superconducting nanowires with a smooth confinement*, Phys. Rev. B **86**, 100503 (2012), doi:[10.1103/PhysRevB.86.100503](https://doi.org/10.1103/PhysRevB.86.100503).
- [24] E. Prada, P. San-Jose and R. Aguado, *Transport spectroscopy of ns nanowire junctions with Majorana fermions*, Phys. Rev. B **86**, 180503 (2012), doi:[10.1103/PhysRevB.86.180503](https://doi.org/10.1103/PhysRevB.86.180503).
- [25] F. Peñaranda, R. Aguado, P. San-Jose and E. Prada, *Quantifying wave-function overlaps in inhomogeneous Majorana nanowires*, Phys. Rev. B **98**, 235406 (2018), doi:[10.1103/PhysRevB.98.235406](https://doi.org/10.1103/PhysRevB.98.235406).
- [26] J. Avila, F. Peñaranda, E. Prada, P. San-Jose and R. Aguado, *Non-Hermitian topology as a unifying framework for the Andreev versus Majorana states controversy*, Commun. Phys. **2**, 133 (2019), doi:[10.1038/s42005-019-0231-8](https://doi.org/10.1038/s42005-019-0231-8).
- [27] S. Nadj-Perge, I. K. Drozdov, J. Li, H. Chen, S. Jeon, J. Seo, A. H. MacDonald, B. A. Bernevig and A. Yazdani, *Observation of Majorana fermions in ferromagnetic atomic chains on a superconductor*, Science **346**, 602 (2014), doi:[10.1126/science.1259327](https://doi.org/10.1126/science.1259327).

- [28] S. Jeon, Y. Xie, J. Li, Z. Wang, B. A. Bernevig and A. Yazdani, *Distinguishing a Majorana zero mode using spin-resolved measurements*, Science **358**, 772 (2017), doi:[10.1126/science.aan3670](https://doi.org/10.1126/science.aan3670).
- [29] H. J. Suominen et al., *Zero-energy modes from coalescing Andreev states in a two-dimensional semiconductor-superconductor hybrid platform*, Phys. Rev. Lett. **119**, 176805 (2017), doi:[10.1103/PhysRevLett.119.176805](https://doi.org/10.1103/PhysRevLett.119.176805).
- [30] F. Nichele et al., *Scaling of Majorana zero-bias conductance peaks*, Phys. Rev. Lett. **119**, 136803 (2017), doi:[10.1103/PhysRevLett.119.136803](https://doi.org/10.1103/PhysRevLett.119.136803).
- [31] A. Fornieri et al., *Evidence of topological superconductivity in planar Josephson junctions*, Nature **569**, 89 (2019), doi:[10.1038/s41586-019-1068-8](https://doi.org/10.1038/s41586-019-1068-8).
- [32] A. Banerjee et al., *Signatures of a topological phase transition in a planar Josephson junction*, (arXiv preprint) doi:[10.48550/arXiv.2201.03453](https://doi.org/10.48550/arXiv.2201.03453).
- [33] S. Vaitiekėnas et al., *Flux-induced topological superconductivity in full-shell nanowires*, Science **367**, 6485 (2020), doi:[10.1126/science.aav3392](https://doi.org/10.1126/science.aav3392).
- [34] P. San-Jose, J. L. Lado, R. Aguado, F. Guinea and J. Fernández-Rossier, *Majorana zero modes in graphene*, Phys. Rev. X **5**, 041042 (2015), doi:[10.1103/PhysRevX.5.041042](https://doi.org/10.1103/PhysRevX.5.041042).
- [35] F. Finocchiaro, F. Guinea and P. San-Jose, *Quantum spin Hall effect in twisted bilayer graphene*, 2D Mater. **4**, 025027 (2017), doi:[10.1088/2053-1583/aa5265](https://doi.org/10.1088/2053-1583/aa5265).
- [36] B. T. Zhou, N. F. Q. Yuan, H.-L. Jiang and K. T. Law, *Ising superconductivity and Majorana fermions in transition-metal dichalcogenides*, Phys. Rev. B **93**, 180501 (2016), doi:[10.1103/PhysRevB.93.180501](https://doi.org/10.1103/PhysRevB.93.180501).
- [37] Y.-T. Hsu, A. Vaezi, M. H. Fischer and E.-A. Kim, *Topological superconductivity in monolayer transition metal dichalcogenides*, Nat. Commun. **8**, 14985 (2017), doi:[10.1038/ncomms14985](https://doi.org/10.1038/ncomms14985).
- [38] M.-X. Deng, G. Y. Qi, W. Luo, R. Ma, R.-Q. Wang, R. Shen, L. Sheng and D. Y. Xing, *Superconducting states and Majorana modes in transition-metal dichalcogenides under inhomogeneous strain*, Phys. Rev. B **99**, 085106 (2019), doi:[10.1103/PhysRevB.99.085106](https://doi.org/10.1103/PhysRevB.99.085106).
- [39] S. Kezilebieke et al., *Topological superconductivity in a van der Waals heterostructure*, Nature **588**, 424 (2020), doi:[10.1038/s41586-020-2989-y](https://doi.org/10.1038/s41586-020-2989-y).
- [40] L. Fu and C. L. Kane, *Superconducting proximity effect and Majorana fermions at the surface of a topological insulator*, Phys. Rev. Lett. **100**, 096407 (2008), doi:[10.1103/PhysRevLett.100.096407](https://doi.org/10.1103/PhysRevLett.100.096407).
- [41] L. Fu and C. L. Kane, *Josephson current and noise at a superconductor/quantum-spin-Hall-insulator/superconductor junction*, Phys. Rev. B **79**, 161408 (2009), doi:[10.1103/PhysRevB.79.161408](https://doi.org/10.1103/PhysRevB.79.161408).
- [42] C. Kane and E. Mele, *Quantum spin Hall effect in graphene*, Phys. Rev. Lett. **95**, 226801 (2005), doi:[10.1103/PhysRevLett.95.226801](https://doi.org/10.1103/PhysRevLett.95.226801).
- [43] M. König, S. Wiedmann, C. Brüne, A. Roth, H. Buhmann, L. W. Molenkamp, X.-L. Qi and S.-C. Zhang, *Quantum spin Hall insulator state in HgTe quantum wells*, Science **318**, 766 (2007), doi:[10.1126/science.1148047](https://doi.org/10.1126/science.1148047).

- [44] E. Icking et al., *Transport spectroscopy of ultraclean tunable band gaps in bilayer graphene*, Adv. Electron. Mater. **8**, 2200510 (2022), doi:[10.1002/aelm.202200510](https://doi.org/10.1002/aelm.202200510).
- [45] M. C. Lemme, D. Akinwande, C. Huyghebaert and C. Stampfer, *2D materials for future heterogeneous electronics*, Nat. Commun. **13**, 1392 (2022), doi:[10.1038/s41467-022-29001-4](https://doi.org/10.1038/s41467-022-29001-4).
- [46] V. E. Calado et al., *Ballistic Josephson junctions in edge-contacted graphene*, Nat. Nanotechnol. **10**, 761 (2015), doi:[10.1038/nnano.2015.156](https://doi.org/10.1038/nnano.2015.156).
- [47] M. Ben Shalom et al., *Quantum oscillations of the critical current and high-field superconducting proximity in ballistic graphene*, Nat. Phys. **12**, 318 (2015), doi:[10.1038/nphys3592](https://doi.org/10.1038/nphys3592).
- [48] M. T. Allen et al., *Observation of electron coherence and Fabry-Perot standing waves at a graphene edge*, Nano Lett. **17**, 7380 (2017), doi:[10.1021/acs.nanolett.7b03156](https://doi.org/10.1021/acs.nanolett.7b03156).
- [49] D. I. Indolese et al., *Compact SQUID realized in a double-layer graphene heterostructure*, Nano Lett. **20**, 7129 (2020), doi:[10.1021/acs.nanolett.0c02412](https://doi.org/10.1021/acs.nanolett.0c02412).
- [50] A. F. Young et al., *Tunable symmetry breaking and helical edge transport in a graphene quantum spin Hall state*, Nature **505**, 528 (2014), doi:[10.1038/nature12800](https://doi.org/10.1038/nature12800).
- [51] M. Kharitonov, *Phase diagram for the $\nu = 0$ quantum Hall state in monolayer graphene*, Phys. Rev. B **85**, 155439 (2012), doi:[10.1103/PhysRevB.85.155439](https://doi.org/10.1103/PhysRevB.85.155439).
- [52] J. L. Lado and J. Fernández-Rossier, *Noncollinear magnetic phases and edge states in graphene quantum Hall bars*, Phys. Rev. B **90**, 165429 (2014), doi:[10.1103/PhysRevB.90.165429](https://doi.org/10.1103/PhysRevB.90.165429).
- [53] J. D. Sanchez-Yamagishi, J. Y. Luo, A. F. Young, B. M. Hunt, K. Watanabe, T. Taniguchi, R. C. Ashoori and P. Jarillo-Herrero, *Helical edge states and fractional quantum Hall effect in a graphene electron-hole bilayer*, Nat. Nanotechnol. **12**, 118 (2017), doi:[10.1038/nnano.2016.214](https://doi.org/10.1038/nnano.2016.214).
- [54] A. Thomson, I. M. Sorensen, S. Nadj-Perge and J. Alicea, *Gate-defined wires in twisted bilayer graphene: From electrical detection of intervalley coherence to internally engineered Majorana modes*, Phys. Rev. B **105**, L081405 (2022), doi:[10.1103/PhysRevB.105.L081405](https://doi.org/10.1103/PhysRevB.105.L081405).
- [55] A. Avsar et al., *Spin-orbit proximity effect in graphene*, Nat. Commun. **5**, 4875 (2014), doi:[10.1038/ncomms5875](https://doi.org/10.1038/ncomms5875).
- [56] Z. Wang, D. Ki, H. Chen, H. Berger, A. H. MacDonald and A. F. Morpurgo, *Strong interface-induced spin-orbit interaction in graphene on WS₂*, Nat. Commun. **6**, 8339 (2015), doi:[10.1038/ncomms9339](https://doi.org/10.1038/ncomms9339).
- [57] B. Yang et al., *Tunable spin-orbit coupling and symmetry-protected edge states in graphene/WS₂*, 2D Mater. **3**, 031012 (2016), doi:[10.1088/2053-1583/3/3/031012](https://doi.org/10.1088/2053-1583/3/3/031012).
- [58] Z. Wang, D.-K. Ki, J. Y. Khoo, D. Mauro, H. Berger, L. S. Levitov and A. F. Morpurgo, *Origin and magnitude of 'designer' spin-orbit interaction in graphene on semiconducting transition metal dichalcogenides*, Phys. Rev. X **6**, 041020 (2016), doi:[10.1103/PhysRevX.6.041020](https://doi.org/10.1103/PhysRevX.6.041020).
- [59] J. O. Island et al., *Spin-orbit-driven band inversion in bilayer graphene by the van der Waals proximity effect*, Nature **571**, 85 (2019), doi:[10.1038/s41586-019-1304-2](https://doi.org/10.1038/s41586-019-1304-2).

- [60] J. F. Sierra, J. Fabian, R. K. Kawakami, S. Roche and S. O. Valenzuela, *Van der Waals heterostructures for spintronics and opto-spintronics*, Nat. Nanotechnol. **16**, 856 (2021), doi:[10.1038/s41565-021-00936-x](https://doi.org/10.1038/s41565-021-00936-x).
- [61] T. Wakamura et al., *Spin-orbit-enhanced robustness of supercurrent in Graphene/ws₂ Josephson junctions*, Phys. Rev. Lett. **125**, 266801 (2020), doi:[10.1103/PhysRevLett.125.266801](https://doi.org/10.1103/PhysRevLett.125.266801).
- [62] P. Rout, N. Papadopoulos and S. Goswami, *Private communication*.
- [63] H. Kwon, K. Sengupta and V. Yakovenko, *Fractional ac Josephson effect in p- and d-wave superconductors*, Eur. Phys. J. B **37**, 349 (2003).
- [64] S. Tewari and J. D. Sau, *Topological invariants for spin-orbit coupled superconductor nanowires*, Phys. Rev. Lett. **109**, 150408 (2012), doi:[10.1103/PhysRevLett.109.150408](https://doi.org/10.1103/PhysRevLett.109.150408).
- [65] R. Wakatsuki, M. Ezawa and N. Nagaosa, *Majorana fermions and multiple topological phase transition in Kitaev ladder topological superconductors*, Phys. Rev. B **89**, 174514 (2014), doi:[10.1103/PhysRevB.89.174514](https://doi.org/10.1103/PhysRevB.89.174514).
- [66] A. David, P. Rakya, A. Kormányos and G. Burkard, *Induced spin-orbit coupling in twisted graphene-transition metal dichalcogenide heterobilayers: Twistronics meets spintronics*, Phys. Rev. B **100**, 085412 (2019), doi:[10.1103/PhysRevB.100.085412](https://doi.org/10.1103/PhysRevB.100.085412).
- [67] A. Avsar, H. Ochoa, F. Guinea, B. Özyilmaz, B. J. van Wees and I. J. Vera-Marun, *Colloquium: Spintronics in graphene and other two-dimensional materials*, Rev. Mod. Phys. **92**, 021003 (2020), doi:[10.1103/RevModPhys.92.021003](https://doi.org/10.1103/RevModPhys.92.021003).
- [68] M. Pacholski, G. Lemut, J. Tworzydło and C. Beenakker, *Generalized eigenproblem without fermion doubling for Dirac fermions on a lattice*, SciPost Phys. **11**, 105 (2021), doi:[10.21468/SciPostPhys.11.6.105](https://doi.org/10.21468/SciPostPhys.11.6.105).
- [69] M. P. Zaletel and J. Yong Khoo, *The gate-tunable strong and fragile topology of multilayer-graphene on a transition metal dichalcogenide*, (arXiv preprint) doi:[10.48550/arXiv.1901.01294](https://doi.org/10.48550/arXiv.1901.01294).
- [70] E. McCann and M. Koshino, *The electronic properties of bilayer graphene*, Rep. Prog. Phys. **76**, 056503 (2013), doi:[10.1088/0034-4885/76/5/056503](https://doi.org/10.1088/0034-4885/76/5/056503).
- [71] M.-H. Liu, P. Rickhaus, P. Makk, E. Tóvári, R. Maurand, F. Tkatschenko, M. Weiss, C. Schönenberger and K. Richter, *Scalable tight-binding model for graphene*, Phys. Rev. Lett. **114**, 036601 (2015), doi:[10.1103/PhysRevLett.114.036601](https://doi.org/10.1103/PhysRevLett.114.036601).
- [72] S. Tewari, T. D. Stanescu, J. D. Sau and S. Das Sarma, *Topological minigap in quasi-one-dimensional spin-orbit-coupled semiconductor Majorana wires*, Phys. Rev. B **86**, 024504 (2012), doi:[10.1103/PhysRevB.86.024504](https://doi.org/10.1103/PhysRevB.86.024504).
- [73] A. P. Schnyder, S. Ryu, A. Furusaki and A. W. W. Ludwig, *Classification of topological insulators and superconductors in three spatial dimensions*, Phys. Rev. B **78**, 195125 (2008), doi:[10.1103/PhysRevB.78.195125](https://doi.org/10.1103/PhysRevB.78.195125).
- [74] H.-J. Kwon, V. M. Yakovenko and K. Sengupta, *Fractional ac Josephson effect in unconventional superconductors*, Low Temp. Phys. **30**, 613 (2004), doi:[10.1063/1.1789931](https://doi.org/10.1063/1.1789931).
- [75] C. R. Dean et al., *Boron nitride substrates for high-quality graphene electronics*, Nat. Nanotechnol. **5**, 722 (2010), doi:[10.1038/nnano.2010.172](https://doi.org/10.1038/nnano.2010.172).

- [76] E. Y. Andrei, G. Li and X. Du, *Electronic properties of graphene: A perspective from scanning tunneling microscopy and magnetotransport*, Rep. Prog. Phys. **75**, 056501 (2012), doi:[10.1088/0034-4885/75/5/056501](https://doi.org/10.1088/0034-4885/75/5/056501).
- [77] P. San-Jose, *Quantica.jl: A quantum lattice simulation library in the julia language*, Zenodo (2021) doi:[10.5281/zenodo.4762964](https://doi.org/10.5281/zenodo.4762964).
- [78] F. Peñaranda, *fernandopenaranda/mbsinblg: v1.1*, Zenodo (2022), [10.5281/zenodo.5948620](https://doi.org/10.5281/zenodo.5948620).
- [79] A. Weiße, G. Wellein, A. Alvermann and H. Fehske, *The kernel polynomial method*, Rev. Mod. Phys. **78**, 275 (2006), doi:[10.1103/RevModPhys.78.275](https://doi.org/10.1103/RevModPhys.78.275).