

Giant spatial anisotropy of magnon Landau damping in altermagnets

António T. Costa^{1,2*}, João C. G. Henriques^{1,3} and Joaquín Fernández-Rossier^{1,4}

1 International Iberian Nanotechnology Laboratory (INL),
Av. Mestre José Veiga, 4715-330 Braga, Portugal

2 Physics Center of Minho and Porto Universities (CF-UM-UP), Universidade do Minho,
Campus de Gualtar, 4710-057 Braga, Portugal

3 Universidade de Santiago de Compostela, 15782 Santiago de Compostela, Spain

4 On permanent leave from Departamento de Física Aplicada,
Universidad de Alicante, 03690 San Vicente del Raspeig, Spain

* antonio.costa@inl.int

Abstract

Altermagnets are a new class of magnetic materials with zero net magnetization (like antiferromagnets) but spin-split electronic bands (like ferromagnets) over a fraction of reciprocal space. As in antiferromagnets, magnons in altermagnets come in two flavours, that either add one or remove one unit of spin to the $S = 0$ ground state. However, in altermagnets these two magnon modes are non-degenerate along some directions in reciprocal space. Here we show that the lifetime of altermagnetic magnons, due to Landau damping caused by coupling to Stoner modes, has a very strong dependence on both flavour and direction. Strikingly, coupling to Stoner modes leads to a complete suppression of magnon propagation along selected spatial directions. This giant anisotropy will impact electronic, spin, and energy transport properties and may be exploited in spintronic applications.



Copyright A. T. Costa *et al.*

This work is licensed under the Creative Commons

[Attribution 4.0 International License](https://creativecommons.org/licenses/by/4.0/).

Published by the SciPost Foundation.

Received 2024-11-26

Accepted 2025-03-25

Published 2025-04-11

doi:[10.21468/SciPostPhys.18.4.125](https://doi.org/10.21468/SciPostPhys.18.4.125)



Check for updates

Contents

1	Introduction	2
2	Model and mean-field ground state	3
2.1	Mean-field results	4
3	Magnons	5
3.1	Itinerant altermagnet	5
4	Conclusion	8
A	Mean-field electronic structure	10
B	Relationship between the density of Stoner modes and the magnon lifetime	10

C	Origin of the anisotropic magnon lifetime	11
D	Insulating altermagnet in the intermediate coupling regime ($U = 3.5\tau$)	12
E	Directionality of the magnon spectrum in the insulating regime (intermediate coupling)	14
	References	15

1 Introduction

The recent recognition of altermagnets as a new class of magnetic materials [1–3], originally predicted by Pekar and Rashba in 1964 [4], has been a very exciting development for both condensed matter and materials physics. In a static configuration, altermagnets camouflage very well as antiferromagnets; however, when you look under the hood the disguise is given away by the spin-polarized electronic bands. It is their dynamics, however, that reveal their true colors [5, 6]. To understand the dynamical properties of a magnetic system it is essential to look at its elementary spin excitations, or magnons [7].

A magnon in a ferromagnetic solid is usually associated to processes by which the total magnetization of the sample is lowered by the equivalent of a quantum of angular momentum, \hbar , and associated with the spin-lowering operator S^- . We thus say that a ferromagnetic magnon carries spin $S^z = -1$. In terms of elementary electronic processes, generating a magnon consists in promoting an electron from the majority spin band (\uparrow) to the minority spin band (\downarrow), and is associated with the operator $a_{\downarrow}^{\dagger}a_{\uparrow}$. By virtue of electron-electron interactions, the electron and the hole involved in this process form a bound state, whose energy depends on the net crystal momentum of the pair.

In antiferromagnets, magnons can have either $S^z = -1$ or $S^z = 1$, associated with lowering the spin of the \uparrow sublattice or raising the spin of the \downarrow sublattice. Due to the complete equivalence between the two spin directions, the two kinds of antiferromagnetic magnons ($S^z = \pm 1$) have identical energies [8]. On the other hand, it has been noted [2, 9] that magnons in altermagnets have unique features when compared to their antiferromagnetic counterparts. The most noticeable difference is that $S^z = -1$ and $S^z = 1$ magnons have distinct energies along certain directions in the reciprocal space, the same direction associated with the spin-split electronic bands.

In metallic magnets, magnons have finite lifetimes, due to the fact that they can decay into uncorrelated electron-hole pairs, also known as a Stoner excitations [10, 11]. The decay probability (hence the inverse of the magnon lifetime) is proportional to the spectral density associated with the Stoner excitations, which usually increases monotonically with energy for a fixed wavevector. Thus, magnon lifetimes typically decrease monotonically as the magnon energy increases [12].

It has been assumed hitherto [9] that, due to the distinct energies of $S^z = \pm 1$ magnons in altermagnets, their lifetimes would also be different, in an almost trivial manner. Other works have looked into the effects of magnon-magnon interactions on magnon lifetimes, a mechanism that is supposed to be relevant for insulating magnets. [13] Apart from that, very little attention has been paid to the lifetime of magnons in altermagnets, and most theoretical approaches employ spin-only models in their description [9, 14–16].

Here we show that Landau damping by Stoner modes in metallic and slightly doped altermagnets has highly non-trivial consequences. Specifically, the combination between the

peculiar symmetry of the altermagnet and the damping by Stoner excitations makes magnons in itinerant altermagnets completely distinct from their antiferro- and ferromagnetic counterparts. The magnons acquire a strong frequency- and spin-dependent directionality, which can potentially be exploited as a resource in spintronics devices [17].

2 Model and mean-field ground state

We model the electronic structure of altermagnets using a Hamiltonian proposed in ref. [18], which is essentially a Hubbard model with an especially chosen hopping structure that realises an altermagnetic symmetry,

$$H = \sum_{ll'} \sum_{\mu\mu'} \sum_{\sigma} \tau_{ll'}^{\mu\mu'} c_{l\mu\sigma}^{\dagger} c_{l'\mu'\sigma} + U \sum_{l,\mu} n_{l\mu\uparrow} n_{l\mu\downarrow}, \quad (1)$$

where $n_{l\mu\sigma} \equiv c_{l\mu\sigma}^{\dagger} c_{l\mu\sigma}$, l and l' label unit cells, μ and μ' label sublattices (A or B) and σ labels the spin projection along the z axis. The hopping matrix $\tau_{ll'}^{\mu\mu'}$ elements have the following structure: nearest-neighbor hopping τ , between different sublattices, is adopted as the energy unit (solid lines in Fig. 1). Second-neighbor hopping (between identical sublattices) is given by $\tau'(1 \pm \delta)$ with different signs for different sublattices. These are indicated in Fig. 1 as dashed and dotted lines. The intra-atomic interaction parameter U can be chosen to place the system in either the metallic or insulating altermagnetic phase; for the value of diagonal hopping we adopted in this work, $2\tau \lesssim U \lesssim 3\tau$ yields a metallic altermagnetic phase, whereas $U \gtrsim 3\tau$ produces the insulating altermagnetic phase. The complete mean-field phase diagram of this model has been explored in Ref. [18]. Here we will choose two representative points, one in the insulating and one in the metallic region, and study the elementary spin excitations above their respective mean-field ground states. The mean-field approximation we employ amounts to the following replacement,

$$U \sum_{l,\mu} n_{l\mu\uparrow} n_{l\mu\downarrow} \longrightarrow \frac{U}{2} \sum_{l,\mu} [(\bar{n}_{\mu l} + \bar{m}_{\mu l}) n_{l\mu\downarrow} + (\bar{n}_{\mu l} - \bar{m}_{\mu l}) n_{l\mu\uparrow}], \quad (2)$$

with $\bar{n}_{\mu l} \equiv \langle n_{l\mu\uparrow} \rangle + \langle n_{l\mu\downarrow} \rangle$ and $\bar{m}_{\mu l} \equiv \langle n_{l\mu\uparrow} \rangle - \langle n_{l\mu\downarrow} \rangle$, plus a constant term that can be safely ignored. The average occupancies $\bar{n}_{\mu l}$ and magnetic moments $\bar{m}_{\mu l}$ are determined self-consistently.

We obtain the magnon spectrum of altermagnets by studying the transverse spin susceptibilities,

$$\chi_{\mu\nu}^{+-}(\vec{r}_{l'} - \vec{r}_l, t) \equiv -i\theta(t) \left\langle \left[S_{l\mu}^{+}(t), S_{l'\nu}^{-}(0) \right] \right\rangle, \quad (3)$$

and

$$\chi_{\mu\nu}^{-+}(\vec{r}_{l'} - \vec{r}_l, t) \equiv -i\theta(t) \left\langle \left[S_{l\mu}^{-}(t), S_{l'\nu}^{+}(0) \right] \right\rangle, \quad (4)$$

where t is the time, $S_{l\mu}^{-} \equiv c_{l\mu\downarrow}^{\dagger} c_{l\mu\uparrow}$, $(S_{l\mu}^{+} = (S_{l\mu}^{-})^{\dagger})$ is the operator that creates a spin excitation with $S^z = -1$ ($S^z = 1$) at cell l in the sublattice μ , \vec{r}_l is the position of unit cell l , and $\theta(t)$ is the Heaviside unit step function. These two-time correlation functions cannot be computed exactly for an interacting model such as the one defined in Eq. 1; the simplest approach that can describe magnons is the so-called random phase approximation (RPA), in which the interaction is taken into account, to all orders in perturbation theory, between the electron and the hole that form the spin-flip excitation [10]. The RPA relates the transverse interacting susceptibilities χ^{\perp} ($\perp \equiv +- \text{ or } -+$) to the mean-field susceptibilities $\bar{\chi}^{\perp}$, which are the same Green functions defined in Eqs. 3 and 4, with the thermal average $\langle \cdot \rangle$ evaluated for the mean-field

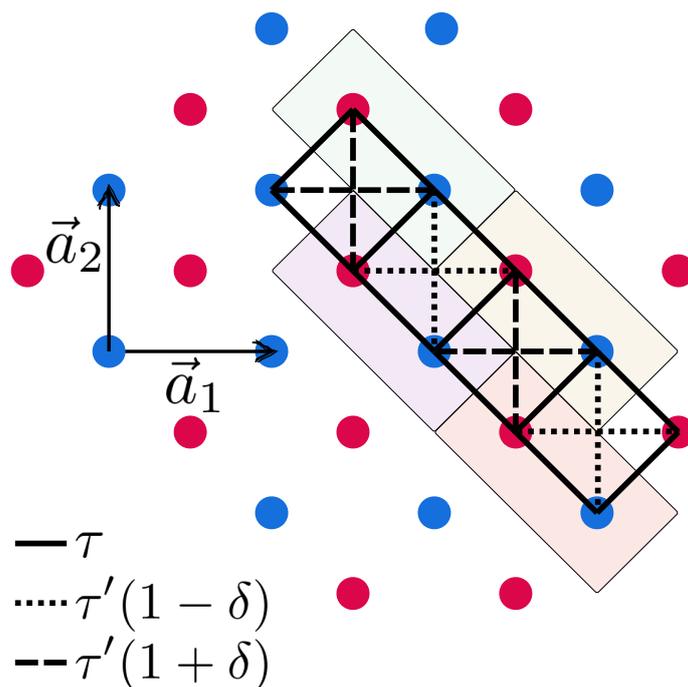


Figure 1: Schematic representation of the model altermagnet on a square lattice defined by primitive vectors \vec{a}_1 and \vec{a}_2 , with $|\vec{a}_1| = |\vec{a}_2| = a$. Blue and red circles indicate atomic sites belonging to different sublattices. The solid line connecting different sublattices represents the nearest-neighbor hopping τ . Dashed and dotted lines represent the alternating second neighbor hoppings $\tau'(1 \pm \delta)$. The lightly colored rectangle indicates the unit cells.

configuration. For the model considered here, after Fourier transforming both in time and position, the RPA equations are

$$\chi_{\mu\nu}^{+-}(\mathcal{Q}) = \bar{\chi}_{\mu\nu}^{+-}(\mathcal{Q}) - U \sum_{\xi} \bar{\chi}_{\mu\xi}^{+-}(\mathcal{Q}) \chi_{\xi\nu}^{+-}(\mathcal{Q}), \quad (5)$$

where $\mathcal{Q} \equiv (\vec{q}, \hbar\Omega)$. We obtain an analogous expression for χ^{-+} . The spectral density associated with magnons, projected on sublattice μ , is given by

$$\rho_{\mu}^{\perp}(\mathcal{Q}) = -\frac{1}{\pi} \text{Im} \chi_{\mu\mu}^{\perp}(\mathcal{Q}), \quad (6)$$

where \perp can be either $+-$ or $-+$, denoting the transversal character of these response functions with respect to the equilibrium staggered magnetization (Néel vector). Magnon energies $\hbar\Omega(\vec{q})$ are associated with the positions of the peaks of ρ^{+-} (for the $S^z = -1$ magnons) or ρ^{-+} (for the $S^z = 1$ magnons), at fixed wave-vector \vec{q} . Analogously, magnon lifetimes are defined as the inverse of the full width at half-maximum of the magnon peaks.

2.1 Mean-field results

An insulating altermagnetic state can be obtained by choosing $U \gtrsim 3\tau$; however, for $3\tau \lesssim U \lesssim 10\tau$ the mean-field configuration belongs to an intermediate coupling regime, for which the spin dynamics can not yet be properly described by a spin-only (Heisenberg-like) model.¹ Thus, to benchmark our fermionic model against a spin model, we chose $U = 10\tau$,

¹For a discussion of the partial failure of spin-only models for this case, we refer the reader to Appendix D. A similar discussion appears in Ref. [19].

together with the hopping values $\tau' = 0.17\tau$ and $\delta = 0.83$. The self-consistent mean-field solution gives the bands shown in Fig. 6 of appendix A, with a staggered magnetic moment $m_A - m_B = 1.86\mu_B$ per unit cell. For the reciprocal space path we plotted in Fig. 6, the spin splitting is zero only along the line $q_y = q_x$. Along the line $q_y = \frac{\pi}{a} - q_x$ there is the characteristic crossing between the \uparrow and \downarrow spin bands, associated with the altermagnetic symmetry.

The metallic altermagnetic state can be obtained either by tweaking the hopping parameters, as shown in ref. [18], or by reducing the Hubbard parameter U . We chose the latter option to minimize the differences between the shapes of the electronic bands in the metallic and insulating states. By setting $\tau' = 0.17\tau$, $\delta = 0.83$ and $U = 2.5\tau$ we obtain the metallic altermagnetic bands shown in Fig. 6 of appendix A, with a staggered magnetic moment $m_A - m_B = 0.74\mu_B$ per unit cell.

3 Magnons

To benchmark our methodology, we first analyze the spin excitations of the insulating altermagnet in the strong coupling limit ($U = 10\tau$), for which the spin model results should be valid [15, 20]. By scanning the spectral densities ρ^{+-} and ρ^{-+} in the $(\hbar\Omega, \vec{q})$ space we obtain the dispersion relations for $S^z = -1$ magnons (+-) and for $S^z = 1$ magnons (-+), shown in Fig. 2. The energy splitting between the two polarizations, one of the hallmarks of altermagnetism, is clearly seen along high-symmetry directions in the Brillouin zone. We also show the dispersion relation for (linearized) Holstein-Primakoff magnons, extracted from a Heisenberg model for the altermagnet, including up to third-neighbor exchange. As expected, the agreement with the RPA treatment of the fermionic model is very good in this case.

Along specific lines within the Brillouin zone we observe a behavior analogous to the “band inversion” associated with topologically non-trivial electronic bands. For instance, along the reciprocal space path going from $(\frac{\pi}{a}, 0)$ to $(0, \frac{\pi}{a})$ there is a crossing between the $S^z = -1$ and the $S^z = 1$ magnon branches. In the presence of spin-orbit coupling a gap may appear at the crossing point $(\frac{\pi}{2a}, \frac{\pi}{2a})$, possibly accompanied by a finite Berry curvature. This crossing is also associated with the peculiar directional behavior of altermagnetic magnons. If we focus on magnons with one S^z value we see that the energy at the $(\frac{\pi}{a}, 0)$ point in reciprocal space (thus, propagating along the x direction in real space with wavelength $\lambda = 2a$) is $\sim 10\%$ different from that of a magnon with the same wavelength propagating along the y direction, as seen in Fig. 2. This difference can be as large as 40% for different values of the model parameters, as illustrated in fig. 11 of the appendix E, where we plot the magnons spectral densities as a function of propagation direction, for a fixed wavelength. Similar differences are seen between the energies of the two magnon flavors in metallic altermagnets (Fig. 4). Combined with the fact that, for sufficiently small wavelengths (typically smaller than $\sim 5a$) magnons with a well-defined S^z are strongly sublattice-polarized, this feature may be exploited to guide magnons in spintronics devices.

3.1 Itinerant altermagnet

We now turn our attention to the behaviour of magnons in itinerant altermagnets. In contrast to the insulating case, it can be expected that their lifetime is limited by Landau damping by Stoner modes [10, 11, 21]. Magnons with energies exceeding single-particle spin-flip excitations (also known as Stoner excitations), can decay into the Stoner continuum [10]. The magnon lifetime is inversely proportional to the density of Stoner modes, which is given by the imaginary part of the mean-field transverse susceptibility $\tilde{\chi}^\perp$. The effect of damping for a conducting altermagnet ($U = 2.5\tau$) is seen in the evolution of the spectral weight of spin excitations, shown along two different directions, (q, q) and $(q, 0)$ with $|q| < \frac{\pi}{a}$, in Figure 3a,b.

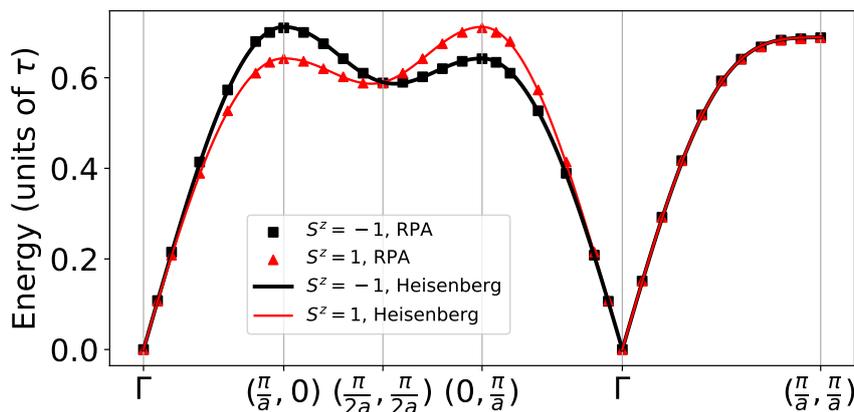


Figure 2: Dispersion relation for magnons in an insulating altermagnet in the strong coupling regime ($U = 10\tau$). The Heisenberg model used to fit the RPA energies includes up to third-neighbor exchange.

For low energy, the spectral density has well defined peaks, whose position gives the magnon energy and the inverse of its linewidth gives the magnon lifetime. As the energies are increased, the peaks get broader and, above some energy threshold, they vanish into a continuum. Along the (q, q) direction, both $S_z = \pm 1$ excitations have the same spectral weight (fig. 3a). In contrast, along the $(q, 0)$ direction (fig. 3b), the $S^z = -1$ spin excitations have Lorentzian spectral densities with relatively small linewidth in the whole wave number range, whereas the spectral density associated with the $S^z = 1$ spin excitations has a behavior similar to the (q, q) case. We thus find that, for itinerant altermagnets, magnons with a given S^z are only well defined along certain directions.

To make the connection between magnon lifetimes and density of Stoner modes, it is useful to plot both magnons' and Stoner excitations' spectral densities as color-coded functions of energy and wave number, shown in fig. 4. By following the bright spots in the top left panel, it is possible to trace dispersion relations for the $S^z = -1$ magnons, in analogy to the insulating case. For the $S^z = 1$ magnon, the bright spots disappear around $q \sim \frac{2\pi}{5a}$. This can be correlated with the boundaries of the Stoner continuum for $S^z = 1$ spin excitations, plotted in the bottom right panel. In contrast, the density of $S^z = -1$ Stoner modes is uniformly small over the whole wave number and energy ranges where $S^z = -1$ magnons exist. A detailed discussion of the origin of the density of Stoner modes in terms of the geometry of the spin-polarized Fermi surface pockets of the metallic altermagnet is presented in Appendix C.

The giant magnon-lifetime anisotropy is better seen in a color-coded polar plot of the magnon spectral density, for a fixed wavelength. The angular variable indicates the propagation direction, and the radial variable is the magnon energy. In fig. 5 we show such a plot for $\lambda = \frac{10a}{3}$ (wave number $q = \frac{3\pi}{5a}$). The top-left panel shows the spectral density ρ_A^{+-} for $S^z = -1$ magnons, projected on sublattice A, and the top-right panel displays the equivalent quantity for sublattice B (ρ_B^{+-}). It is clear that $S^z = -1$ magnons are strongly suppressed for angles $\gtrsim 30^\circ$, and the $S^z = 1$ magnons for angles $\lesssim 60^\circ$. Such strong directionality is rarely seen for quasiparticles and elementary excitations, and is potentially very useful for applications, especially when one considers the fact that magnons of wavelengths $\lambda \lesssim 4a$ live preferentially in one of the sublattices. Thus, it is in principle possible to excite magnons along specific directions by choosing their excitation frequency and the sublattice to excite. Selectively addressing the sublattice may be challenging in systems where spin sublattices have atomic size, but not so much in synthetic magnets, where spin sublattices are associated with molecules containing tens of atoms [20, 22].

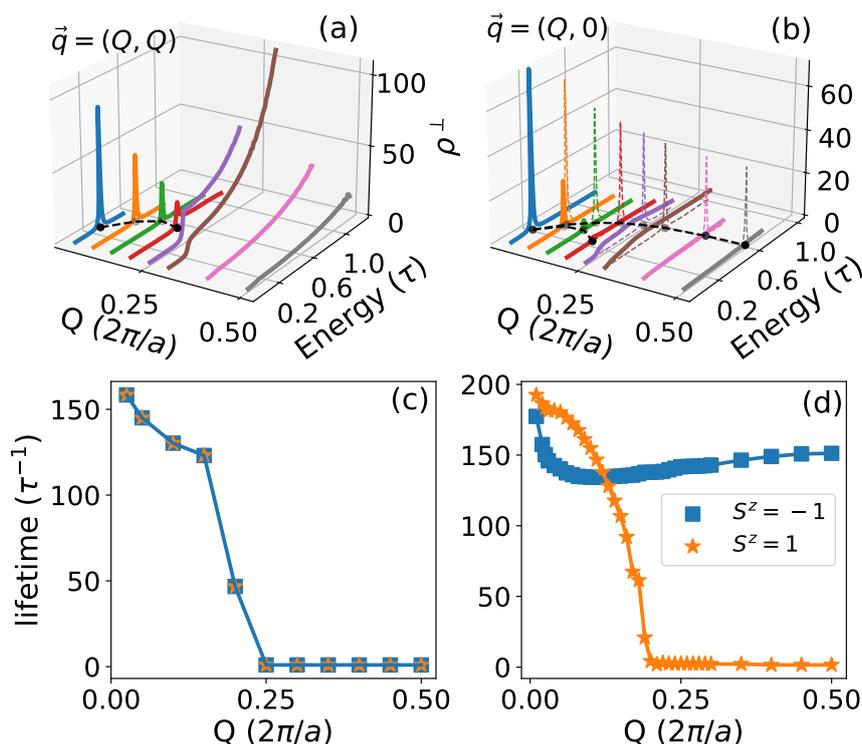


Figure 3: Top: spin excitation spectral densities in the metallic phase ($U = 2.5\tau$), along $\vec{q} = \frac{1}{\sqrt{2}}(q, q)$ (a) and $\vec{q} = (q, 0)$ (b), as a function of energy, for selected wave numbers. To improve visualization, the spectral density has been multiplied by 100 for the three largest wavenumbers ($q = 0.3, 0.4$ and 0.5), by 50 for $q = 0.25$ and by 5 for $q = 0.2$. In (b), solid lines correspond to ρ^{+-} , associated with the $S^z = 1$ spin excitations, and dashed lines correspond to ρ^{-+} , associated with the $S^z = -1$ spin excitations. Bottom: Lifetimes of the metallic magnons ($U = 2.5\tau$) propagating along the $\vec{q} = \frac{1}{\sqrt{2}}(q, q)$ (c) and $\vec{q} = (q, 0)$ (d), as a function of wave number, for $S^z = -1$ (squares) and $S^z = 1$ (stars) spin excitations.

We have also considered the case of a doped insulating altermagnet, by choosing $U = 3.5\tau$ and imposing an electronic occupation of 1.05 electrons per atomic site. In this case the anisotropic suppression of magnons is observed for propagation angles $30^\circ \lesssim \theta \lesssim 75^\circ$, as shown in the bottom panels of fig. 5. Thus, whenever it is possible to dope an insulating altermagnet electrostatically, it is in principle also possible to control electrostatically the propagation direction of magnons.

The effects of a giant spatial anisotropy in magnon lifetimes are likely to be noticed on several transport coefficients of metallic altermagnets [23]. Electronic transport is expected to be impacted by electron-magnon scattering, especially at low temperatures. Moreover, with current high-resolution spin-polarized electron energy loss spectroscopy [24, 25] it should be possible to probe experimentally the lifetime anisotropy predicted by our theoretical analysis.

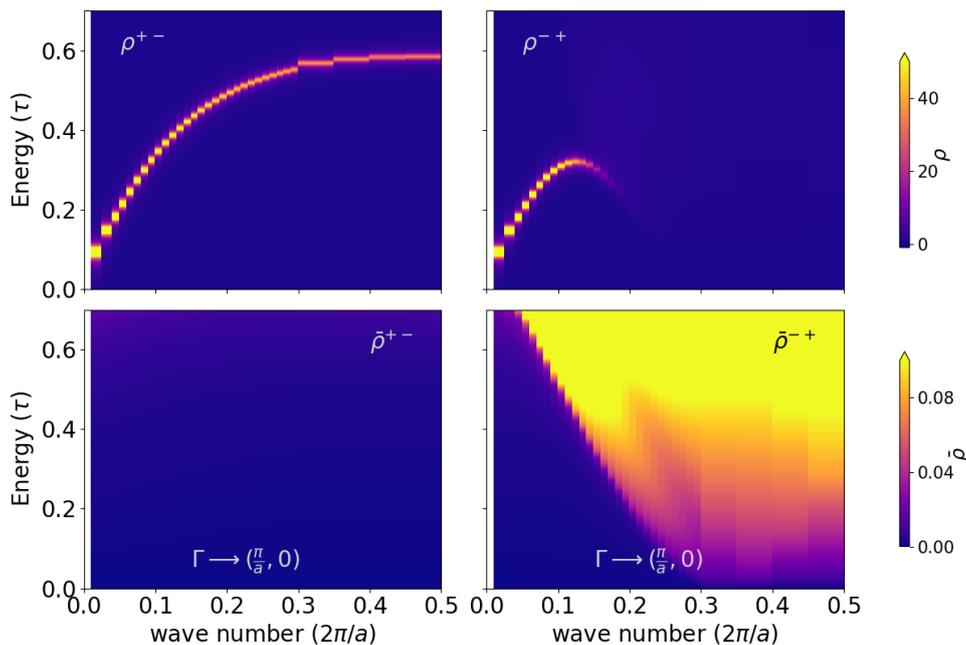


Figure 4: Top: Spectral densities for $S^z = -1$ (ρ^{+-} , left) and $S^z = 1$ (ρ^{-+} , right) metallic magnons ($U = 2.5\tau$) propagating along the x direction, as a function of wave number and energy. Bottom: Spectral densities for $S^z = -1$ ($\bar{\rho}^{+-}$, left) and $S^z = 1$ ($\bar{\rho}^{-+}$, right) Stoner excitations (single-particle spin flips) propagating along the x direction, as a function of wave number and energy.

We would like to emphasize that the lifetimes of magnons in itinerant magnets is related to the frequency and wave-vector dependent spectral density of Stoner modes, as detailed in the appendix B. The authors of a previous work [9] have estimated the relative intensity of magnon damping, as a function of magnon wave vector only, by integrating the spectral density of Stoner excitations over the whole magnon band width. This quantity can not be associated with the lifetime of individual magnons, although it can give an idea of the overall importance of Stoner excitations for the magnon spectrum. The relevant quantity for determining the lifetime of a magnon with well-defined energy and momentum is the mean-field transverse spin susceptibility calculated at the energy of the magnon (the pole of the RPA transverse spin susceptibility), as discussed in appendix B.

4 Conclusion

We have studied the intrinsic damping of magnons in altermagnets. These collective modes come with two values of $S_z = \pm 1$. Contrary to their counterparts in ferro- and antiferromagnets, we find a giant spatial anisotropy of magnon lifetimes in itinerant altermagnets. We find that, for a given direction, only magnons with a given sign of S_z survive without melting due to Landau damping by Stoner modes. The ultimate reason for this unique behaviour relies on the existence of spin-polarized Fermi surface pockets that characterizes altermagnets. Therefore, we expect our predictions are generic of all itinerant altermagnets, rather than model specific and will have to be considered in future magnonic applications.

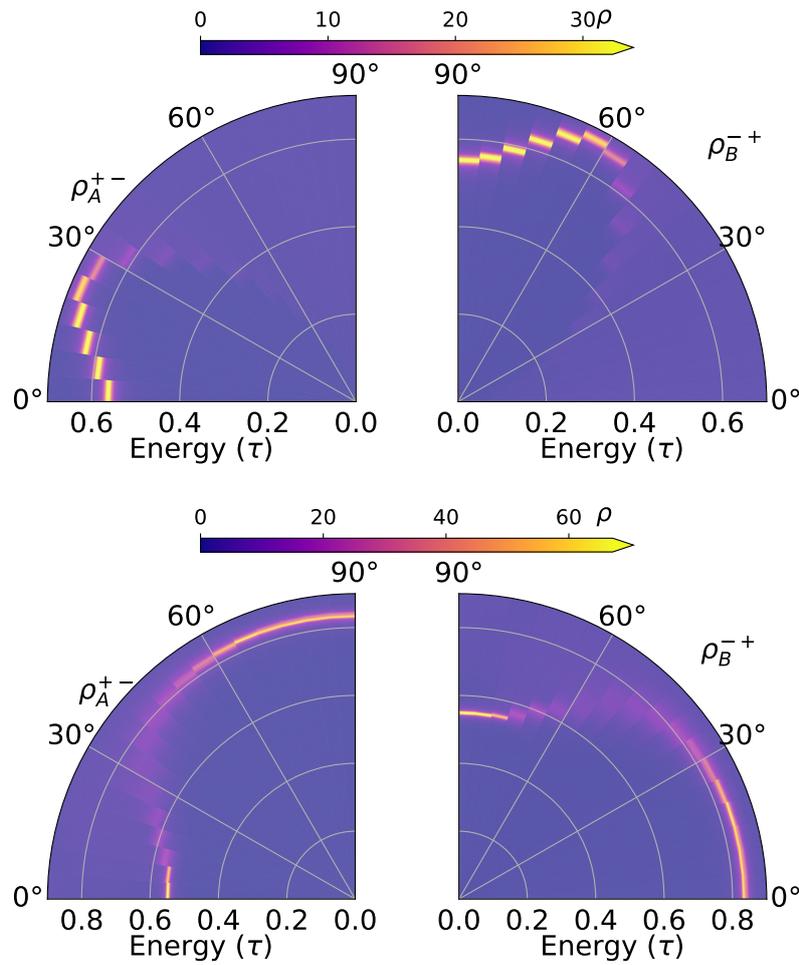


Figure 5: Magnon spectral densities as functions of propagation angle, for a fixed wavelength ($\frac{10a}{3}$). The radial variable represents energy (in units of the nearest-neighbor hopping τ). ρ_A^{+-} corresponds to $S^z = -1$ magnons, ρ_B^{-+} corresponds to $S^z = 1$ magnons. Top panels: metallic phase ($U = 2.5\tau$); bottom panels: doped insulating phase ($U = 3.5\tau$, excess 0.1 electrons per unit cell).

Acknowledgments

A.T.C. acknowledges fruitful discussions with D. L. R. Santos.

Funding information The authors acknowledge financial support from FCT (Grant No. PTDC/FIS-MAC/2045/2021), SNF Sinergia (Grant Pimag, CRSII5_205987) the European Union (Grant FUNLAYERS - 101079184). J.F.-R. acknowledges financial funding from Generalitat Valenciana (Prometeo2021/017 and MFA/2022/045), Spanish Government through PID2022-141712NB-C22, and the Advanced Materials programme supported by MCIN with funding from European Union NextGenerationEU (PRTR-C17.11) and by Generalitat Valenciana (MFA/2022/045).

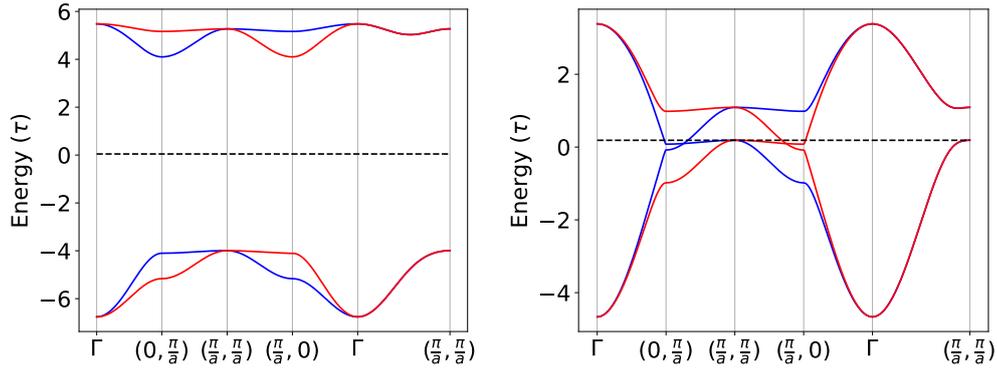


Figure 6: Electron energy bands for the strong-coupling insulating (left panel, $U = 10\tau$) and metallic (right panel, $U = 2.5\tau$) mean-field ground state configuration of the altermagnet Hamiltonian (eq. 1 of the main text), with $\tau' = 0.16\tau$ and $\delta = 0.83$. Red and blue lines represent \uparrow and \downarrow spin sub-bands. The black dashed line marks the Fermi energy.

A Mean-field electronic structure

We present the electronic bands corresponding to the mean-field configurations considered in the letter: strong-coupling insulating ($U = 10\tau$, fig. 6, left panel), metallic ($U = 2.5\tau$, fig 6, right panel), and slightly doped insulating ($U = 3.5\tau$, fig. 7, right panel). Both metallic and insulating phases have half-filled bands (one electron per lattice site), whereas the doped phase has 1.05 electrons per lattice site. Table 1 shows the values of the Hamiltonian parameters associated with the different phases, as well as the mean-field staggered magnetic moment per unit cell. We also show the intermediate-coupling insulating case ($U = 3.5\tau$, fig. 7, left panel).

B Relationship between the density of Stoner modes and the magnon lifetime

The standard random phase approximation (RPA) applied to the transverse spin susceptibility of a Hubbard Hamiltonian results in a relationship between the magnon Green function χ^{+-} and the mean-field Green function $\bar{\chi}^{+-}$,

$$\chi^{+-}(\vec{q}, \hbar\Omega) = \frac{\bar{\chi}^{+-}(\vec{q}, \hbar\Omega)}{1 + U\bar{\chi}^{+-}(\vec{q}, \hbar\Omega)}. \quad (\text{B.1})$$

Table 1: Values for the Hamiltonian parameters (in units of the nearest-neighbor hopping τ) used in this work, and respective staggered magnetic moment per unit cell, in units of Bohr magnetons μ_B .

	τ'	δ	U	$ m_\uparrow - m_\downarrow (\mu_B)$
Insulating (strong coupling)	0.16	0.83	10	1.86
Insulating (intermediate coupling)	0.16	0.83	3.5	1.28
Metallic	0.16	0.83	2.5	0.74

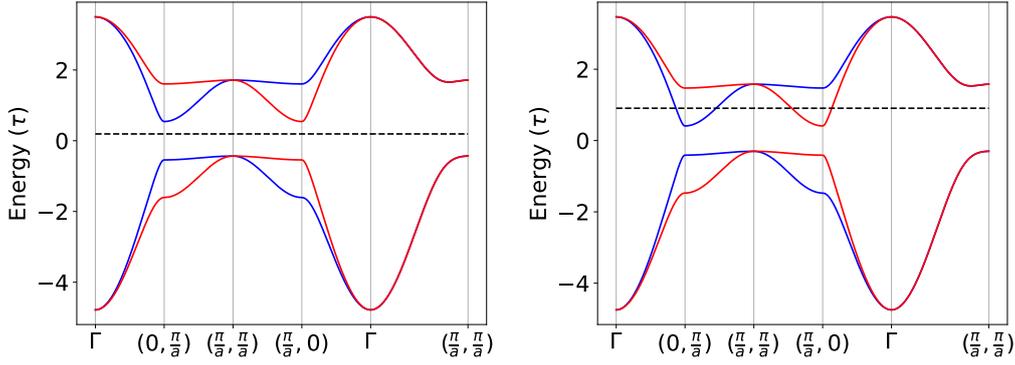


Figure 7: Electron energy bands for the mean-field ground state configuration of the altermagnet Hamiltonian (eq. 1 of the main text) in the insulating intermediate coupling regime ($U = 3.5\tau$) at half-filling (left panel) and away from half-filling (1.05 electrons per lattice site, right panel). The values for the hopping parameters are $\tau' = 0.16\tau$, $\delta = 0.83$. Red and blue lines represent \uparrow and \downarrow spin sub-bands. The black dashed line marks the Fermi energy.

We would like to cast this expression in a form that resembles a Green function with a self-energy correction,

$$G = \frac{1}{\bar{G}^{-1} + \Sigma}, \quad (\text{B.2})$$

where \bar{G} is the bare Green function and Σ is the self-energy. For this it is useful to split all quantities into their real and imaginary parts, denoted below by R and I subscripts. The real and imaginary parts of the magnon Green function then become (we will omit the energy and wave vector arguments for now to avoid cluttering the expressions)

$$\begin{aligned} \text{Re}[\chi^{+-}] &= \frac{\bar{\chi}_R^{+-}(1 + U\bar{\chi}_R^{+-}) + U(\bar{\chi}_I^{+-})^2}{(1 + U\bar{\chi}_R^{+-})^2 + (U\bar{\chi}_I^{+-})^2}, \\ \text{Im}[\chi^{+-}] &= \frac{\bar{\chi}_I^{+-}}{(1 + U\bar{\chi}_R^{+-})^2 + (U\bar{\chi}_I^{+-})^2}. \end{aligned} \quad (\text{B.3})$$

Similarly,

$$\begin{aligned} \text{Re}[G] &= \frac{\bar{G}^{-1} + \Sigma_R}{(\bar{G}^{-1} + \Sigma_R)^2 + \Sigma_I^2}, \\ \text{Im}[G] &= -\frac{\Sigma_I}{(\bar{G}^{-1} + \Sigma_R)^2 + \Sigma_I^2}. \end{aligned} \quad (\text{B.4})$$

By comparing the imaginary parts of the generic Green function G to $\text{Im}[\chi^{+-}]$ we notice immediately a clear analogy between $U\bar{\chi}_I^{+-}$ and Σ_I . Notice also that, as in the electronic case, magnon damping is inextricably tied to shifts in magnon energy, through the real part of the self-energy Σ_R . It is clear, then, that the lifetime of a magnon with wave vector \vec{q} and energy $\hbar\Omega(\vec{q})$ is determined by the spectral density of Stoner modes with wave vector \vec{q} and energy $\hbar\Omega(\vec{q})$.

C Origin of the anisotropic magnon lifetime

To further shed light on the mechanism behind the lifetime anisotropy of metallic magnons, it is useful to look at constant energy contours of the electronic bands in the mean-field altermagnetic configuration. The goal is to identify qualitatively the direction dependence of

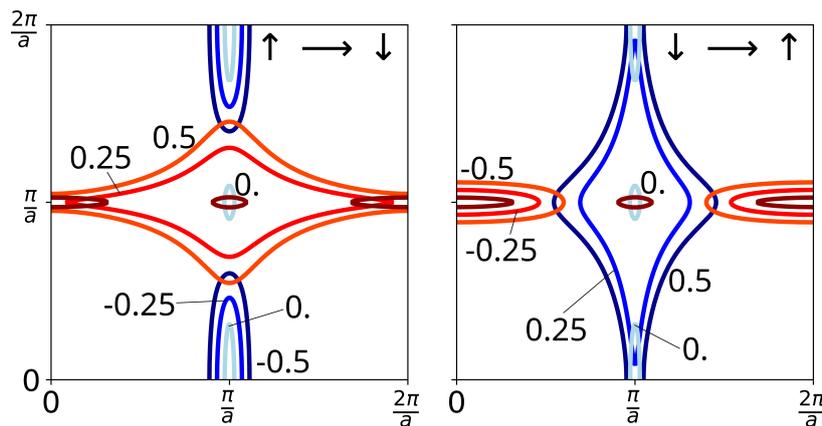


Figure 8: Contours of the electronic bands around the Fermi level; blue curves are for \uparrow spin bands, red curves for \downarrow . Left panel ($\uparrow \rightarrow \downarrow$): occupied \uparrow states (shades of blue, at energies $E_F - 0.5\tau$, $E_F - 0.25\tau$ and E_F) and unoccupied \downarrow states (shades of red, E_F , $E_F + 0.25\tau$ and $E_F + 0.5\tau$). Right panel ($\downarrow \rightarrow \uparrow$): occupied \downarrow states (shades of red, at energies $E_F - 0.5\tau$, $E_F - 0.25\tau$ and E_F) and unoccupied \uparrow states (shades of blue, E_F , $E_F + 0.25\tau$ and $E_F + 0.5\tau$).

single-particle spin-flip transitions that give rise to the anisotropic density of Stoner modes. In figure 8 we show three constant energy contours for each spin direction, blue contours for \uparrow spin electrons, red contours for \downarrow . In the left panel we show contours for occupied \uparrow states (including the Fermi contour at zero energy) and unoccupied \downarrow states (also including the Fermi contour at zero energy), relevant for $S^z = -1$ spin flips ($\downarrow \rightarrow \uparrow$). Thus, in the left panel we can identify possible single-particle spin-flip transitions by connecting blue and red contours. In the left panel we see that, apart from the very small pockets at $(\frac{\pi}{a}, \frac{\pi}{a})$, there is no horizontal line connecting blue and red contours. The consequence is that the density of $S^z = -1$ Stoner modes with wave vectors along the x direction is very small, and $S^z = -1$ magnons propagating along the x direction are long-lived. On the other hand, there are plenty of connections between blue and red contours at angles $\gtrsim 30^\circ$, meaning that magnons propagating along those directions will be substantially damped. In the right panel we show the analogous information for $S^z = 1$ spin flips ($\downarrow \rightarrow \uparrow$): occupied \downarrow states (including the Fermi contour at zero energy) and unoccupied \uparrow states (also including the Fermi contour at zero energy). Now it is clear that there are many possible single-particle spin-flip transitions with wave vectors along x , whereas very few with wave vectors along y , thus meaning that $S^z = 1$ magnons are strongly damped when propagating along x but long-lived when propagating along y .

D Insulating altermagnet in the intermediate coupling regime ($U = 3.5\tau$)

As mentioned in the main text, the insulating altermagnetic phase of the model is obtained for $U \gtrsim 3\tau$. In this regime, although the electronic bands are clearly those of an altermagnetic insulator (see the left panel of figure 7), the magnons bear marks of itinerant magnetism, especially at short wavelengths. A clear signature of itinerant behavior is the fact that the magnon lineshape acquires a finite linewidth and, at large enough energies, deviates significantly from a Lorentzian shape. This is seen in fig. 10 for a short wavelength magnon ($\lambda = 2a$) propagating along the x direction. The lineshape of the $S^z = 1$ magnon (right panel) is very close to a Lorentzian (dashed orange line). In contrast, the lineshape of the higher energy $S^z = -1$ magnon (left panel) is clearly not a Lorentzian.

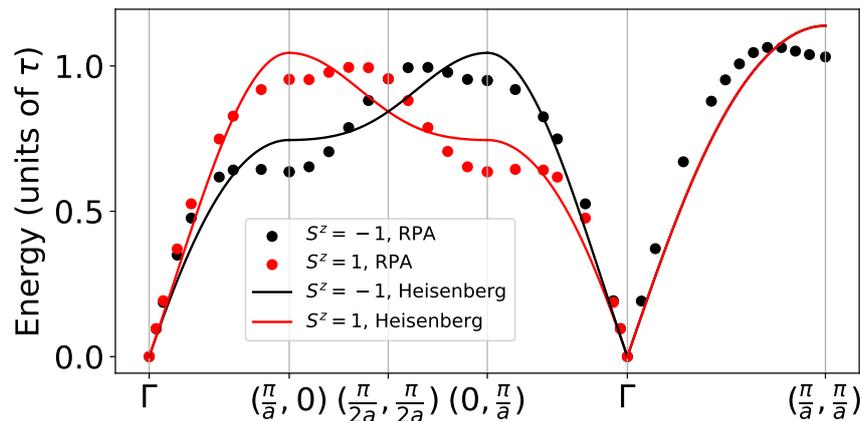


Figure 9: Dispersion relation for magnons in an insulating altermagnet in the intermediate coupling regime ($U = 3.5\tau$). The Heisenberg model used to fit the RPA energies includes up to third-neighbor exchange.

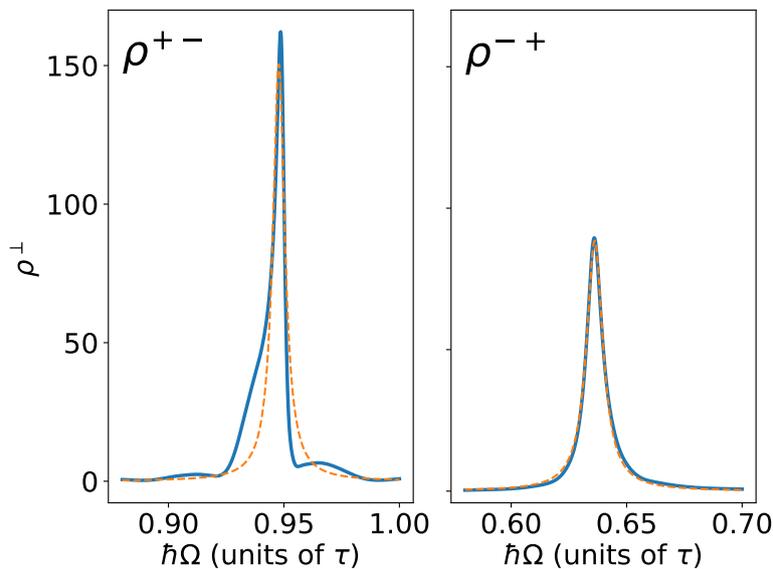


Figure 10: Spectral density of insulating magnons in the intermediate regime ($U = 3.5\tau$), for wave vector $\vec{q} = (\frac{\pi}{a}, 0)$. The left and right panels correspond to $S^z = -1$ and $S^z = 1$ magnons, respectively.

Another consequence of the coupling between magnons and Stoner excitations is a renormalization of magnon energies relative to those predicted by a localized spin model. In fig. 9 we compare the dispersion relation of magnons for the insulating altermagnet in the intermediate coupling regime, extracted from the fermionica model, to the energies of linearized Holstein-Primakoff magnons of a localized spins model, with exchanges up to third neighbors. The exchange parameters of the localized spin model have been obtained from a fit to the fermionic model energies. Although the main qualitative features of the dispersion are captured by the localized spins model, it does a poor job of matching quantitatively the magnon energies over the whole Brillouin zone, since the spin only model cannot capture the renormalization of the magnon energies by Stoner excitations.

To illustrate the effect of the coupling to the Stoner continuum we plot, in fig. 10, the spectral densities for magnons with $S^z = -1$ (ρ^{+-}) and $S^z = 1$ (ρ^{-+}). Notice that the lineshape of the $S^z = -1$ magnon (left panel) is clearly not a Lorentzian, whereas the $S^z = 1$ magnon is well fitted by a Lorentzian with a finite linewidth, denoting a finite lifetime.

E Directionality of the magnon spectrum in the insulating regime (intermediate coupling)

Here we illustrate the directional dependence of the magnon energies for the intermediate coupling ($U = 3.5\tau$) insulating case (figure 11). The main difference between this case and the metallic and slightly doped cases is that the magnons appear as well-defined collective excitation for all directions of propagations. In Fig. 5 of the main text, illustrating the metallic case, it is clear that, for certain directions of propagation, the magnon feature in the spectral density is suppressed. For the insulating intermediate coupling case magnons propagating along all directions are well-defined, but their energies are strongly anisotropic, as illustrated in Fig. 11. The smallest magnon energy for that wavelength ($\lambda = \frac{10a}{3}$) is $\sim 0.65\tau$, whereas the largest magnon energy is $\sim 0.9\tau$.

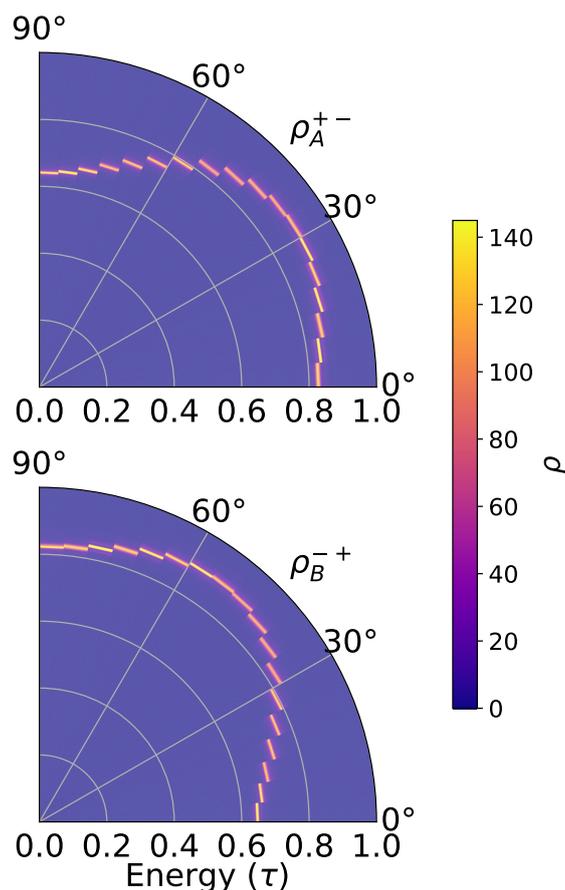


Figure 11: **Directionality of magnons in an insulator.** We plot the magnon spectral densities, as a function propagation angle, for a fixed wavelength ($\frac{10a}{3}$) for an insulating altermagnet. The top panel shows ρ_A^{+-} (for the $S^z = -1$ polarization) and the bottom panel shows ρ_B^{-+} (for the $S^z = 1$ polarization). The radial variable represents energy (in units of the nearest-neighbor hopping τ).

References

- [1] L.-D. Yuan, Z. Wang, J.-W. Luo, E. I. Rashba and A. Zunger, *Giant momentum-dependent spin splitting in centrosymmetric low-z antiferromagnets*, Phys. Rev. B **102**, 014422 (2020), doi:[10.1103/PhysRevB.102.014422](https://doi.org/10.1103/PhysRevB.102.014422).
- [2] L. Šmejkal, J. Sinova and T. Jungwirth, *Emerging research landscape of altermagnetism*, Phys. Rev. X **12**, 040501 (2022), doi:[10.1103/PhysRevX.12.040501](https://doi.org/10.1103/PhysRevX.12.040501).
- [3] L. Šmejkal, J. Sinova and T. Jungwirth, *Beyond conventional ferromagnetism and antiferromagnetism: A phase with nonrelativistic spin and crystal rotation symmetry*, Phys. Rev. X **12**, 031042 (2022), doi:[10.1103/PhysRevX.12.031042](https://doi.org/10.1103/PhysRevX.12.031042).
- [4] S. I. Pekar and E. I. Rashba, *Combined resonance in crystals in inhomogeneous magnetic fields*, Zh. Eksp. Teor. Fiz. **47**, 1927 (1964).
- [5] T. A. Maier and S. Okamoto, *Weak-coupling theory of neutron scattering as a probe of altermagnetism*, Phys. Rev. B **108**, L100402 (2023), doi:[10.1103/PhysRevB.108.L100402](https://doi.org/10.1103/PhysRevB.108.L100402).
- [6] S. Sarkar et al., *Composite antiferromagnetic and orbital order with altermagnetic properties at a cuprate/manganite interface*, PNAS Nexus **3**, pgae100 (2024), doi:[10.1093/pnasnexus/pgae100](https://doi.org/10.1093/pnasnexus/pgae100).
- [7] Y. Takahashi, *Spin fluctuation theory of itinerant electron magnetism*, Springer, Berlin, Heidelberg, Germany, ISBN 9783642366659 (2013), doi:[10.1007/978-3-642-36666-6](https://doi.org/10.1007/978-3-642-36666-6).
- [8] S. M. Rezende, A. Azevedo and R. L. Rodríguez-Suárez, *Introduction to antiferromagnetic magnons*, J. Appl. Phys. **126**, 151101 (2019), doi:[10.1063/1.5109132](https://doi.org/10.1063/1.5109132).
- [9] L. Šmejkal et al., *Chiral magnons in altermagnetic RuO₂*, Phys. Rev. Lett. **131**, 256703 (2023), doi:[10.1103/PhysRevLett.131.256703](https://doi.org/10.1103/PhysRevLett.131.256703).
- [10] S. Doniach and E. Sondheimer, *Green's functions for solid state physicists*, Imperial College Press, London, UK, ISBN 9781860940804 (1998).
- [11] L. H. M. Barbosa, R. B. Muniz, A. T. Costa and J. Mathon, *Spin waves in ultrathin ferromagnetic overlayers*, Phys. Rev. B **63**, 174401 (2001), doi:[10.1103/PhysRevB.63.174401](https://doi.org/10.1103/PhysRevB.63.174401).
- [12] E. Michel, H. Ibach, C. M. Schneider, D. L. R. Santos and A. T. Costa, *Lifetime and mean free path of spin waves in ultrathin cobalt films*, Phys. Rev. B **94**, 014420 (2016), doi:[10.1103/PhysRevB.94.014420](https://doi.org/10.1103/PhysRevB.94.014420).
- [13] F. Garcia-Gaitan, A. Kefayati, J. Q. Xiao and B. K. Nikolić, *Magnon spectrum of altermagnets beyond linear spin wave theory: Magnon-magnon interactions via time-dependent matrix product states versus atomistic spin dynamics*, Phys. Rev. B **111**, L020407 (2025), doi:[10.1103/PhysRevB.111.L020407](https://doi.org/10.1103/PhysRevB.111.L020407).
- [14] J. Sødequist and T. Olsen, *Two-dimensional altermagnets from high throughput computational screening: Symmetry requirements, chiral magnons, and spin-orbit effects*, Appl. Phys. Lett. **124**, 182409 (2024), doi:[10.1063/5.0198285](https://doi.org/10.1063/5.0198285).
- [15] P. M. Cónsoli and M. Vojta, *SU(N) altermagnetism: Lattice models, magnon modes, and flavor-split bands*, (arXiv preprint) doi:[10.48550/arXiv.2402.18629](https://doi.org/10.48550/arXiv.2402.18629).
- [16] E. W. Hodt and J. Linder, *Spin pumping in an altermagnet/normal-metal bilayer*, Phys. Rev. B **109**, 174438 (2024), doi:[10.1103/PhysRevB.109.174438](https://doi.org/10.1103/PhysRevB.109.174438).

- [17] A. E. Kanj, O. Gomonay, I. Boventer, P. Bortolotti, V. Cros, A. Anane and R. Lebrun, *Antiferromagnetic magnon spintronic based on nonreciprocal and nondegenerated ultrafast spin-waves in the canted antiferromagnet α -Fe₂O₃*, *Sci. Adv.* **9**, eadh1601 (2023), doi:[10.1126/sciadv.adh1601](https://doi.org/10.1126/sciadv.adh1601).
- [18] P. Das, V. Leeb, J. Knolle and M. Knap, *Realizing altermagnetism in Fermi-Hubbard models with ultracold atoms*, *Phys. Rev. Lett.* **132**, 263402 (2024), doi:[10.1103/PhysRevLett.132.263402](https://doi.org/10.1103/PhysRevLett.132.263402).
- [19] J. Henriques, D. Jacob, A. Molina-Sánchez, G. Catarina, A. T. Costa and J. Fernández-Rossier, *Beyond spin models in orbitally degenerate open-shell nanographenes*, *Nano Lett.* **24**, 12928 (2024), doi:[10.1021/acs.nanolett.4c03416](https://doi.org/10.1021/acs.nanolett.4c03416).
- [20] G. Catarina, J. C. G. Henriques, A. Molina-Sánchez, A. T. Costa and J. Fernández-Rossier, *Broken-symmetry magnetic phases in two-dimensional triangulene crystals*, *Phys. Rev. Res.* **5**, 043226 (2023), doi:[10.1103/PhysRevResearch.5.043226](https://doi.org/10.1103/PhysRevResearch.5.043226).
- [21] A. T. Costa, R. B. Muniz and D. L. Mills, *Spin waves and their damping in itinerant ultrathin ferromagnets: Intermediate wave vectors*, *Phys. Rev. B* **74**, 214403 (2006), doi:[10.1103/PhysRevB.74.214403](https://doi.org/10.1103/PhysRevB.74.214403).
- [22] Y. Liu, J. Yu and C.-C. Liu, *Twisted magnetic Van der Waals bilayers: An ideal platform for altermagnetism*, *Phys. Rev. Lett.* **133**, 206702 (2024), doi:[10.1103/PhysRevLett.133.206702](https://doi.org/10.1103/PhysRevLett.133.206702).
- [23] I. Žutić, J. Fabian and S. Das Sarma, *Spintronics: Fundamentals and applications*, *Rev. Mod. Phys.* **76**, 323 (2004), doi:[10.1103/RevModPhys.76.323](https://doi.org/10.1103/RevModPhys.76.323).
- [24] K. Zakeri and C. Berthod, *Theory of spin-polarized high-resolution electron energy loss spectroscopy from nonmagnetic surfaces with a large spin-orbit coupling*, *Phys. Rev. B* **106**, 235117 (2022), doi:[10.1103/PhysRevB.106.235117](https://doi.org/10.1103/PhysRevB.106.235117).
- [25] K. Zakeri, D. Rau, J. Jandke, F. Yang, W. Wulfhekel and C. Berthod, *Direct probing of a large spin-orbit coupling in the FeSe superconducting monolayer on STO*, *ACS Nano* **17**, 9575 (2023), doi:[10.1021/acsnano.3c02876](https://doi.org/10.1021/acsnano.3c02876).