

Reply to the Referee's reports

“Curvature effects on phase transitions in chiral magnets”

First of all we thank the Editor for the efficient review process and the Referees for their time as well as constructive criticism aimed at improving our manuscript. Following the suggestions we have improved the paper. All revisions are indicated in the manuscript in blue color.

Sincerely yours,
Authors.

Reply to Referee #1

Comment 1:

In the conclusion, it would be good to go beyond the calculation results and explain in simple terms why the effect of curvature is stronger when competing with Neel type DMI. It would be good also to have some outlook. Indeed, the paper shows that large curvatures are required to get large effects. But when the curvature is too large, the hedgehog structure becomes unstable. Indeed, the κ^2 energy of the hedgehog state should be compared to that of the uniform (in 3D space) magnetization, which is 1/2 in the same units, discarding magnetostatic terms. This leads to $\kappa < 0.707$, close to the value 0.72 often considered in the figures. From this, I reckon that the graphs stop at $\kappa = 0.72$ because, above it, one goes to the uniform magnetization. This would thus be the largest possible curvature.

Answer 1:

The answer on this comment we would like to split into two parts:

- Following Referee's comment we added into the conclusions the explanation why the curvature induced effects is stronger in the case of the Néel type of DMI:

page 7 3rd sentence in conclusions

The curvature effects are more pronounced for the case of Néel intrinsic DMI because the curvature-induced DMI is usually of the Néel type, thus a direct competition takes place. Note, that for the same reason the Néel skyrmions are more strongly affected by the curvature gradients as compared to the Bloch skyrmions [33] and the DMI-free skyrmions stabilized by curvature are of Néel type [45].

- Indeed, with the increase of the curvature the hedgehog state becomes unstable and the transition to a nonuniform state takes place. This transition is denoted by the blue solid line on the phase diagrams shown in Fig. 3. For small enough DMI, the nonuniform state is the two-domain state ($q = 1$) which can be thought of as an onion state of the tube. With the further curvature increase the two-domain state asymptotically approaches the uniform state with $\mathbf{m} = \mathbf{m}_0 \perp \hat{\mathbf{z}}$. This uniform state has energy 1/2 in the considered units. Note

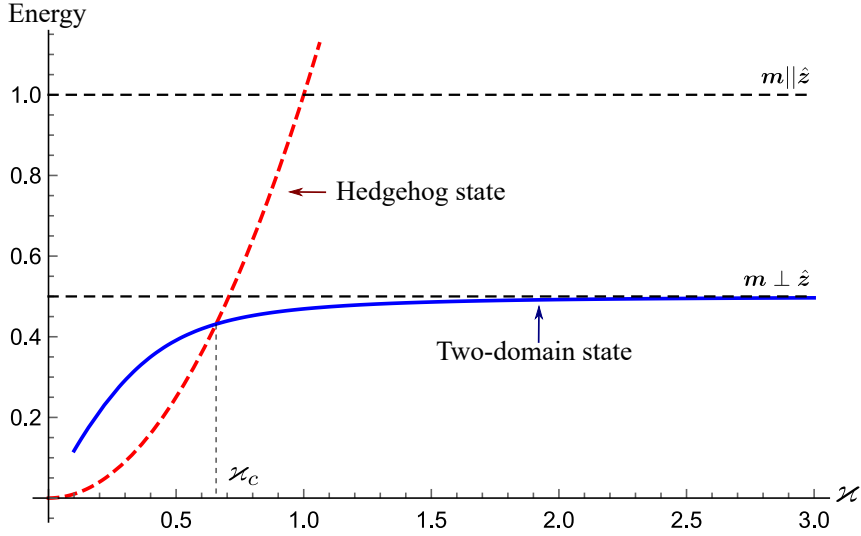


Figure R.1: Energies of different states of the tube for the case $d = 0$.

that the other uniform state with $\mathbf{m} = \mathbf{m}_0 \parallel \hat{\mathbf{z}}$ has higher energy equal to 1. The comparison of energies is shown in the Fig. R.1. As one can see there is only one critical curvature value $\kappa_c \approx 0.657$ (for $d = 0$), which separates the hedgehog and two-domain states. This critical curvature was previously found in Ref. [53]. There are no other critical values. The fact that the phase diagrams in Fig. 3 are limited to $\kappa \approx 0.72$ is just a necessary contingency (the plots must be terminated somewhere).

Comment 2:

The paper makes a large use of analytical calculations. So the formulas should be carefully checked. I found several mistakes in them, which costed me some time.

- (a) in (B.1), line 2, the second term should have $\sin^2(\phi + \psi)$
- (b) in (B.1), line 3, the cross product $\nabla\theta \times \epsilon$ should be transformed to a scalar by a dot product with the normal vector \mathbf{n} , like in (A.5d)
- (c) in (B.2), the first equalities for each line do not hold, as numerical factors are lacking. These play no role for the second equalities, as the right-hand side is zero. But they are important if the reader wants to rederive these formulas. So these factors ($1/2$ in front of $dE/d\theta$ and $dE/d\phi$, $1/(2\kappa)$ in front of $dE/d\psi$) should be restored.
- (d) for (B.4), second line, same comment as for (B.1)
- (e) for (B.5), same comment as for (B.2)

Answer 2:

We appreciate that the Referee has read our manuscript so carefully and we thank him/her for the spend time. Indeed, in all cases mentioned by the Referee we made misprints. Fortunately, these mistakes are just typos and they do not affect the subsequent calculations. We fixed the misprints in the manuscript.

Comment 3:

The paper uses sometimes the CGS system, sometimes the SI system. This forces

to replicate the column of Table I (with a mistake there: 1 mJ/m^2 is equal to 1 erg/cm^2). I suggest to follow the (not so) modern practice, namely to use SI units throughout.

Answer 3:

Following the recommendation of the Referee we proceed to SI units. Note that the supplementals are mainly affected, since we use the dimensionless units for the main text.

Comment 4:

Check the English. Especially for the abstract. The "del operator" mentioned below (A.2) is not a standard term. Why not simply say "gradient"? The word "whereas" in between (C.2d) and (C.2e) seems to stand for "whether". Ref. [46] should refer to Appendix D.

Answer 4:

We thanks the Referee for his comment. In the DMI energy we have a divergence, curl, and gradient. Therefore we used term "del operator". We also revised text accordingly.

Reply to Referee #2

Comment 1:

Do the authors study the possibility of the solution corresponding to the hedgehog state is a special case of a general solution given by Eq. (5)?

Answer 1:

No, formulas (5) and (6) describe the *nonuniform* multidomain state with $q \geq 1$. The *uniform* hedgehog state with $q = 0$ we consider separately. In principle, formula (5) can be used for the hedgehog state at the limit case $T \rightarrow \infty$ ($C \rightarrow 0$). However, we believe that such a generalization may confuse the reader.

Comment 2:

From the analysis of Fig. 3, one can state that there are regions in which Neel DMI and Bloch DMI coexist? If yes, it would be useful to include this discussion in the text.

Answer 2:

The DMI strength shown in Fig. 3 is the intrinsic DMI (not curvature induced). And in our MS we do not consider the joint action of intrinsic Bloch and Néel DMI. In order to prevent the possible confusion we denoted it in the caption of Fig. 3:

page 5 caption of Fig. 3

... with Bloch and Néel type of intrinsic DMI ...

Comment 3:

There are some parts of the text that are confusing. For instance, the presentation of hedgehog and inhomogeneous solutions are presented without proper separation. This fact can bring some difficulties in the understanding of the results. I recommend the authors to perform a revision in the text to better present their results. For instance, there are some parameters that are not presented immediately after appearing in the equations, as the integration constant C .

Answer 3:

We thanks the referee for his comment. The homogeneous hedgehog state is trivial,

therefore we did not consider it in a subsection. Following the Referee’s recommendation we highlighted words “homogeneous” and “inhomogeneous” in the main text. We insert the following text before formula (5)

page 5 before Eq. (5)

... normal magnetization component of the inhomogeneous state ...

And we add the description of constant C :

page 5 after Eq. (5)

... C is an integration constant ...

Comment 4:

The text should be revised. There are some problems with English. For instance: “one obtains”, “is reads”, and others.

Answer 4:

We proofread the text.

Comment 5:

What do the authors mean with the “simultaneous action of DMI and curvature”?

Answer 5:

We reformulate it as follows:

page 6 before formula (7)

... for the case $\varkappa > 0$ and $d^2 > 0$ the DW width decreases as compared to the case $\varkappa = 0$ (planar film) or $d = 0$.

And as follows:

page 7 before formula (11)

... due to non-zero DMI and curvature the width of the well separated Néel DWs is increased. This behavior is opposite to the case of the Bloch DWs.

Comment 6:

I call the attention of the authors for some interesting results regarding curvature effects in nanomagnets with DMI. Some of them were developed by authors of this paper: Phys. Rev. B 102, 014432 (2020); <https://doi.org/10.1038/s42005-020-0387-2>; Phys. Rev. B 102, 024444 (2020); Nanotechnology 31, 125707 (2020); J. Appl. Phys. 108, 033917 (2010); <https://doi.org/10.1038/s41598-019-45553-w>; and others.

Answer 6:

We thank the Referee’s for his comment. We added the corresponding citations in the introduction with Refs. [33, 34] and Ref. [23] into the discussion about magnetostatic interaction.

Curvature effects on phase transitions in chiral magnets

Kostiantyn V. Yershov^{1,2*}, Volodymyr P. Kravchuk^{1,3}, Denis D. Sheka⁴,
Ulrich K. Röbner²

1 Bogolyubov Institute for Theoretical Physics of National Academy of Sciences of
Ukraine, 03143 Kyiv, Ukraine

2 Leibniz-Institut für Festkörper- und Werkstoffforschung, IFW Dresden, 01069
Dresden, Germany

3 Institut für Theoretische Festkörperphysik, Karlsruher Institut für Technologie,
D-76131 Karlsruhe, Germany

4 Taras Shevchenko National University of Kyiv, 01601 Kyiv, Ukraine

*yershov@bitp.kiev.ua

Abstract

Periodical equilibrium states of magnetization exist in chiral ferromagnetic films, if the constant of **antisymmetric exchange (Dzyaloshinskii–Moriya interaction)** exceeds some critical value. Here, we demonstrate that **this critical value** can be significantly modified in curved film. **The competition between symmetric and antisymmetric exchange interactions in a curved film** can lead to a new type of domain wall which is inclined with respect to the cylinder axis. **The wall structure is intermediate between Bloch and Néel ones.** The exact analytical solutions for phase boundary curves and the new domain wall are obtained.

Contents

1	Introduction	2
2	Model	2
3	DMI of Bloch type	4
4	DMI of Néel type	6
5	Conclusions	7
A	Introduction of the curvilinear basis and magnetic interactions on a curvilinear shell	8
B	DMI induced periodical solution for a cylindrical surface	9
	B.1 DMI of Bloch type	9
	B.2 DMI of Néel type	10
C	Details of the spin-lattice simulations	12

C.1 Simulations of tubes without dipole-dipole interaction ($\mathcal{D} = 0$)	13
C.2 Simulations of tubes with dipole-dipole interaction ($\mathcal{D} = 1$)	14
D Details of full-scale micromagnetic simulations	15
D.1 Full-scale micromagnetic simulations with small quality factor	15
References	15

1 Introduction

Magnetic nanostructure with arbitrary curvilinear shapes can acquire a multitude of ground-state configurations [1–4] under the twisting influence of the [Dzyaloshinskii–Moriya interaction \(DMI\)](#) and the effect of the curved surfaces/interfaces. Modulated states arise, if a nanomagnet has typical lengths comparable to the twisting length [5–7] which is determined by the material parameters and can be influenced by the curvature. The magnetic phase-diagram of curvilinear ferromagnets becomes much richer as compared to a flat specimen. Among simple curvilinear shapes, hollow cylindrical tubes or wires are very promising for a broad range of biomedical [8–11] and technological [12, 13] applications, also see Review [14]. Nanotubes can also be assembled into interconnected networks [15] which makes them attractive for advanced hardware concepts in neuromorphic computing [16]. It is important to note that magnetic nanotubes can be produced experimentally with different techniques [17–22].

Magnetic nanotubes belong to the simplest magnetic systems with pattern-induced chirality breaking [1, 23]: two energetically equivalent vortex [domain walls \(DWs\)](#) with opposite chiralities possess different dynamical properties, leading to a suppression of the Walker breakdown [24] and Cherenkov-like radiation of magnons for fast DWs [25, 26]. Additionally, tubular geometry results in the asymmetric spin-wave dispersion relation in azimuthally magnetized tubes [27, 28], similarly to systems with intrinsic DMI [29, 30]. In this context, an interrelation between effects due to intrinsic DMI and curvature-induced chirality is expected. An important question is, how the curvature modifies the critical DMI d_0 [5, 7], which separates homogeneous and periodic magnetization structures. This is important for assessing the stability of skyrmions [31] and their motion [32] along the tubes and other curvilinear surfaces [33, 34]. Here, we present a detailed study of equilibrium states of the ferromagnetic nanotubes with intrinsic DMI of different symmetries. We show that: (i) The curvature modifies the critical DMI strength. (ii) New types of DWs appear in the periodic phase.

2 Model

We consider the tubular shell as a ribbon of thickness h and width w , close-coiled upon the rod of radius R , see Fig. 1. The central line of the ribbon makes angle $\pi/2 - \psi$ with the cylinder axis. The ribbon width is determined as $w = 2\pi R \sin \psi$,

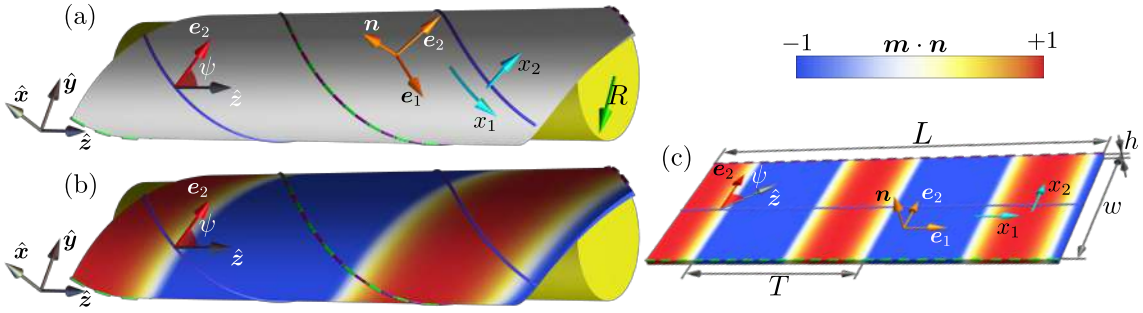


Figure 1: (Color online) **Schematic presentation of the geometry:** (a),(b) The tubular shell is presented as a ribbon [gray in (a) and colored surfaces in (b)] of thickness h and width w which is tightly (without gaps) rolled up around the rod (yellow) of radius R ; (c) unrolled ribbon. Thick blue line $\boldsymbol{\varsigma}(x_1, 0)$ corresponds to the ribbon center, dashed lines $\boldsymbol{\varsigma}(x_1, -w/2)$ and $\boldsymbol{\varsigma}(x_1, w/2)$ with $w = 2\pi R \sin \psi$ correspond to the ribbon side edges. Color scheme corresponds to the normal magnetization component.

this results in a closed cylindrical surface, i.e. without a bordering rim along the axis. The surface of the ribbon $\boldsymbol{\varsigma}$ can be parameterized in the following way: $\boldsymbol{\varsigma}(x_1, x_2) = R \cos(\rho_s/R) \hat{\boldsymbol{x}} + R \sin(\rho_s/R) \hat{\boldsymbol{y}} + \rho_z \hat{\boldsymbol{z}}$, where $\rho_s = x_1 \cos \psi - x_2 \sin \psi$ and $\rho_z = x_1 \sin \psi + x_2 \cos \psi$, $x_1 \in [0, L]$ and $x_2 \in [-w/2, w/2]$ are coordinates within the ribbon surface, see Fig. 1. Such a nontrivial parametrization of the cylinder surface is useful for description of DWs which may be arbitrarily oriented along the tube axis, i.e. ψ defines the angle between the DW and $\hat{\boldsymbol{z}}$ axis. Parametrization $\boldsymbol{\varsigma}(x_1, x_2)$ induces the natural tangential basis $\boldsymbol{e}_\alpha = \partial_\alpha \boldsymbol{\varsigma}$ with the corresponding Euclidean metric tensor elements $g_{\alpha\beta} = \boldsymbol{e}_\alpha \cdot \boldsymbol{e}_\beta = \delta_{\alpha\beta}$. Here, $\alpha, \beta = 1, 2$ and $\partial_\alpha \equiv \partial_{x_\alpha}$. Note that in our particular case \boldsymbol{e}_α are orthogonal vectors of unit length. This enables us to introduce the orthonormal basis $\{\boldsymbol{e}_1, \boldsymbol{e}_2, \boldsymbol{n}\}$, where $\boldsymbol{n} = \boldsymbol{e}_1 \times \boldsymbol{e}_2$ is a normal vector to the surface, see Fig. 1.

Assuming small thickness of the coiled film ($h \ll R$), we consider the magnetization as a continuous function of two variables $\boldsymbol{M} = \boldsymbol{M}(x_1, x_2)$, which obeys the periodic boundary condition $\boldsymbol{M}(x_1, w/2) = \boldsymbol{M}(x_1 + T, -w/2)$ with $T = 2\pi R \cos \psi$. Such constraint for \boldsymbol{M} is a requirement of continuity of the magnetization for the used parameterization of the cylinder surface. The energy of the system is modelled by the functional

$$E = h \int \int [\mathcal{A} \mathcal{E}_x + \mathcal{K} (1 - m_n^2) + \mathcal{D} \mathcal{E}_D] dx_1 dx_2, \quad (1)$$

where three contributions are taken into account. The first term in (1) is the exchange energy density with $\mathcal{E}_x = \sum_{i=x,y,z} (\partial_i \boldsymbol{m})^2$, where \mathcal{A} is the exchange constant. Here $\boldsymbol{m} = \boldsymbol{M}/M_s$ is the unit magnetization vector with M_s the saturation magnetization. The second term is the easy-normal anisotropy, where $\mathcal{K} > 0$ and $m_n = \boldsymbol{m} \cdot \boldsymbol{n}$ is the normal magnetization component. The competition between exchange and anisotropy results in the magnetic length $\ell = \sqrt{\mathcal{A}/\mathcal{K}}$, which determines a length scale of the system. The last term in (1) represents DMI contribution \mathcal{E}_D with \mathcal{D} the DMI constant. We consider two types of DMI: (i) $\mathcal{E}_D^B = \boldsymbol{m} \cdot [\nabla \times \boldsymbol{m}]$ is applicable for systems with T and O symmetries [30]. In the following this is called DMI of Bloch type, since for planar films it results in DWs and skyrmions of Bloch type. (ii) $\mathcal{E}_D^N = m_n \nabla \cdot \boldsymbol{m} - \boldsymbol{m} \cdot \nabla m_n$ is valid for ultrathin films [35, 36], bilayers [37] or materials belonging to C_{nv} crystallographic group. In the following we call this DMI

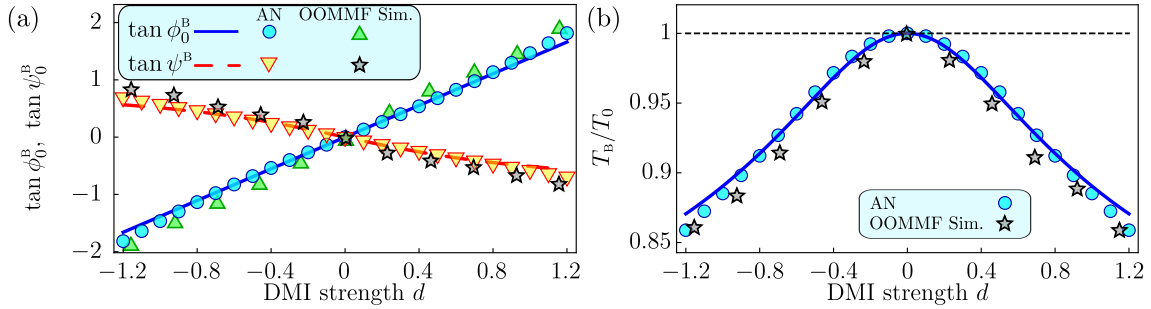


Figure 2: (Color online) **Parameters of periodical state in tubular shells:** (a) and (b) show the angles ϕ_0^B , ψ^B , and period T_B as functions of DMI for $\varkappa \approx 0.72$. In (a), lines are plotted by means of (3); in (b), solid line is $T_B/T_0 = |\cos \psi^B|$. Symbols correspond to numerical simulations: “AN” – spin-lattice simulations with the effectively reduced anisotropy constant [see Appendix C]; and “OOMMF Sim.” – full-scale micromagnetic simulations [see Appendix D].

of Néel type. Here and below the indices B and N correspond to the Bloch and Néel DMI types, respectively.

In our model, we assume that the magnetostatic contribution is negligibly small as compared with the anisotropy contribution, i.e. we consider systems with quality factor $Q = 2\mathcal{K}/(\mu_0 M_s^2) \gg 1$ [38]. Examples of chiral magnets which satisfies these condition were recently studied in [32,39]. Additionally, for thin stripes the magnetostatic contribution can be reduced to an effective easy-surface anisotropy [23,40–43], which simply results in a shift of the anisotropy constant $\mathcal{K} \rightarrow \mathcal{K} - \mu_0 M_s^2/2$. This approximation is widely used for the description of equilibrium states on toroidal nanoshells [44], statics and dynamics of skyrmions [32,45–47] and DWs [48] in curved nanoshells.

Using a curvilinear reference frame we parametrize the magnetization in the following way $\mathbf{m} = \sin \theta \cos \phi \mathbf{e}_1 + \sin \theta \sin \phi \mathbf{e}_2 + \cos \theta \mathbf{n}$. Expressions for \mathcal{E}_x , \mathcal{E}_D^B , and \mathcal{E}_D^N for a general case of a local curvilinear basis were previously obtained in Refs. [49], [50], and [45], respectively (also see Appendix A). In the following we look for the equilibrium magnetization states. To this end we minimize energy (1) with respect to functions $\theta(x_1, x_2)$, $\phi(x_1, x_2)$ and constant ψ .

3 DMI of Bloch type

First, we consider the case of Bloch DMI $\mathcal{E}_D = \mathcal{E}_D^B$. For such kind of DMI we find two solutions, see Appendix B.1. The *homogeneous* (in the curvilinear reference frame) solution corresponds to the hedgehog state ($\mathbf{m} = \pm \mathbf{n}$), its total energy normalized by $E_0 = hwL\mathcal{K}$ is

$$\mathcal{E}_B^{\text{un}} = \varkappa^2, \quad (2)$$

where $\varkappa = \ell/R$ is the dimensionless curvature. Additionally an *inhomogeneous* solution is found with

$$\tan \phi_0^B = -\tan 2\psi^B = \frac{d}{\varkappa}, \quad (3)$$

where $d = \mathcal{D}/\sqrt{A\mathcal{K}}$ is DMI strength. It is important that angle ϕ_0^B , which defines orientation of the tangential magnetization component, is a coordinate independent

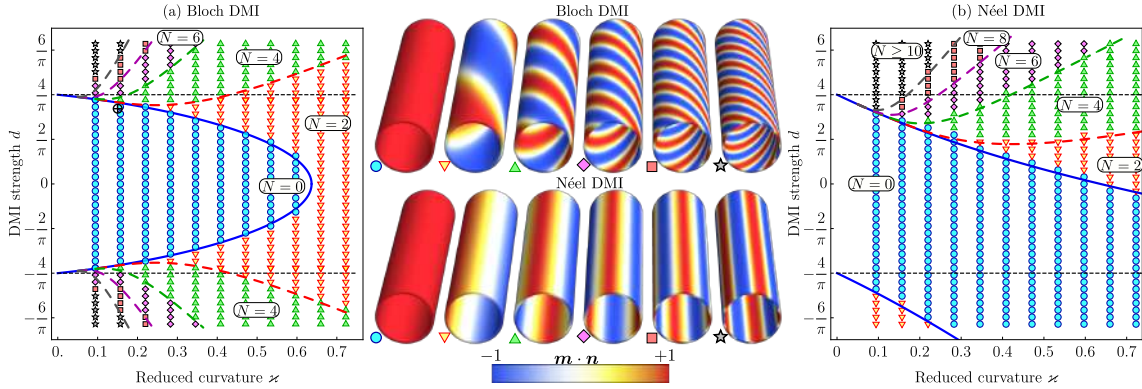


Figure 3: (Color online) **Equilibrium states in tubular shells:** (a) and (b) show phase diagrams of equilibrium states in tubular shell with Bloch and Néel type of **intrinsic** DMI, respectively. Symbols display the results from numerical simulations: circles – normal (hedgehog) magnetization distribution ($\mathbf{m} = \pm\mathbf{n}$); other symbols – periodic states (gray stars correspond to states with $q \geq 5$). Blue solid lines in (a) and (b) are analytical critical lines determined by Eqs. (8) and (12), respectively; dashed lines in (a) and (b) mark transitions, where the periodic equilibrium states change their number of DWs, as determined by numerical solution of energies equality $\mathcal{E}_B^{\text{per}}(q) = \mathcal{E}_B^{\text{per}}(q+1)$ and $\mathcal{E}_N^{\text{per}}(q) = \mathcal{E}_N^{\text{per}}(q+1)$: $q = 1$ corresponds to red dashed line, $q = 2$ – green, $q = 3$ – purple, $q = 4$ – gray. Dashed black horizontal lines correspond to critical DMI parameter in a flat systems $d_0 = \pm 4/\pi$. Symbol \oplus in (a) corresponds to the boundary between the hedgehog and periodic states obtained by means of micromagnetic simulations in Ref. [32].

constant. The relation (3) can be interpreted as follows: for given d and z , there is a curvilinear frame of reference determined by the angle ψ^B in which the magnetization angle ϕ^B is constant. Angles ϕ_0^B and ψ^B as functions of DMI strength are plotted in Fig. 2(a). For both types of DMI angle $\theta(x_1)$, which defines the magnitude of the normal magnetization component of the **inhomogeneous state**, depends on only one coordinate x_1 , oriented along the stripe, see Fig. 1. It is determined by the common “DW” equation

$$\theta_{\xi_1 \xi_1} - \lambda \sin \theta \cos \theta = 0 \quad (4)$$

with the solution

$$\theta(\xi_1) = \text{am} \left(\sqrt{C} \xi_1, -\frac{\lambda}{C} \right), \quad (5)$$

where $\text{am}(\bullet, \bullet)$ is Jacobi’s amplitude [51, 52], C is an **integration constant**, and $\xi_1 = x_1/\ell$ is the dimensionless coordinate. The solution (5) describes the sequence of DWs oriented along the x_2 coordinate (perpendicularly to the ribbon, see Fig. 1). For each type of DMI, parameter $\lambda = \lambda(z, d)$ is a function of curvature and DMI strength. For well separated DWs, λ defines the DW width $\Delta = 1/\sqrt{\lambda}$. The integration constant C determines the period $\theta(\xi_1 + T) = \theta(\xi_1)$

$$T = \frac{4}{\sqrt{C}} K \left(-\frac{\lambda}{C} \right) = T_0 |\cos \psi| / q, \quad (6)$$

with $K(\bullet)$ is the complete elliptic integral of the first kind [51, 52]. On the other hand, period $T = T_0 |\cos \psi| / q$ is predetermined by the periodical boundary conditions discussed above. Here $q \in \mathbb{N}$ determines the number of DWs $N = 2q$ on the tube and $T_0 = 2\pi/z$. N is even due to the periodical boundary conditions enforced by

the tubular geometry. For the case of Bloch DMI constant $C \equiv C_B$ is determined by the equation (6) with $\psi = \psi^B$ taken from (3) and $\lambda \equiv \lambda_B = 1 + \varkappa (\sqrt{d^2 + \varkappa^2} - \varkappa) / 2$. One should note that for the case $\varkappa > 0$ and $d^2 > 0$ the DW width decreases as compared to the case $\varkappa = 0$ (planar film) or $d = 0$. For the corresponding period we use the notation $T \equiv T_B$. Period T_B as a function of the DMI strength is plotted in Fig. 2(b). The normalized energy of periodic states per period ($T = T_B$) is

$$\mathcal{E}_B^{\text{per}} = \mathcal{E}_B^{\text{un}} + \frac{\varkappa q}{\cos \psi^B} \left[\frac{4}{\pi} \sqrt{C_B(q)} E \left(-\frac{\lambda_B}{C_B(q)} \right) - (\varkappa + \sqrt{\varkappa^2 + d^2}) - C_B(q) \frac{\cos \psi^B}{q\varkappa} \right], \quad (7)$$

where $E(\bullet)$ is the complete elliptic integral of the second kind [51, 52]. For a planar film, the transition between the homogeneous and periodical state is characterized by infinite increase of period of the spiral state [7]. Although, for the cylindrical surface the period is finite in the transition point, for the limit case $\varkappa \rightarrow 0$ one has $T \rightarrow \infty$. Using that $C \rightarrow 0$ in this limit, we obtain from the equality $\mathcal{E}_B^{\text{per}} = \mathcal{E}_B^{\text{un}}$ the analytical expression for the critical DMI

$$d_c^B = \pm d_0 \sqrt{1 - \varkappa^2 - \frac{\varkappa \pi^2 - 4}{2 \pi^2} \left[\varkappa + \sqrt{\varkappa^2 + \pi^2 (1 - \varkappa^2)} \right]}, \quad (8)$$

where $d_0 = 4/\pi$ is a critical DMI parameter for flat systems, which separates homogeneous and periodic magnetization distributions [5, 7]. Although the expression (8) is obtained in the small curvature limit, it describes very well the existence region of the homogeneous state for the whole range of curvatures, see Fig. 3(a). The boundary (8) is also in a good agreement with results obtained by means of micromagnetic simulations in Ref. [32], see symbol \oplus in Fig. 3(a). The equality of energies $\mathcal{E}_B^{\text{per}}(\varkappa, d_c, q) = \mathcal{E}_B^{\text{per}}(\varkappa, d_c, q + 1)$ determines the boundary between states with different number of DWs. The resulting phase diagram is plotted in Fig. 3(a). In the limit case of very small curvature ($\varkappa \ll 1$), the boundary curve (8) has the asymptotic behavior $d_c^B \approx \pm d_0 \mp (1 - 4/\pi^2) \varkappa$. Thus the curvature decreases the critical magnitude of the DMI strength. The boundary curve (8) intersects the abscissa with $\varkappa_0^B = 2/\pi$. For $\varkappa > \varkappa_0^B$ the periodical state with two DWs exists even without intrinsic DMI, see Fig. 3. This effect is analogous to the effect of spontaneous formation of the onion state in nanorings when curvature exceeds some critical value [53].

4 DMI of Néel type

Let us now consider the case of Néel DMI $\mathcal{E}_D = \mathcal{E}_D^N$. The energy of the *homogeneous* hedgehog state ($\mathbf{m} = \pm \mathbf{n}$) reads

$$\mathcal{E}_N^{\text{un}} = \varkappa (d + \varkappa). \quad (9)$$

Similarly to the case of Bloch DMI, there is an *inhomogeneous* solution in form of periodical modulation. As well as in the previous case, the angle ϕ takes the constant value (for details see Appendix B.2):

$$\cos \phi_0^N = -\text{sgn}(d + 2\varkappa). \quad (10)$$

However, in contrast to the previous case, DWs are always aligned along the cylinder. This corresponds to the equilibrium value $\psi^N = 0$ (or equivalently $\psi^N = \pi$). As

previously, the normal magnetization component is described by the same Eq. (5) with $C \equiv C_N$ determined by (6) with $\psi = \psi^N$ and $\lambda \equiv \lambda_N = 1 - \varkappa d$. Note that [due to non-zero DMI and curvature the width of the well separated Néel DWs is increased. This behavior is opposite to the case of the Bloch DWs.](#) The normalized energy of the modulated state per period ($T = T_N = T_0/q$) is

$$\mathfrak{E}_N^{\text{per}} = \mathfrak{E}_N^{\text{un}} + \varkappa q \left[\frac{4}{\pi} \sqrt{C_N(q)} \text{E} \left(-\frac{\lambda_N}{C_N(q)} \right) - |2\varkappa + d| - \frac{C_N(q)}{q\varkappa} \right]. \quad (11)$$

The equality of energies $\mathfrak{E}_N^{\text{un}}(\varkappa, d_c) = \mathfrak{E}_N^{\text{per}}(\varkappa, d_c)$ determines the boundary between homogeneous and periodic states. In the small curvature limit we obtain

$$d_c^N = \pm d_0 \left[\sqrt{1 + 2\varkappa^2 \left(1 + \frac{2}{\pi^2} \right)} \mp \varkappa \left(\frac{2}{\pi} + \frac{\pi}{2} \right) \right]. \quad (12)$$

As in the case of Bloch type DMI, the expression (12) describes the boundary of the homogeneous state in the phase diagram for a wide range of curvatures. The equality of energies $\mathfrak{E}_N^{\text{per}}(\varkappa, d_c, q) = \mathfrak{E}_N^{\text{per}}(\varkappa, d_c, q+1)$ determines the boundary between states with different number of DWs. The resulting phase diagram is plotted in Fig. 3(b). In the limit case of very small curvature ($\varkappa \ll 1$), the boundary curve (12) has the linear asymptotic behavior $d_c^N \approx \pm d_0 - 2(1 + 4/\pi^2) \varkappa$. Thus, due to the curvature the absolute value of the critical DMI can be decreased as well as increased depending on the sign of the DMI. Similarly to the case of Bloch type DMI, the boundary curve (12) intersects the abscissa with $\varkappa_0^N = \varkappa_0^B = 2/\pi$ and for the case $\varkappa > \varkappa_0^N$ the periodical state exists even without intrinsic DMI, see Fig. 3.

5 Conclusions

At the example of cylindrical thin tubes, we show that curvature modifies the value of critical DMI for curved systems, see Eqs. (8) and (12), which separates the hedgehog state with homogeneous magnetization normal to the film from the inhomogeneous modulated states. For the case of Néel type of DMI this effect is much stronger (in the limit case $\varkappa \ll 1$) as compared to the case of the Bloch DMI. [The curvature effects are more pronounced for the case of Néel intrinsic DMI because the curvature-induced DMI is usually of the Néel type, thus a direct competition takes place. Note, that for the same reason the Néel skyrmions are more strongly affected by the curvature gradients as compared to the Bloch skyrmions \[33\] and the DMI-free skyrmions stabilized by curvature are of Néel type \[45\].](#) We found an exact solution for equilibrium states on the cylindrical surface for two different types of DMI and plotted the corresponding phase diagrams, see Fig. 3. The presence of the Néel DMI does not modify the structure of DWs, i.e. DWs are oriented along the cylinder axis ($\psi^N = 0$) and they are of Néel type. For the case of Bloch DMI, the DWs are of a type intermediate between Bloch and Néel due to competition of intrinsic DMI and geometry-induced DMI of Néel type. These DWs are inclined by the angle $\psi^B \in (-\pi/4; \pi/4)$, see Eq. (3) and Fig. 3. The direction of DWs inclination (sign of the angle ψ^B) is defined by the sign of the DMI parameter. This effect is similar (i) to the field-induced inclined DWs in flat stripes [54]. In our case the role of the external field is played by the geometry-induced easy-axis anisotropy along the cylinder axis. And it also resembles (ii) the DMI-induced chiral twist

of domains separated by the head-to-head (tail-to-tail) DWs in nanotubes [48]. In both cases, the periodical boundary conditions, enforced by the closed cylindrical geometry, result in even number of domains on the cylinder.

Acknowledgements

We thank U. Nitzsche for technical support.

Funding information K.V.Y. acknowledges financial support from UKRATOP-project (funded by BMBF under reference 01DK18002). In part, this work was supported by the Program of Fundamental Research of the Department of Physics and Astronomy of the National Academy of Sciences of Ukraine (Project No. 0120U100855), by the Alexander von Humboldt Foundation (Research Group Linkage Programme), and by Taras Shevchenko National University of Kyiv (Project No. 19BF052-01).

A Introduction of the curvilinear basis and magnetic interactions on a curvilinear shell

The surface parametrization $\boldsymbol{\varsigma}(x_1, x_2)$ induces the natural tangential basis $\mathbf{g}_\alpha = \partial_\alpha \boldsymbol{\varsigma}$ with the corresponding metric tensor elements $g_{\alpha\beta} = \mathbf{g}_\alpha \cdot \mathbf{g}_\beta$. Here, $\alpha, \beta = 1, 2$ and $\partial_\alpha \equiv \partial_{x_\alpha}$. As the vectors \mathbf{g}_α are orthogonal, one can introduce the orthonormal basis $\{\mathbf{e}_1, \mathbf{e}_2, \mathbf{n}\}$ with

$$\mathbf{e}_\alpha = \frac{\mathbf{g}_\alpha}{\sqrt{g_{\alpha\alpha}}}, \quad \mathbf{n} = \mathbf{e}_1 \times \mathbf{e}_2. \quad (\text{A.1})$$

Using the Gauß-Godazzi formula and Weingarten's equation [55, 56] one can obtain the following differential properties of the basis vectors

$$\nabla_\alpha \mathbf{e}_\beta = h_{\alpha\beta} \mathbf{n} - \Omega_{\alpha\epsilon\beta\gamma} \mathbf{e}_\gamma, \quad \nabla_\alpha \mathbf{n} = -h_{\alpha\beta} \mathbf{e}_\beta. \quad (\text{A.2})$$

Here, $\nabla_\alpha \equiv (g_{\alpha\alpha})^{-1/2} \partial_\alpha$ (no summation over α) are components of the surface del operator and $\|h_{\alpha\beta}\|$ is a modified second fundamental form. The second fundamental form determines the Gauß curvature $\mathcal{K} = \det \|h_{\alpha\beta}\|$ and the mean curvature $\mathcal{H} = \text{tr} \|h_{\alpha\beta}\|$. Components of the spin connection vector $\boldsymbol{\Omega}$ are determined by the relation $\Omega_\gamma = \frac{1}{2} \epsilon_{\alpha\beta} \mathbf{e}_\alpha \cdot \nabla_\gamma \mathbf{e}_\beta$.

Using curvilinear reference frame (A.1), we introduce the following magnetization parametrization

$$\mathbf{m} = \sin \theta \boldsymbol{\varepsilon} + \cos \theta \mathbf{n}, \quad \boldsymbol{\varepsilon} = \cos \phi \mathbf{e}_1 + \sin \phi \mathbf{e}_2, \quad (\text{A.3})$$

where θ and ϕ are magnetic angles, and $\boldsymbol{\varepsilon}$ is a normalized projection of the vector \mathbf{m} on the tangential plane.

The first term in (1) is the exchange density $\mathcal{E}_x = \sum_{i=x,y,z} (\partial_i \mathbf{m})^2$ with \mathcal{A} the exchange constant. In the curvilinear reference frame exchange energy can be written as [45, 49, 53]

$$\begin{aligned} \mathcal{E}_x = & \nabla_\alpha m_\beta \nabla_\alpha m_\beta + \nabla_\alpha m_n \nabla_\alpha m_n \\ & + 2h_{\alpha\beta} (m_\beta \nabla_\alpha m_n - m_n \nabla_\alpha m_\beta) + 2\epsilon_{\alpha\beta} \Omega_\gamma m_\beta \nabla_\gamma m_\alpha \\ & + (h_{\alpha\gamma} h_{\gamma\beta} + \Omega^2 \delta_{\alpha\beta}) m_\alpha m_\beta + (\mathcal{K}^2 - 2\mathcal{H}) m_n^2 + 2\epsilon_{\alpha\gamma} h_{\gamma\beta} \Omega_\beta m_\alpha m_n. \end{aligned} \quad (\text{A.4a})$$

Using the angular parametrization (A.3) one can obtain [45, 49, 53]

$$\mathcal{E}_x = [\nabla\theta - \Gamma]^2 + [\sin\theta(\nabla\phi - \Omega) - \cos\theta\partial_\phi\Gamma]^2, \quad (\text{A.4b})$$

where $\Gamma = \|h_{\alpha\beta}\| \cdot \boldsymbol{\varepsilon}$.

The second term in (1) corresponds to the Dzyaloshinskii–Moriya interaction (DMI) \mathcal{E}_D , with \mathcal{D} being the DMI constant. In the curvilinear frame of reference the Néel type DMI $\mathcal{E}_D^N = m_n \nabla \cdot \mathbf{m} - \mathbf{m} \cdot \nabla m_n$ can be written as [45]

$$\mathcal{E}_D^N = m_n \nabla_\alpha m_\alpha - m_\alpha \nabla_\alpha m_n - \epsilon_{\alpha\beta} \Omega_\beta m_\alpha m_n - \mathcal{H} m_n^2. \quad (\text{A.5a})$$

Using the angular parametrization (A.3) one can obtain (up to the boundary terms) [45, 46]

$$\mathcal{E}_D^N = 2(\nabla\theta \cdot \boldsymbol{\varepsilon}) \sin^2\theta - \mathcal{H} \cos^2\theta + \text{boundary terms}, \quad (\text{A.5b})$$

while, for the Bloch type DMI symmetry $\mathcal{E}_D^B = \mathbf{m} \cdot [\nabla \times \mathbf{m}]$ this interaction in the curvilinear reference frame reads as [50]

$$\mathcal{E}_D^B = \epsilon_{\alpha\beta} (m_n \nabla_\alpha m_\beta - m_\beta \nabla_\alpha m_n) + \epsilon_{\alpha\beta} h_{\beta\gamma} m_\alpha m_\gamma - \Omega_\alpha m_\alpha m_n. \quad (\text{A.5c})$$

Substituting the angular parametrization (A.3) into (A.5c) results in the expression (up to the boundary terms) [50]

$$\mathcal{E}_D^B = \sin^2\theta [(2\nabla\theta - \Gamma) \times \boldsymbol{\varepsilon}] \cdot \mathbf{n}. \quad (\text{A.5d})$$

The last term in (1) corresponds to the uniaxial anisotropy $\mathcal{E}_A = \sin^2\theta$, with $\mathcal{K} > 0$ the easy-normal anisotropy constant.

Parameterization $\boldsymbol{\varsigma}(x_1, x_2) = R \cos(\rho_s/R) \hat{\mathbf{x}} + R \sin(\rho_s/R) \hat{\mathbf{y}} + \rho_z \hat{\mathbf{z}}$ results in the following first and modified second fundamental forms

$$g_{\alpha\beta} = \delta_{\alpha\beta}, \quad \|h_{\alpha\beta}\| = \frac{1}{R} \begin{vmatrix} -\cos^2\psi & \cos\psi \sin\psi \\ \cos\psi \sin\psi & -\sin^2\psi \end{vmatrix}, \quad (\text{A.6})$$

respectively. Tubular geometry has zero Gauß curvature $\mathcal{K} = 0$, nonzero mean curvature $\mathcal{H} = -R^{-1}$ (here minus is related to the direction of the normal vector), and zero components of spin connection vector $\Omega = \mathbf{0}$.

B DMI induced periodical solution for a cylindrical surface

B.1 DMI of Bloch type

In this section we consider DMI in form $\mathcal{E}_D = \mathcal{E}_D^B$ which is defined in (A.5d). The total energy density in (1) reads as

$$\begin{aligned} \frac{\mathcal{E}}{\mathcal{K}} &= \left(\tilde{\nabla}\theta\right)^2 + \left(\tilde{\nabla}\phi\right)^2 \sin^2\theta + 2\kappa \cos(\phi + \psi) \tilde{\nabla}\theta \cdot \boldsymbol{\eta} \\ &\quad - 2\kappa \sin\theta \cos\theta \sin(\phi + \psi) \tilde{\nabla}\phi \cdot \boldsymbol{\eta} + \kappa^2 [1 - \sin^2\theta \sin^2(\phi + \psi)] + \sin^2\theta \\ &\quad + d \sin^2\theta \left[2(\theta_{\xi_1} \sin\phi - \theta_{\xi_2} \cos\phi) + \frac{\kappa}{2} \sin 2(\phi + \psi) \right], \quad \boldsymbol{\eta} = \mathbf{e}_1 \cos\psi - \mathbf{e}_2 \sin\psi, \end{aligned} \quad (\text{B.1})$$

where $\kappa = \ell/R$ is a reduced curvature with $\ell = \sqrt{\mathcal{A}/\mathcal{K}}$ being the magnetic length, the operator $\tilde{\nabla}$ acts on the dimensionless curvilinear coordinates $\xi_\alpha = x_\alpha/\ell$, and

$d = \mathcal{D}/\sqrt{\mathcal{A}\mathcal{K}}$ is a reduced DMI strength. The equilibrium values of θ , ϕ , and ψ are determined by the equations

$$\begin{aligned}
\frac{1}{2} \frac{\delta E}{\delta \theta} &= -\tilde{\Delta}\theta + \sin\theta \cos\theta \left[\left(\tilde{\nabla}\phi \right)^2 + 1 \right] + 2\kappa \sin^2\theta \sin(\phi + \psi) \tilde{\nabla}\phi \cdot \boldsymbol{\eta} \\
&\quad - \kappa^2 \sin\theta \cos\theta \sin^2(\phi + \psi) - d \left[\sin^2\theta \tilde{\nabla}\phi \cdot \boldsymbol{\varepsilon} - \frac{1}{4} \kappa \sin 2\theta \sin 2(\phi + \psi) \right] = 0, \\
\frac{1}{2} \frac{\delta E}{\delta \phi} &= -\tilde{\nabla} \cdot \left[\sin^2\theta \tilde{\nabla}\phi \right] - 2\kappa \sin(\phi + \psi) \sin^2\theta \tilde{\nabla}\theta \cdot \boldsymbol{\eta} - \kappa^2 \sin^2\theta \sin(\phi + \psi) \cos(\phi + \psi) \\
&\quad + d \sin^2\theta \left[\tilde{\nabla}\theta \cdot \boldsymbol{\varepsilon} + \frac{\kappa}{2} \cos 2(\phi + \psi) \right] = 0, \\
\frac{1}{2\kappa} \frac{\delta E}{\delta \psi} &= -\theta_{\xi_1} \sin(\phi + 2\psi) - \theta_{\xi_2} \cos(\phi + 2\psi) - \frac{1}{2} \sin 2\theta [\phi_{\xi_1} \cos(\phi + 2\psi) - \phi_{\xi_2} \sin(\phi + 2\psi)] \\
&\quad - \kappa \sin^2\theta \sin(\phi + \psi) \cos(\phi + \psi) + \frac{d}{2} \sin^2\theta \cos 2(\phi + \psi) = 0.
\end{aligned} \tag{B.2}$$

Here $\tilde{\nabla}_\alpha = \ell \nabla_\alpha \equiv \partial_{\xi_\alpha}$ and $\tilde{\Delta} = \tilde{\nabla}^2$.

Equations (B.2) have a trivial solutions $\theta \equiv 0$ and $\theta \equiv \pi$, which corresponds to the uniform magnetization distribution in the curvilinear reference frame, i.e. $\mathbf{m} = \pm \mathbf{n}$, with energy (2).

We also found an inhomogeneous solution (3) with $\phi = \phi_0^B = \text{const}$:

$$\cos \phi_0^B = -\frac{\kappa \operatorname{sgn}(d)}{\sqrt{\kappa^2 + d^2}}, \quad \sin \psi^B = -\frac{d}{\sqrt{2 [d^2 + \kappa (\kappa + \sqrt{\kappa^2 + d^2})]}}. \tag{B.3}$$

Note that for the case $d > 0$ one has $-\pi/4 \leq \psi^B \leq 0$ and $\phi_0^B = \pi - 2\psi^B$. While for the case $d < 0$ one has $0 \leq \psi^B \leq \pi/4$ and $\phi_0^B = -2\psi^B$. The magnetic angle θ is defined by the equation (4) with the solution (5).

Energy as a function of DMI strength for Bloch DMI for different q is plotted in Fig. 4(a).

B.2 DMI of Néel type

Here we consider DMI in form $\mathcal{E}_D = \mathcal{E}_D^N$ which is defined in Eqs. (A.5a) and (A.5b). The total energy density in (1) reads as

$$\begin{aligned}
\frac{\mathcal{E}}{\mathcal{K}} &= \left(\tilde{\nabla}\theta \right)^2 + \left(\tilde{\nabla}\phi \right)^2 \sin^2\theta + 2\kappa \cos(\phi + \psi) \tilde{\nabla}\theta \cdot \boldsymbol{\eta} - 2\kappa \sin\theta \cos\theta \sin(\phi + \psi) \tilde{\nabla}\phi \cdot \boldsymbol{\eta} \\
&\quad + \kappa^2 [1 - \sin^2\theta \sin^2(\phi + \psi)] + d \left[2 \left(\tilde{\nabla}\theta \cdot \boldsymbol{\varepsilon} \right) \sin^2\theta + \kappa \cos^2\theta \right] + \sin^2\theta.
\end{aligned} \tag{B.4}$$

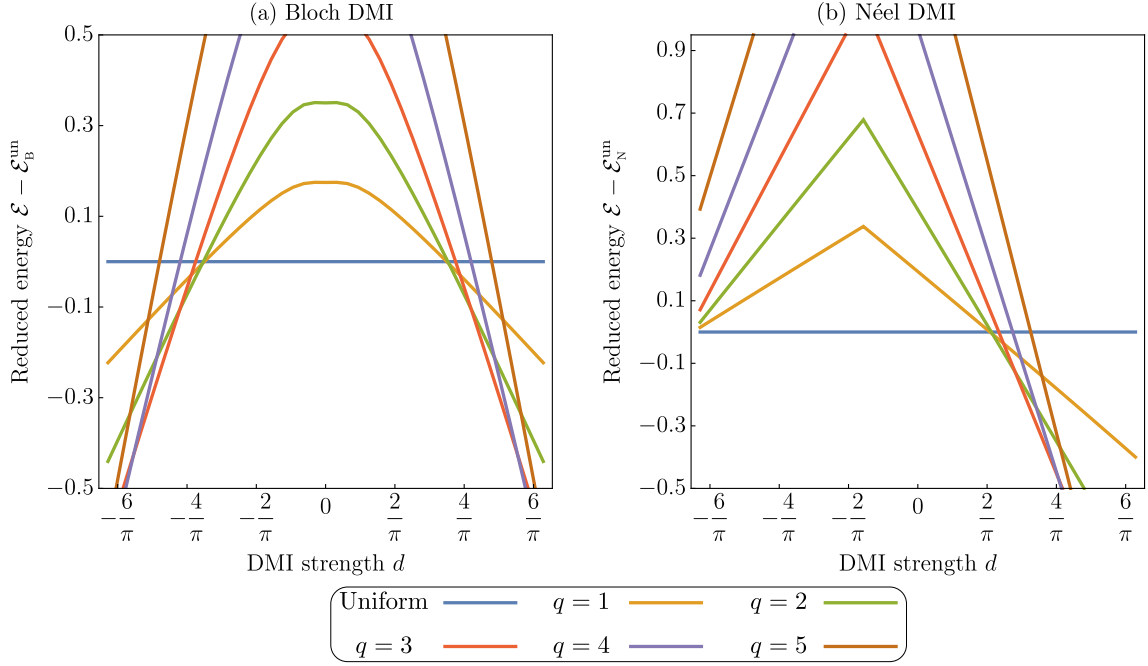


Figure 4: (Color online) Energies of the cylinder with $\varkappa = 0.25$ for Bloch (a) and Néel (b) DMI types.

The equilibrium values of θ , ϕ , and ψ determined by the equations

$$\begin{aligned}
\frac{1}{2} \frac{\delta E}{\delta \theta} &= -\tilde{\Delta} \theta + \sin \theta \cos \theta \left[\left(\tilde{\nabla} \phi \right)^2 + 1 \right] + 2\varkappa \sin^2 \theta \sin(\phi + \psi) \tilde{\nabla} \phi \cdot \boldsymbol{\eta} \\
&\quad - \varkappa^2 \sin \theta \cos \theta \sin^2(\phi + \psi) - d \left[\sin^2 \theta \tilde{\nabla} \phi \cdot \frac{\partial \boldsymbol{\varepsilon}}{\partial \phi} + \varkappa \sin \theta \cos \theta \right] = 0, \\
\frac{1}{2} \frac{\delta E}{\delta \phi} &= -\tilde{\nabla} \cdot \left[\sin^2 \theta \tilde{\nabla} \phi \right] - 2\varkappa \sin(\phi + \psi) \sin^2 \theta \tilde{\nabla} \theta \cdot \boldsymbol{\eta} - \varkappa^2 \sin^2 \theta \sin(\phi + \psi) \cos(\phi + \psi) \\
&\quad + d \sin^2 \theta \tilde{\nabla} \theta \cdot \frac{\partial \boldsymbol{\varepsilon}}{\partial \phi} = 0, \\
\frac{1}{2\varkappa} \frac{\delta E}{\delta \psi} &= -\theta_{\xi_1} \sin(\phi + 2\psi) - \theta_{\xi_2} \cos(\phi + 2\psi) - \frac{1}{2} \sin 2\theta [\phi_{\xi_1} \cos(\phi + 2\psi) - \phi_{\xi_2} \sin(\phi + 2\psi)] \\
&\quad - \varkappa \sin^2 \theta \sin(\phi + \psi) \cos(\phi + \psi) = 0.
\end{aligned} \tag{B.5}$$

Equations (B.5) have a trivial solutions $\theta \equiv 0$ and $\theta \equiv \pi$, which corresponds to the hedgehog state $\mathbf{m} = \pm \mathbf{n}$, i. e. the homogeneous magnetization distribution in the curvilinear reference frame; the energy of the hedgehog state is described by Eq. (9).

We also found an inhomogeneous solution with $\phi = \phi_0^N = \text{const}$, see (10), and magnetic angle θ defined in (5).

Energy as a function of DMI strength for Néel DMI for different q is plotted in Fig. 4(b).

C Details of the spin-lattice simulations

In order to verify our analytical calculations we perform a set numerical simulations for a ferromagnetic cylindrical surface. We consider a cylindrical surface as a square lattice with lattice constant a . Each node is characterized by a magnetic moment $\mathbf{m}_{\mathbf{p}}(t)$ which is located at the position $\mathbf{r}_{\mathbf{p}}(t)$. Here $\mathbf{p} = (i, j)$ is a two dimensional vector which defines the magnetic moment and its position on the lattice with size $N_1 \times N_2$ ($i \in [1, N_1]$ and $j \in [1, N_2]$). Magnetic moments are ferromagnetically coupled. We are interested in the case when the system is a closed cylindrical surface, hence we impose the periodical boundary conditions $\mathbf{m}_{(N_1+1, j)} = \mathbf{m}_{(1, j)}$ and $\mathbf{r}_{(N_1+1, j)} = \mathbf{r}_{(1, j)}$. The dynamics of magnetic system is govern by discrete Landau–Lifshitz–Gilbert equations

$$\frac{d\mathbf{m}_{\mathbf{p}}}{d\tau} = \mathbf{m}_{\mathbf{p}} \times \frac{\partial \mathcal{H}}{\partial \mathbf{m}_{\mathbf{p}}} + \alpha \mathbf{m}_{\mathbf{p}} \times \left[\mathbf{m}_{\mathbf{p}} \times \frac{\partial \mathcal{H}}{\partial \mathbf{m}_{\mathbf{p}}} \right], \quad (\text{C.1})$$

where $\tau = \omega_0 t$ is a reduced time with $\omega_0 = \mu_0 |\gamma_0| M_s$, α is a dimensionless damping coefficients, and \mathcal{H} is a dimensionless energy normalized by $\mu_0 M_s^2$. We consider four contributions to the energy of the system

$$\mathcal{H} = \mathcal{H}_X + \mathcal{H}_A + \mathcal{H}_D + \mathcal{H}_{\text{DDI}}. \quad (\text{C.2a})$$

The first term in (C.2a) is the exchange energy

$$\mathcal{H}_X = -\frac{1}{2} \frac{\ell_x^2}{a^2} \sum_{\mathbf{p}, \delta} \mathbf{m}_{\mathbf{p}} \cdot \mathbf{m}_{\mathbf{p}+\delta}, \quad (\text{C.2b})$$

where δ runs over nearest neighbours of the square lattice and $\ell_x = \sqrt{\mathcal{A} / (\mu_0 M_s^2)}$.

The second term in (C.2a) is the anisotropy energy

$$\mathcal{H}_A = -\frac{Q}{2} \sum_{\mathbf{p}} (\mathbf{m}_{\mathbf{p}} \cdot \mathbf{n}_{\mathbf{p}})^2, \quad (\text{C.2c})$$

where $\mathbf{n}_{\mathbf{p}}$ is easy-normal axis vector at node with coordinate $\mathbf{r}_{\mathbf{p}}$, and $Q = 2\mathcal{K} / (\mu_0 M_s^2)$ is a quality factor [38].

The third term in Eq. (C.2a) is a DMI energy

$$\mathcal{H}_D = \frac{d \ell_x}{2 a} \sqrt{\frac{Q - \Lambda}{2}} \sum_{\mathbf{p}, \delta} \mathbf{d}_{\mathbf{p}, \delta} \cdot [\mathbf{m}_{\mathbf{p}} \times \mathbf{m}_{\mathbf{p}+\delta}], \quad (\text{C.2d})$$

where $\mathbf{d}_{\mathbf{p}, \delta}$ is a DMI vector. For the case of Néel DMI $\mathbf{d}_{\mathbf{p}, \delta} = \mathbf{n}_{\mathbf{p}} \times \mathbf{u}_{\mathbf{p}, \delta}$ with $\mathbf{u}_{\mathbf{p}, \delta} = (\mathbf{r}_{\mathbf{p}+\delta} - \mathbf{r}_{\mathbf{p}}) / a$ being a unit vector which connects two nearest neighbors. For Bloch DMI symmetry we have $\mathbf{d}_{\mathbf{p}, \delta} = \mathbf{u}_{\mathbf{p}, \delta}$. Parameter $\Lambda = \{0, 1\}$ defines *whether* long range dipole-dipole interaction is present or not, i.e. $\Lambda = 0$ corresponds to simulations without dipole-dipole interaction and $\Lambda = 1$ vice versa.

The last term in Eq. (C.2a) is a long range dipole-dipole interaction

$$\mathcal{H}_{\text{DDI}} = \Lambda \frac{a^3}{8\pi} \sum_{\substack{\mathbf{p}, \mathbf{b} \\ \mathbf{p} \neq \mathbf{b}}} \left[\frac{\mathbf{m}_{\mathbf{p}} \cdot \mathbf{m}_{\mathbf{b}}}{|\mathbf{r}_{\mathbf{pb}}|^3} - 3 \frac{(\mathbf{m}_{\mathbf{p}} \cdot \mathbf{r}_{\mathbf{pb}})(\mathbf{m}_{\mathbf{b}} \cdot \mathbf{r}_{\mathbf{pb}})}{|\mathbf{r}_{\mathbf{pb}}|^5} \right], \quad (\text{C.2e})$$

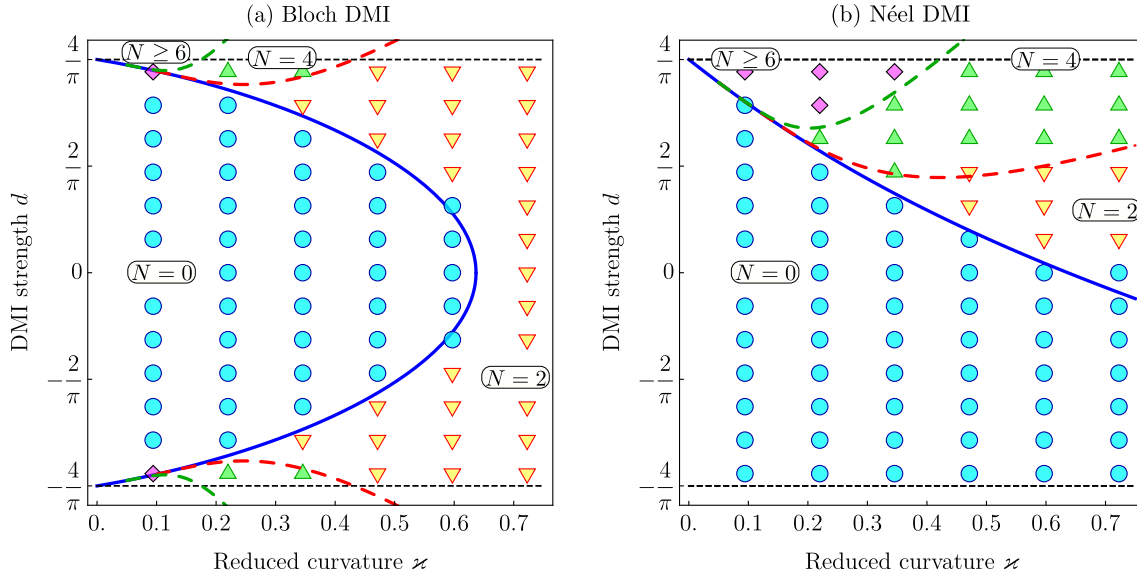


Figure 5: (Color online) **Equilibrium states in tubular shells with dipole-dipole interaction:** (a) and (b) show phase diagrams of equilibrium states in tubular shell with Bloch and Néel type DMI, respectively. Symbols display the results of spin-lattice simulations: circles – normal (hedgehog) magnetization distribution ($\mathbf{m} = \pm \mathbf{n}$); other symbols – periodic states (purple diamond correspond to states with $q \geq 3$). Blue solid lines in (a) and (b) are analytical critical lines determined by Eqs. (8) and (12), respectively; dashed lines in (a) and (b) mark transitions between the periodic equilibrium states with different number of DWs, as determined by numerical solution of equations $\mathcal{E}_B^{\text{per}}(q) = \mathcal{E}_B^{\text{per}}(q+1)$ and $\mathcal{E}_N^{\text{per}}(q) = \mathcal{E}_N^{\text{per}}(q+1)$: $q = 1$ corresponds to red dashed line, $q = 2$ – green. Dashed black horizontal lines correspond to critical DMI parameter in a flat systems $d_0 = \pm 4/\pi$.

where $\mathbf{r}_{pb} = \mathbf{r}_p - \mathbf{r}_b$.

For analytical calculations the dipole-dipole effects can be approximated by a simple redefinition of the anisotropy constants, leading to a new magnetic length,

$$\begin{aligned} \mathcal{K} &\rightarrow \mathcal{K}^{\text{eff}} = \mathcal{K} - \Lambda \mu_0 M_s^2 / 2, \\ \ell &\rightarrow \ell^{\text{eff}} = \sqrt{\frac{\mathcal{A}}{\mathcal{K}^{\text{eff}}}} = \ell_x \sqrt{\frac{2}{Q - \Lambda}}, \\ d &\rightarrow d^{\text{eff}} = \frac{\mathcal{D}}{\sqrt{\mathcal{A} \mathcal{K}^{\text{eff}}}}. \end{aligned} \quad (\text{C.3})$$

The dynamical problem is considered as a set of $3N_1N_2$ ordinary differential equations (C.1) with respect to $3N_1N_2$ unknown functions $m_p^x(\tau)$, $m_p^y(\tau)$, $m_p^z(\tau)$. For given initial conditions, the set of time evolution equations (C.1) is integrated numerically using Runge–Kutta method in Python. During the integration process, the condition $|\mathbf{m}_p(\tau)| = 1$ is controlled.

C.1 Simulations of tubes without dipole-dipole interaction ($\Lambda = 0$)

We considered cylinders with $N_1 = 300a$ and $N_2 = 900a$, quality factor $Q = 2$ (correspond to $\ell = \ell_x$), the magnetic length $\ell \in [4.5a, 34.5a]$ with $\Delta\ell = 3a$, and DMI constant $d \in [-2, 2]$ with $\Delta d = 0.1$. We simulate numerically Landau–Lifshitz–Gilbert equations (C.1) in the overdamped regime ($\alpha = 0.1$) during a long-time interval $\Delta\tau \gg (\alpha\omega_0)^{-1}$.

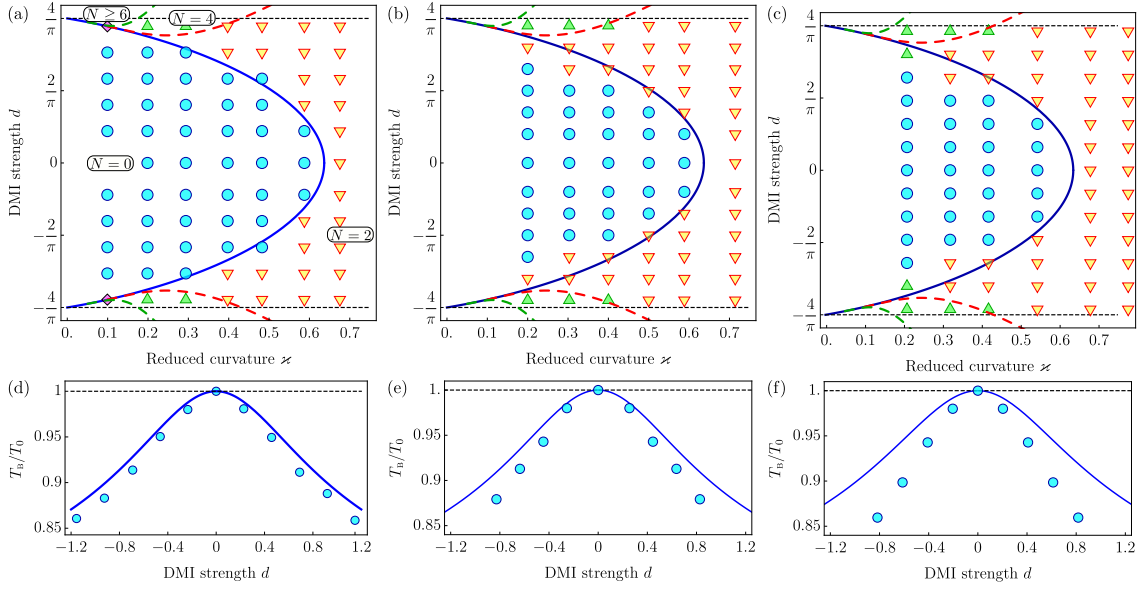


Figure 6: (Color online) **Phase diagrams of equilibrium states in nanotube with Bloch type DMI.** (a), (b), and (c) are phase diagrams of equilibrium states in nanotube with Bloch type DMI: (a) and (d) FeGe epitaxial film with $Q \approx 26.3$; (b) and (e) artificial material with $Q = 2$; (c) and (f) Pt/Co/AlOx layer structure with $Q \approx 1.71$. In (a)-(c) symbols display the results of full-scale micromagnetic simulations: circles – normal (hedgehog) magnetization distribution ($\mathbf{m} = \pm \mathbf{n}$); other symbols – periodic states (purple diamond correspond to states with $q \geq 3$). Blue solid line is analytical critical line determined by Eq. (8); dashed lines mark transitions between periodic equilibrium states with different number of DWs, as determined by numerical solution of energies equality $\mathcal{E}_B^{\text{per}}(q) = \mathcal{E}_B^{\text{per}}(q+1)$: $q = 1$ corresponds to red dashed line, $q = 2$ – green. Dashed black horizontal lines correspond to critical DMI parameter in a flat systems $d_0 = \pm 4/\pi$. (d)-(f) are periods $T_B/T_0 = |\cos \psi^B|$ of magnetization structure in tube with $\kappa \approx 0.72$, $\kappa \approx 0.71$, and $\kappa \approx 0.78$, respectively.

We performed a set of simulations for various ranges of magnetic and geometrical parameters. We simulate Eqs. (C.1) as described above for eight different initial states, namely, the normal, q -domain walls with $q = \{2, 4, 6, 8, 10\}$, and two random states. The final static state with the lowest energy is considered to be the equilibrium magnetization state. We present simulation data in Figs. 2 and 3 by symbols together with theoretical results (plotted by lines).

C.2 Simulations of tubes with dipole-dipole interaction ($\Lambda = 1$)

We considered cylinders with $N_1 = 200a$ and $N_2 = 600a$, quality factor $Q = 3$ (correspond to $\ell^{\text{eff}} = \ell_x$), the magnetic length $\ell^{\text{eff}} \in [3a, 23a]$ with $\Delta \ell^{\text{eff}} = 4a$, and DMI constant $d^{\text{eff}} \in [-1.2, 1.2]$ with $\Delta d^{\text{eff}} = 0.2$. The simulations are performed in the same way as described in Sec. C.1.

We present simulation data in Fig. 5 by symbols together with theoretical results (plotted by lines).

D Details of full-scale micromagnetic simulations

The micromagnetic simulations were performed with the OOMMF code [57] supplemented with the extension for the DMI in cubic crystals [58]. Four magnetic interactions were taken into account, namely exchange, magnetostatic, DMI, and uniaxial anisotropy contributions. We used the parameters for the epitaxial FeGe film [39, 59]: exchange constant $\mathcal{A} = 8.78 \times 10^{-12}$ J/m, saturation magnetization $M_s = 1.1 \times 10^5$ A/m, easy-normal anisotropy $\mathcal{K} = 2 \times 10^5$ J/m³, and DMI constant $\mathcal{D} \in [-1.5, 1.5] \times 10^{-3}$ J/m². This material parameters results in a quality factor $Q \approx 26.3$ and effective magnetic length $\ell^{\text{eff}} \approx 6.76$ nm. We considered magnetic nanotubes with fixed length $\tilde{L} = 500$ nm and thickness $h = 4$ nm. The inner radius of tubes was in the range $R \in [7, 66]$ nm, which results in the dimensionless curvature $\varkappa = \ell^{\text{eff}} / (R + h/2) \approx [0.1, 0.73]$ (we considered surface between the outer and inner radii). The mesh size of $0.5 \times 0.5 \times 0.5$ nm³ is used in our simulations.

The simulations are performed in the same way as described in Sec. C.1. Results of numerical simulations are presented in Fig. 2 and Fig. 6(a),(d) by symbols.

D.1 Full-scale micromagnetic simulations with small quality factor

Additionally we performed simulations for systems with small quality factor:

- We used the following artificial material parameters: exchange constant $\mathcal{A} = 5\pi \times 10^{-12}$ J/m, saturation magnetization $M_s = 5 \times 10^5$ A/m, easy-normal anisotropy $\mathcal{K} = \pi \times 10^5$ J/m³, and DMI constant $\mathcal{D} \in [-1.9, 1.9] \times 10^{-3}$ J/m². This material parameters results in a quality factor $Q = 2$ and effective magnetic length $\ell^{\text{eff}} = 10$ nm. We considered magnetic nanotubes with fixed length $\tilde{L} = 500$ nm and thickness $h = 4$ nm. The inner radius of tubes was in the range $R \in [12, 48]$ nm, which results in the dimensionless curvature $\varkappa = \ell^{\text{eff}} / (R + h/2) \approx [0.2, 0.71]$ (for the mid-cylinder surface between the outer and inner radii). The mesh size of $1 \times 1 \times 1$ nm³ is used in our simulations.

Results of numerical simulations are presented in Fig. 6(b),(e) by symbols.

- We used the material parameters of Pt/Co/AlOx layer structure [45]: exchange constant $\mathcal{A} = 1.6 \times 10^{-11}$ J/m, saturation magnetization $M_s = 1.1 \times 10^6$ A/m, easy-normal anisotropy $\mathcal{K} = 1.3 \times 10^6$ J/m³, and DMI constant $\mathcal{D} \in [-3.6, 3.6] \times 10^{-3}$ J/m². These material parameters result in a quality factor $Q \approx 1.71$ and effective magnetic length $\ell^{\text{eff}} \approx 5.44$ nm. We considered magnetic nanotubes with fixed length $\tilde{L} = 500$ nm and thickness $h = 2$ nm. The inner radius of tubes was in the range $R \in [6, 25]$ nm, which results in the dimensionless curvature $\varkappa = \ell^{\text{eff}} / (R + h/2) \approx [0.21, 0.78]$ (for the mid-cylinder surface between the outer and inner radii). The mesh size of $0.5 \times 0.5 \times 0.5$ nm³ is used in our simulations.

Results of numerical simulations are presented in Fig. 6(c),(f) by symbols.

References

- [1] R. Streubel, P. Fischer, F. Kronast, V. P. Kravchuk, D. D. Sheka, Y. Gaididei, O. G. Schmidt and D. Makarov, *Magnetism in curved geometries (top-*

- ical review*), Journal of Physics D: Applied Physics **49**(36), 363001 (2016), doi:[10.1088/0022-3727/49/36/363001](https://doi.org/10.1088/0022-3727/49/36/363001).
- [2] A. Fernández-Pacheco, R. Streubel, O. Fruchart, R. Hertel, P. Fischer and R. P. Cowburn, *Three-dimensional nanomagnetism*, Nature Communications **8**, 15756 (2017).
- [3] M. I. Sloika, D. D. Sheka, V. P. Kravchuk, O. V. Pylypovskyi and Y. Gaididei, *Geometry induced phase transitions in magnetic spherical shell*, Journal of Magnetism and Magnetic Materials **443**, 404 (2017), doi:[10.1016/j.jmmm.2017.07.036](https://doi.org/10.1016/j.jmmm.2017.07.036).
- [4] O. M. Volkov, D. D. Sheka, Y. Gaididei, V. P. Kravchuk, U. K. Röbner, J. Fassbender and D. Makarov, *Mesoscale Dzyaloshinskii-Moriya interaction: geometrical tailoring of the magnetochirality*, Scientific Reports **8**(1), 866 (2018), doi:[10.1038/s41598-017-18835-4](https://doi.org/10.1038/s41598-017-18835-4).
- [5] A. Bogdanov and A. Hubert, *Thermodynamically stable magnetic vortex states in magnetic crystals*, Journal of Magnetism and Magnetic Materials **138**(3), 255 (1994), doi:[10.1016/0304-8853\(94\)90046-9](https://doi.org/10.1016/0304-8853(94)90046-9).
- [6] A. B. Butenko, A. A. Leonov, U. K. Röbner and A. N. Bogdanov, *Stabilization of skyrmion textures by uniaxial distortions in noncentrosymmetric cubic helimagnets*, Physical Review B **82**(5), 052403 (2010), doi:[10.1103/physrevb.82.052403](https://doi.org/10.1103/physrevb.82.052403).
- [7] S. Rohart and A. Thiaville, *Skyrmion confinement in ultrathin film nanostructures in the presence of Dzyaloshinskii-Moriya interaction*, Physical Review B **88**(18), 184422 (2013), doi:[10.1103/PhysRevB.88.184422](https://doi.org/10.1103/PhysRevB.88.184422).
- [8] M. Eisenstein, *An attractive alternative*, Nature Methods **2**(7), 484 (2005), doi:[10.1038/nmeth0705-484b](https://doi.org/10.1038/nmeth0705-484b).
- [9] S. J. Son, J. Reichel, B. He, M. Schuchman and S. B. Lee, *Magnetic nanotubes for magnetic-field-assisted bioseparation, biointeraction, and drug delivery*, Journal of the American Chemical Society **127**(20), 7316 (2005), doi:[10.1021/ja0517365](https://doi.org/10.1021/ja0517365).
- [10] E. Kaniukov, A. Shumskaya, D. Yakimchuk, A. Kozlovskiy, I. Korolkov, M. Ibragimova, M. Zdorovets, K. Kadyrzhanov, V. Rusakov, M. Fadeev, E. Lobko, K. Saunina *et al.*, *FeNi nanotubes: perspective tool for targeted delivery*, Applied Nanoscience **9**(5), 835 (2018), doi:[10.1007/s13204-018-0762-4](https://doi.org/10.1007/s13204-018-0762-4).
- [11] A. Kozlovskiy, M. Zdorovets, K. Kadyrzhanov, I. Korolkov, V. Rusakov, L. Nikolaevich, O. Fesenko, O. Budnyk, D. Yakimchuk, A. Shumskaya and E. Kaniukov, *FeCo nanotubes: possible tool for targeted delivery of drugs and proteins*, Applied Nanoscience **9**(5), 1091 (2018), doi:[10.1007/s13204-018-0889-3](https://doi.org/10.1007/s13204-018-0889-3).
- [12] V. S. Tkachenko, V. V. Kruglyak and A. N. Kuchko, *Spectrum and reflection of spin waves in magnonic crystals with different interface profiles*, Physical Review B **81**(2) (2010), doi:[10.1103/physrevb.81.024425](https://doi.org/10.1103/physrevb.81.024425).

- [13] Z. xiong Li, M. ning Wang, Y. zhuang Nie, D. wei Wang, Q. lin Xia, W. Tang, Z. ming Zeng and G. hua Guo, *Spin-wave propagation spectrum in magnetization-modulated cylindrical nanowires*, Journal of Magnetism and Magnetic Materials **414**, 49 (2016), doi:[10.1016/j.jmmm.2016.04.057](https://doi.org/10.1016/j.jmmm.2016.04.057).
- [14] M. Staño and O. Fruchart, *Magnetic nanowires and nanotubes*, In *Handbook of Magnetic Materials*, pp. 155–267. Elsevier, doi:[10.1016/bs.hmm.2018.08.002](https://doi.org/10.1016/bs.hmm.2018.08.002) (2018).
- [15] J. de la Torre Medina, T. da Câmara Santa Clara Gomes, Y. G. V. Galván and L. Piraux, *Large-scale 3-d interconnected ni nanotube networks with controlled structural and magnetic properties*, Scientific Reports **8**(1), 14555 (2018), doi:[10.1038/s41598-018-32437-8](https://doi.org/10.1038/s41598-018-32437-8).
- [16] C. D. Schuman, T. E. Potok, R. M. Patton, J. D. Birdwell, M. E. Dean, G. S. Rose and J. S. Plank, *A survey of neuromorphic computing and neural networks in hardware*, ArXiv e-prints (2017), <http://arxiv.org/abs/1705.06963v1>.
- [17] R. Streubel, L. Han, F. Kronast, A. A. Ünal, O. G. Schmidt and D. Makarov, *Imaging of buried 3D magnetic rolled-up nanomembranes*, Nano Letters **14**(7), 3981 (2014), doi:[10.1021/nl501333h](https://doi.org/10.1021/nl501333h).
- [18] J. Pablo-Navarro, C. Magén and J. M. de Teresa, *Three-dimensional core–shell ferromagnetic nanowires grown by focused electron beam induced deposition*, Nanotechnology **27**(28), 285302 (2016), doi:[10.1088/0957-4484/27/28/285302](https://doi.org/10.1088/0957-4484/27/28/285302).
- [19] J. M. D. Teresa, A. Fernández-Pacheco, R. Córdoba, L. Serrano-Ramón, S. Sanguiao and M. R. Ibarra, *Review of magnetic nanostructures grown by focused electron beam induced deposition (FEBID)*, Journal of Physics D: Applied Physics **49**(24), 243003 (2016), doi:[10.1088/0022-3727/49/24/243003](https://doi.org/10.1088/0022-3727/49/24/243003).
- [20] M. Staño, S. Schaefer, A. Wartelle, M. Rioult, R. Belkhou, A. Sala, T. O. Menteş, A. Locatelli, L. Cagnon, B. Trapp, S. Bochmann, S. Martin *et al.*, *Flux-closure domains in high aspect ratio electroless-deposited CoNiB nanotubes*, SciPost Physics **5**(4), 038 (2018), doi:[10.21468/scipostphys.5.4.038](https://doi.org/10.21468/scipostphys.5.4.038).
- [21] D. I. Shlimas, A. L. Kozlovskiy, M. V. Zdorovets, K. K. Kadyrzhanov, V. V. Uglov, I. E. Kenzhina, E. E. Shumskaya and E. Y. Kaniukov, *Obtaining of Ni nanotubes with specified properties*, Materials Research Express **5**(3), 035024 (2018), doi:[10.1088/2053-1591/aab3b2](https://doi.org/10.1088/2053-1591/aab3b2).
- [22] A. Pereira, J. Escrig, J. L. Palma, C. L. de Dicastillo, C. Patiño and M. J. Galotto, *Magnetic nanotubes obtained from atomic layer deposition coated electrospun nanofibers*, Journal of Vacuum Science & Technology B **36**(6), 061803 (2018), doi:[10.1116/1.5058706](https://doi.org/10.1116/1.5058706).
- [23] D. D. Sheka, O. V. Pylypovskyi, P. Landeros, Y. Gaididei, A. Kákay and D. Makarov, *Nonlocal chiral symmetry breaking in curvilinear magnetic shells*, Communications Physics **3**, 128 (2020), doi:[10.1038/s42005-020-0387-2](https://doi.org/10.1038/s42005-020-0387-2).
- [24] N. L. Schryer and L. R. Walker, *The motion of 180° domain walls in uniform dc magnetic fields*, Journal of Applied Physics **45**(12), 5406 (1974), doi:[10.1063/1.1663252](https://doi.org/10.1063/1.1663252).

- [25] M. Yan, C. Andreas, A. Kákay, F. García-Sánchez and R. Hertel, *Fast domain wall dynamics in magnetic nanotubes: Suppression of Walker breakdown and Cherenkov-like spin wave emission*, Applied Physics Letters **99**(12), 122505 (2011), doi:[10.1063/1.3643037](https://doi.org/10.1063/1.3643037).
- [26] M. Yan, A. Kákay, C. Andreas and R. Hertel, *Spin-Cherenkov effect and magnonic Mach cones*, Physical Review B **88**, 220412 (2013), doi:[10.1103/PhysRevB.88.220412](https://doi.org/10.1103/PhysRevB.88.220412).
- [27] J. A. Otálora, M. Yan, H. Schultheiss, R. Hertel and A. Kákay, *Curvature-induced asymmetric spin-wave dispersion*, Physical Review Letters **117**, 227203 (2016), doi:[10.1103/PhysRevLett.117.227203](https://doi.org/10.1103/PhysRevLett.117.227203).
- [28] J. A. Otálora, M. Yan, H. Schultheiss, R. Hertel and A. Kákay, *Asymmetric spin-wave dispersion in ferromagnetic nanotubes induced by surface curvature*, Physical Review B **95**(18), 184415 (2017), doi:[10.1103/physrevb.95.184415](https://doi.org/10.1103/physrevb.95.184415).
- [29] K. Zakeri, Y. Zhang, J. Prokop, T.-H. Chuang, N. Sakr, W. X. Tang and J. Kirschner, *Asymmetric Spin-Wave Dispersion on Fe(110): Direct Evidence of the Dzyaloshinskii-Moriya Interaction*, Physical Review Letters **104**, 137203 (2010), doi:[10.1103/PhysRevLett.104.137203](https://doi.org/10.1103/PhysRevLett.104.137203).
- [30] D. Cortes-Ortuno and P. Landeros, *Influence of the Dzyaloshinskii-Moriya interaction on the spin-wave spectra of thin films*, Journal of Physics: Condensed Matter **25**(15), 156001 (2013), doi:[10.1088/0953-8984/25/15/156001](https://doi.org/10.1088/0953-8984/25/15/156001).
- [31] X. Huo and Y. Liu, *The stability of a skyrmion in a nanotube*, New Journal of Physics **21**(9), 093024 (2019), doi:[10.1088/1367-2630/ab3d89](https://doi.org/10.1088/1367-2630/ab3d89).
- [32] X. Wang, X. S. Wang, C. Wang, H. Yang, Y. Cao and P. Yan, *Current-induced skyrmion motion on magnetic nanotubes*, Journal of Physics D: Applied Physics **52**(22), 225001 (2019), doi:[10.1088/1361-6463/ab0c64](https://doi.org/10.1088/1361-6463/ab0c64).
- [33] A. Korniienko, A. Kákay, D. D. Sheka and V. P. Kravchuk, *Effect of curvature on the eigenstates of magnetic skyrmions*, Physical Review B **102**, 014432 (2020), doi:[10.1103/PhysRevB.102.014432](https://doi.org/10.1103/PhysRevB.102.014432).
- [34] V. L. Carvalho-Santos, R. M. Corona, D. Altbir and S. Castillo-Sepúlveda, *Shifts in the skyrmion stabilization due to curvature effects in dome- and antidome-shaped surfaces*, Physical Review B **102**, 024444 (2020), doi:[10.1103/PhysRevB.102.024444](https://doi.org/10.1103/PhysRevB.102.024444).
- [35] A. Bogdanov and U. Röbler, *Chiral symmetry breaking in magnetic thin films and multilayers*, Physical Review Letters **87**(3), 037203 (2001), doi:[10.1103/physrevlett.87.037203](https://doi.org/10.1103/physrevlett.87.037203).
- [36] A. Thiaville, S. Rohart, É. Jué, V. Cros and A. Fert, *Dynamics of Dzyaloshinskii domain walls in ultrathin magnetic films*, EPL (Europhysics Letters) **100**(5), 57002 (2012), doi:[10.1209/0295-5075/100/57002](https://doi.org/10.1209/0295-5075/100/57002).
- [37] H. Yang, A. Thiaville, S. Rohart, A. Fert and M. Chshiev, *Anatomy of Dzyaloshinskii-Moriya interaction at Co/Pt interfaces*, Physical Review Letters **115**, 267210 (2015), doi:[10.1103/PhysRevLett.115.267210](https://doi.org/10.1103/PhysRevLett.115.267210).

- [38] A. Hubert and R. Schäfer, *Magnetic domains: the analysis of magnetic microstructures*, Springer–Verlag, Berlin (1998).
- [39] W. Wang, M. Albert, M. Beg, M.-A. Bisotti, D. Chernyshenko, D. Cortés-Ortuño, I. Hawke and H. Fangohr, *Magnon-driven domain-wall motion with the Dzyaloshinskii–Moriya interaction*, Physical Review Letters **114**(8), 087203 (2015), doi:[10.1103/physrevlett.114.087203](https://doi.org/10.1103/physrevlett.114.087203).
- [40] V. Slastikov, *Micromagnetism of thin shells*, Mathematical Models and Methods in Applied Sciences **15**(10), 1469 (2005), doi:[10.1142/S021820250500087X](https://doi.org/10.1142/S021820250500087X).
- [41] G. Gioia and R. D. James, *Micromagnetics of very thin films*, Proceedings of the Royal Society of London. Series A: Mathematical, Physical and Engineering Sciences **453**(1956), 213 (1997), doi:[10.1098/rspa.1997.0013](https://doi.org/10.1098/rspa.1997.0013).
- [42] R. V. Kohn and V. V. Slastikov, *Effective dynamics for ferromagnetic thin films: a rigorous justification*, Proceedings of the Royal Society A: Mathematical, Physical and Engineering Sciences **461**(2053), 143 (2005), doi:[10.1098/rspa.2004.1342](https://doi.org/10.1098/rspa.2004.1342).
- [43] R. V. Kohn and V. V. Slastikov, *Another thin-film limit of micromagnetics*, Archive for Rational Mechanics and Analysis **178**(2), 227 (2005).
- [44] A. Teixeira, S. Castillo-Sepúlveda, S. Vojkovic, J. Fonseca, D. Altbir, Á. Núñez and V. Carvalho-Santos, *Analysis on the stability of in-surface magnetic configurations in toroidal nanoshells*, Journal of Magnetism and Magnetic Materials **478**, 253 (2019), doi:[10.1016/j.jmmm.2019.01.093](https://doi.org/10.1016/j.jmmm.2019.01.093).
- [45] V. P. Kravchuk, U. K. Röbler, O. M. Volkov, D. D. Sheka, J. van den Brink, D. Makarov, H. Fuchs, H. Fangohr and Y. Gaididei, *Topologically stable magnetization states on a spherical shell: Curvature-stabilized skyrmions*, Physical Review B **94**, 144402 (2016), doi:[10.1103/PhysRevB.94.144402](https://doi.org/10.1103/PhysRevB.94.144402).
- [46] V. P. Kravchuk, D. D. Sheka, A. Kákay, O. M. Volkov, U. K. Röbler, J. van den Brink, D. Makarov and Y. Gaididei, *Multiplet of skyrmion states on a curvilinear defect: Reconfigurable skyrmion lattices*, Physical Review Letters **120**(6), 067201 (2018), doi:[10.1103/PhysRevLett.120.067201](https://doi.org/10.1103/PhysRevLett.120.067201).
- [47] O. V. Pylypovskiy, D. Makarov, V. P. Kravchuk, Y. Gaididei, A. Saxena and D. D. Sheka, *Chiral skyrmion and skyrmionium states engineered by the gradient of curvature*, Physical Review Applied **10**(6), 064057 (2018), doi:[10.1103/physrevapplied.10.064057](https://doi.org/10.1103/physrevapplied.10.064057).
- [48] A. Goussev, J. M. Robbins, V. Slastikov and O. A. Tretiakov, *Dzyaloshinskii–Moriya domain walls in magnetic nanotubes*, Physical Review B **93**, 054418 (2016), doi:[10.1103/PhysRevB.93.054418](https://doi.org/10.1103/PhysRevB.93.054418).
- [49] Y. Gaididei, V. P. Kravchuk and D. D. Sheka, *Curvature effects in thin magnetic shells*, Physical Review Letters **112**, 257203 (2014), doi:[10.1103/PhysRevLett.112.257203](https://doi.org/10.1103/PhysRevLett.112.257203).
- [50] K. V. Yershov, V. P. Kravchuk, D. D. Sheka, J. van den Brink and Y. Gaididei, *Spontaneous deformation of flexible ferromagnetic ribbons induced by*

- Dzyaloshinskii-Moriya interaction*, Physical Review B **100**(14), 140407(R) (2019), doi:[10.1103/PhysRevB.100.140407](https://doi.org/10.1103/PhysRevB.100.140407).
- [51] Here, we define the incomplete elliptic integrals of the first and second kinds as $F_1(\varphi, k) = \int_0^\varphi d\vartheta/\sqrt{1 - k \sin^2 \vartheta}$ and $F_2(\varphi, k) = \int_0^\varphi d\vartheta\sqrt{1 - k \sin^2 \vartheta}$, respectively. The complete elliptic integrals of the first and second kinds are defined as $K(k) = F_1(\pi/2, k)$ and $E(k) = F_2(\pi/2, k)$, respectively. Variable $\varphi = \text{am}(x, k)$ is the Jacobi's amplitude and it is related to the elliptic integral of the first kind by $F_1[\text{am}(x, k), k] = x$.
- [52] F. W. J. Olver, D. W. Lozier, R. F. Boisvert and C. W. Clark, eds., *NIST Handbook of Mathematical Functions*, Cambridge University Press, New York, NY, ISBN 0521140633 (2010).
- [53] D. D. Sheka, V. P. Kravchuk and Y. Gaididei, *Curvature effects in statics and dynamics of low dimensional magnets*, Journal of Physics A: Mathematical and Theoretical **48**(12), 125202 (2015), doi:[10.1088/1751-8113/48/12/125202](https://doi.org/10.1088/1751-8113/48/12/125202).
- [54] C. B. Muratov, V. V. Slastikov, A. G. Kolesnikov and O. A. Tretiakov, *Theory of the Dzyaloshinskii domain-wall tilt in ferromagnetic nanostrips*, Physical Review B **96**(13), 134417 (2017), doi:[10.1103/PhysRevB.96.134417](https://doi.org/10.1103/PhysRevB.96.134417).
- [55] B. A. Dubrovin, A. T. Fomenko and S. P. Novikov, *Modern Geometry — Methods and Applications: Part I. The Geometry of Surfaces, Transformation Groups, and Fields*, vol. 1 of *Graduate Texts in Mathematics 93*, Springer New York, 2 edn., ISBN 0387976639,9780387976631,3540976639 (1984).
- [56] W. Kühnel, *Differential Geometry: Curves – Surfaces – Manifolds*, American Mathematical Society, doi:[10.1090/stml/077](https://doi.org/10.1090/stml/077) (2015).
- [57] *The Object Oriented MicroMagnetic Framework*, Developed by M. J. Donahue and D. Porter mainly, from NIST.
- [58] D. Cortés-Ortuño, M. Beg, V. Nehruji, R. A. Pepper and H. Fangohr, *OOMMF extension: Dzyaloshinskii-Moriya interaction (DMI) for crystallographic classes T and O*, doi:[10.5281/zenodo.1196820](https://doi.org/10.5281/zenodo.1196820) (2018).
- [59] S. X. Huang and C. L. Chien, *Extended skyrmion phase in epitaxial FeGe(111) thin films*, Physical Review Letters **108**, 267201 (2012), doi:[10.1103/PhysRevLett.108.267201](https://doi.org/10.1103/PhysRevLett.108.267201).